

Submillimeter spectroscopy of tilted $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$ films: observation of a mixed a-c excitation

A. Pimenov¹, A. V. Pronin¹, A. Loidl¹, A. Kampf², S. I. Krasnovobodtsev³, and V. S. Nozdrin³

¹*Experimentalphysik V, EKM, Universität Augsburg, 86135 Augsburg, Germany*

²*Theoretische Physik III, EKM, Universität Augsburg, 86135 Augsburg, Germany*

³*Lebedev Physics Institute, Russ. Acad. Sciences, 117942 Moscow, Russia*

The anisotropic conductivity of a series of tilted $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$ thin films was measured by quasi-optical spectroscopy in the frequency range $3\text{ cm}^{-1} < \nu < 40\text{ cm}^{-1}$. Two characteristic features have been observed in the low-temperature transmission spectra. The first one at $\nu = 12\text{ cm}^{-1}$ was shown to reflect the c-axis plasma frequency of $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$. The second feature represents a new mixed ab-plane/c-axis excitation. The frequency of this resonance may be changed in a controllable way by rotating the polarization of the incident radiation.

Among the cuprate superconductors, $\text{Nd}_{2-x}\text{Ce}_x\text{CuO}_4$ (NCCO) has attracted considerable interest because it can be considered as electron-doped compound [1], which reveals the (T') tetragonal structure and is extremely two-dimensional [1,2]. Earlier in-plane microwave experiments on NCCO [3–5] appeared to be consistent with the conventional s-wave BCS predictions. However, recent data including flux quantization [6] and penetration depth at microwaves [7] and at radiowaves [8] provided strong experimental evidence of d-wave symmetry of the pairing state.

In contrast to a number of ab-plane experiments, there exists only few information concerning the c-axis properties of NCCO due to small dimensions of the samples along the c-axis. Most experiments on c-axis dynamics [9,10] were carried out using ceramic NCCO samples. Alternatively, the method of grazing-incidence reflection is known to be powerful in extracting the c-axis properties of strongly anisotropic superconductors [11]. The experiments using instead of the grazing reflection a tilted sample [12] and the normal-incidence geometry may be considered as modification of this method.

In this letter we present the results of submillimeter-wave ($3\text{ cm}^{-1} < \nu < 40\text{ cm}^{-1}$) experiments on tilted $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$ films at low temperatures. The spectra reveal two new features below the superconducting transition, which could be identified as: i) plasma resonance along the c-axis and ii) mixed ab-plane/c-axis excitation. Using the measurements at different polarizations of the incident radiation it was possible to separate the effective conductivity at a tilted angle into components within the ab-plane and along the c-axis.

The experiments were carried out on different $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$ films yielding similar results. For simplicity, the results from only one film are presented. The films were prepared using a two-beam-laser deposition on yttrium stabilized ZrO_2 substrates [13]. X-ray analysis revealed the c-axis orientation of the films. The substrate of the presented film was tilted from (001) plane by an angle $\alpha = 0.8^\circ \pm 0.4^\circ$. Therefore, the film was also

tilted by the same angle from the ideal c-axis orientation. The ac-susceptibility measurements revealed a narrow superconducting transition ($\Delta T[10\% - 90\%] = 0.9\text{ K}$) with the onset temperature of 20.1 K . The film thickness, estimated from the deposition time, was $d = 170\text{ nm}$.

The transmission experiments in the frequency range $6\text{ cm}^{-1} < \nu < 40\text{ cm}^{-1}$ were carried out in a quasi-optical arrangement [14], which allows both the measurements of transmission and phase shift of a film on a substrate. The properties of the substrate were determined in a separate experiment. Utilizing the Fresnel optical formulas for the complex transmission coefficient of the substrate-film system, the absolute values of the complex conductivity $\sigma^* = \sigma_1 + i\sigma_2$ were determined directly from the observed spectra without any approximations. The radiation in this method is continuously tunable in frequency and is linearly polarized. This allows to perform experiments for different directions of the currents, induced in the sample. The geometry of the transmission experiment is represented in the inset of Fig. 1.

Fig. 1 shows the transmission spectra of a $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$ thin film at $T = 6\text{ K}$ and at $T \approx T_C$. A new feature, that can be observed in the spectra of the superconducting state, is the appearance of a transmission peak at $\nu = 12\text{ cm}^{-1}$. This feature may be called "antiresonance" as it corresponds to an *increase* in transmission. In addition to this antiresonance, a suppression of the low-temperature transmission is seen in the frequency range $18\text{ cm}^{-1} < \nu < 30\text{ cm}^{-1}$. This suppression corresponds to a broad resonance and is somewhat masked by the interference pattern, caused by the substrate.

Fig. 2 shows the effective conductivity of the film as calculated from transmission and phase shift spectra for $T = 6\text{ K}$. Because the exact expressions for the complex transmission coefficient were used, the substrate interference patterns are absent in this presentation. The effective conductivity is shown for different orientations of incident radiation and is labeled by the angle φ (inset of Fig. 1).

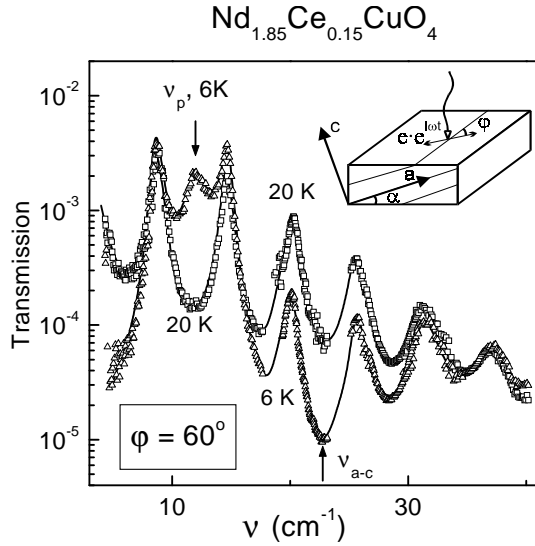


FIG. 1. Submillimeter-wave transmission spectra of a $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$ film at $T = T_C$ (20K) and at $T=6\text{K}$. Lines are drawn to guide the eye. Arrows indicate the position of the c-axis plasma frequency and of a mixed a-c excitation. The inset shows the geometry of the transmission experiment.

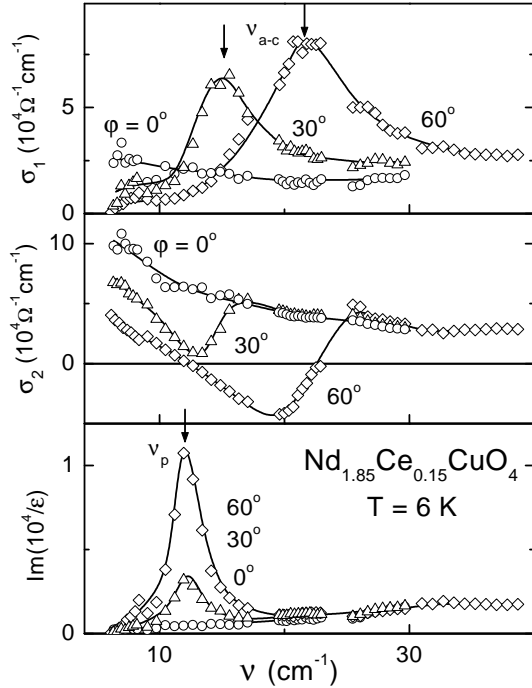


FIG. 2. Low-temperature conductivity spectra of a $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$ film for different orientations of the incident radiation. Lines are drawn to guide the eye. Upper panel: σ_1 . Middle panel: σ_2 . Lower panel: Imaginary part of the loss function $\text{Im}(1/\epsilon)$. Arrows indicate the position of the c-axis plasma frequency and of the mixed a-c excitation.

The comparison of Fig. 1 and Fig. 2 clearly shows that a zero-crossing of σ_2 and a peak in the loss function $\text{Im}(1/\epsilon)$ correspond to the antiresonance at $\nu = 12 \text{ cm}^{-1}$.

The suppression of the transmission at $\nu \sim 23 \text{ cm}^{-1}$ yields a peak in the real part of conductivity. Interestingly, both features have completely different dependence upon the rotating of the polarization plane (φ). As will be seen below, the antiresonance at 12 cm^{-1} corresponds to the c-axis plasma frequency and is therefore independent upon the polarization of the incident radiation. Contrary, the peak at 23 cm^{-1} ($\varphi = 60^\circ$) represents the mixed ab-plane/c-axis excitation. The degree of mixing may be controlled by the geometry of the experiment, which explains the φ -dependence of the peak position.

The spectra for $\varphi = 0^\circ$ corresponds to currents flowing only within the ab-planes and resemble the spectra of a superconductor below the gap frequency: σ_1 has only a weak frequency dependence and is suppressed by approximately a factor of three compared to the normal-state conductivity, σ_2 is strongly enhanced compared to the normal state and reveals approximately a $1/\omega$ frequency dependence. From its slope the low-frequency penetration depth may be estimated as $\lambda_{ab}(6\text{K}) = 230 \pm 30 \text{ nm}$.

In order to calculate the effective conductivity of a tilted sample, consider a free-standing film of thickness d in a uniform electromagnetic field $Ee^{-i\omega t}$ as shown in the inset of Fig. 1. For simplicity, the film is assumed to be thin compared to the penetration depth, $d \ll \lambda$. In this case the current and field distribution may be considered to be uniform. Taking into account the charges formed at the surface, the following equation for the effective conductivity is obtained:

$$\sigma_{eff} = \frac{-i\epsilon_0\omega(\sigma_a \cos^2 \alpha + \sigma_c \sin^2 \alpha) + \sigma_a \sigma_c}{-i\epsilon_0\omega + \sigma_a \sin^2 \alpha + \sigma_c \cos^2 \alpha} \quad (1)$$

Here ϵ_0 is the permittivity of free space, σ_a (σ_c) is the complex conductivity in the ab-plane (along the c-axis), and ω is the angular frequency.

Within the approximation $\alpha \approx \sin \alpha \ll 1$ and $|\sigma_a| \gg |\sigma_c|$, the Eq. (1) can be written as:

$$\sigma_{eff} = \frac{\sigma_a(\sigma_c - i\epsilon_0\omega)}{\sigma_a\alpha^2 + (\sigma_c - i\epsilon_0\omega)} \quad (2)$$

Two simple conclusions can be immediately drawn from this expression, if the real parts of the conductivities (σ_{1a}, σ_{1c}) are only weakly frequency dependent: i) the effective conductivity should reveal a peak if $\text{Im}[\sigma_a\alpha^2 + (\sigma_c - i\epsilon_0\omega)] = 0$ and ii) the inverse conductivity shows a peak (i.e. longitudinal resonance) if $\text{Im}[\sigma_c - i\epsilon_0\omega] = 0$. Assuming that only the high-frequency dielectric constant ($-i\epsilon_0\epsilon_{c,\infty}\omega$) and the superconducting condensate ($in_s e^2/m_c \omega$) contribute to the low-temperature c-axis conductivity, the critical frequency in the case ii) can be estimated $\omega_0^2 = n_s e^2/[m_c(\epsilon_\infty + 1)]$, which closely resembles the expression for the screened plasma frequency. Evidently, the expression for ω_0^2 does not depend upon the tilt angle. On the contrary, a substantial angular dependence is expected for the resonance at ω_1 . The change of the tilt angle may be easily achieved experimentally by rotating the polarization of the incident radiation.

In this case the effective tilt angle may be obtained as $\alpha_{eff} = \alpha_0 \sin \varphi$, where $\varphi = 0^\circ$ corresponds to the polarization within the ab-plane.

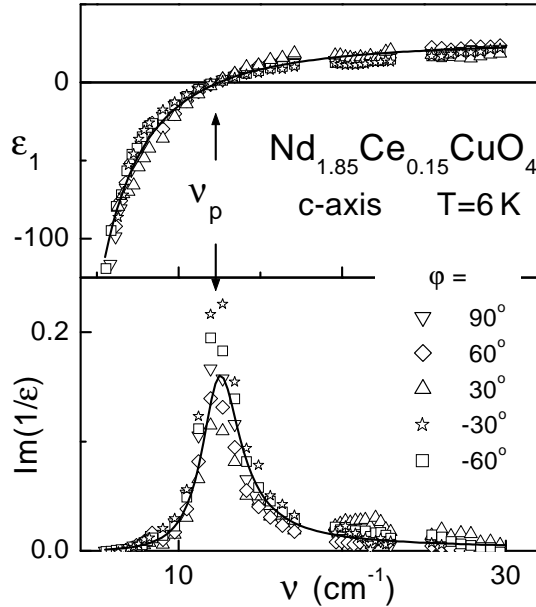


FIG. 3. Dielectric function of $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$ film along the c-axis. Upper panel: ϵ_1 . Lower panel: Imaginary part of the loss function $\text{Im}(1/\epsilon^*)$. Lines are calculated within the following assumptions: i) σ_{1c} is frequency independent and ii) only high frequency dielectric constant ϵ_∞ and superconducting condensate $-(\lambda_c c/\omega)^2$ contribute to ϵ_1 (see text).

Using Eq. (1), it is possible to calculate the c-axis properties of $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$ film. The dielectric function along the c-axis, $\epsilon_c^* = i\sigma_c/\omega\epsilon_0$, obtained in this way, is presented in Fig. 3. Supporting the concept used, the data for all polarizations φ collapse into a single curve. It should be noted, that the uncertainty in determination of α_0 represents the most relevant source of errors in the determination of ϵ_c^* . However, the variation of this angle influences only the absolute values of the conductivity but leaves the overall frequency dependence unchanged.

As demonstrated in Fig. 3, the high-frequency ($\nu > 20 \text{ cm}^{-1}$) c-axis dielectric constant of $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$ is positive which can be ascribed to the phonon contribution. A superconducting response becomes dominating for $\nu < 15 \text{ cm}^{-1}$ from which the low-frequency penetration depth may be estimated as $\lambda_c(6\text{K}) = 24 \pm 8 \mu$. From the zero crossing of the dielectric constant, the screened plasma frequency can be determined as $\nu_p = 12 \text{ cm}^{-1}$. This value is in excellent agreement with the powder data of Shibata and Yamada [9] and with recent results of Singley et al. [15].

In conclusion, the anisotropic properties of a series of slightly tilted $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$ thin films were mea-

sured in the submillimeter frequency range. Two new features were observed in the low-temperature transmission spectra which showed different polarization dependencies. The antiresonance at $\nu = 12 \text{ cm}^{-1}$ corresponds to the c-axis plasma frequency of $\text{Nd}_{1.85}\text{Ce}_{0.15}\text{CuO}_{4-\delta}$. The second resonance represents a mixed ab-plane/c-axis excitation. The frequency of this resonance can be changed in a controllable way by rotating the polarization of the incident radiation.

We acknowledge stimulating discussion with R. Hackl and W. N. Hardy. This work was supported by BMBF (13N6917/0 - EKM)

-
- [1] Y. Tokura, H. Takagi, and S. Uchida, *Nature* **337**, 345 (1989).
 - [2] Y. Hidaka and M. Suzuki, *Nature* **338**, 635 (1989).
 - [3] A. Andreone, A. Cassinese, A. Di Chiara, R. Vaglio, A. Gupta, and E. Sarnelli, *Phys. Rev. B* **49**, 6392 (1994).
 - [4] S. M. Anlage, D.-H. Wu, J. Mao, S. N. Mao, X. X. Xi, T. Venkatesan, J. L. Peng, and R. L. Greene, *Phys. Rev. B* **50**, 523 (1994).
 - [5] D.-H. Wu, J. Mao, S. N. Mao, J. L. Peng, X. X. Xi, T. Venkatesan, R. L. Greene, and S. M. Anlage, *Phys. Rev. Lett.* **70**, 85 (1993).
 - [6] C. C. Tsuei and J. R. Kirtley, cond-mat/0002341.
 - [7] J. D. Kokales, P. Fournier, L. V. Mercaldo, V. V. Talanov, R. L. Greene, and S. M. Anlage, cond-mat/0002300.
 - [8] R. Prozorov, R. W. Giannetta, P. Fournier, and R. L. Greene, cond-mat/0002301.
 - [9] H. Shibata and T. Yamada, *Phys. Rev. B* **54**, 7500 (1996); *ibid.* **56**, 14275 (1997).
 - [10] E. T. Heyen, G. Kliche, W. Kress, W. König, M. Cardona, E. Rampf, J. Prade, U. Schröder, A. D. Kulkarni, F. W. de Wette, S. Pinöl, D. McK. Paul, E. Morán, and M. A. Alario-Franko, *Sol. State Comm.* **74**, 1299 (1990).
 - [11] J. Schützmann, H. S. Somal, A. A. Tsvetkov, D. van der Marel, G. E. Koops, N. Kolesnikov, Z. F. Ren, J. H. Wang, E. Brück, and A. A. Menovsky, *Phys. Rev. B* **55**, 11118 (1997).
 - [12] W. Markowitsch, C. Stockinger, W. Lang, K. Bierleutgeb, J. D. Pedarnig, and D. Bäuerle, *Appl. Phys. Lett.* **71**, 1246 (1997).
 - [13] V. S. Nozdrin, S. I. Krasnosvobodtsev, O. M. Ivanenko, P. V. Bratukhin, and K. V. Mitsen, *Tech. Phys. Lett.* **22**, 996 (1996).
 - [14] G. V. Kozlov and A. A. Volkov in *Millimeter and Submillimeter Wave Spectroscopy of Solids*, Ed. by G. Grüner (Springer, Berlin, 1998), p. 51.
 - [15] E. J. Singley, A. S. Katz, S. I. Woods, R. C. Dynes, D. N. Basov, K. Kurahashi, and K. Yamada, APS March Meeting, Minneapolis 2000.