

Soft x-ray spectroscopy experiments on the near K-edge of B in MB₂ (M=Mg, Al, Ta, and Nb)

J. Nakamura, N. Yamada, and K. Kuroki

Department of Applied Physics and Chemistry, The University of Electro-Communications, Chofu-shi, Tokyo 182-8585, Japan

T.A. Callcott

Department of Physics, University of Tennessee, Knoxville, TN 37996

D.L. Ederer

Department of Physics, Tulane University, New Orleans, LA 70118

J.D. Denlinger

Advanced Light Source, Lawrence Berkeley National Laboratory, Berkeley, CA 94720

R.C.C. Perera

Center for X-ray Optics, Lawrence Berkeley National Laboratory, Berkeley, CA 94720

(Received)

Soft X-ray absorption and emission measurements are performed for the K- edge of B in MB₂ (M=Mg, Al, Ta and Nb). Unique feature of MgB₂ with a high density of B $2p_{xy}(\sigma)$ -state below and above the Fermi edge, which extends to 1 eV above the edge, is confirmed. In contrast, the B $2p$ density of states in AlB₂ and TaB₂, both of occupied and unoccupied states, decreased linearly towards the Fermi energy and showed a dip at the Fermi energy. Furthermore, there is a broadening of the peaks with $p\sigma$ -character in XES and XAS of AlB₂, which is due to the increase of three dimensionality in the $p\sigma$ -band in AlB₂. The DOS of NbB₂ has a dip just below the Fermi energy. The present results indicate that the large DOS of B- $2p\sigma$ states near the Fermi energy are crucial for the superconductivity of MgB₂.

71.20.-b, 74.25.Jb, 78.70.DM, 78.70.En

Since the discovery of superconductivity in MgB₂ with a transition temperature, T_c , of 39 K by Nagamatsu *et al.*, [1] large number of researches from experimental [2,3] and theoretical point [4] of view have been performed, to explain the superconducting properties and mechanism of this new high- T_c superconductor. The observed T_c of ~ 40 K seems to exceed the upper bound of the transition temperature (~ 30 K) estimated for conventional BCS-type superconductors. Hence it is very important to clarify whether its superconducting mechanism is conventional or not. In this context, Bud'ko *et al.* reported a boron isotope effect of $\alpha=0.26$, which suggests that phonons are playing an important role in the occurrence of superconductivity in this compound. [5] Tunneling results indicate an s -wave nature of superconductivity. [6] Theoretically, band calculations have suggested strong electron-phonon coupling. [7–13] All this evidence supports the conventional BCS-type superconductivity in MgB₂. However, a detailed analysis of the specific heat and recent high resolution XPS experiment indicate that the superconducting gap must be anisotropic or two-band-like. [14,15]

In order to clarify the mechanism of high T_c superconductivity in MgB₂, it is important to investigate the difference in the electronic states between MgB₂ and other related compounds: MB₂(M=Al, Ta and Nb). MgB₂ is

a superconductor with $T_c = 39$ K as mentioned, while AlB₂ has been reported to be a non-superconductor. [16] TaB₂ has been reported as a superconductor of 9.5 K by Kaczorowski *et al.*, [17] while it has recently been reported to be a non-superconductor by Gasparov *et al.* [18] T_c of NbB₂ is also controversial: $T_c=6$ K by Cooper *et al.* [19], 5.2 K by Akimitsu *et al.* [20] and 0.62 K by Leyarovskaya and Leyarovski [21], while Gasparov reported it as a non-superconductor. [18]

In the present study, we present X-ray emission (XES) and absorption spectra (XAS) near the boron (B) K edge in MB₂ (M=Mg, Al, Ta and Nb). XAS was measured by both the total fluorescence yield (TFY) and the total electron yield (TEY) measurements at the same time. XES and XAS studies are powerful tools to probe the filled and empty electronic states of a specific orbital. The reason we choose boron is because the band calculations for MgB₂ indicate that the bands near the Fermi energy are mainly composed from boron $2p$ orbitals. By measuring the dipole transition between $2p$ states and $1s$ core level of boron, we can specifically probe the partial density of states (PDOS) of B $2p$ states. Furthermore, XES and XAS by TFY are not surface sensitive in contrast to photo-electron spectroscopy.

The commercial specimens from Rare-Metallic Co. were used as samples of MB₂(M=Mg, Al, Ta and Nb).

The specimens were examined by powder X-ray diffraction (XRD) measurements.

XRD measurements showed single phase MgB_2 type pattern for all specimens. The dc magnetizations were measured with a SQUID magnetometer in the temperature range from 1.8 to 100 K. The temperature dependencies of the susceptibility indicate that the superconducting transition temperature of about 38 K for MgB_2 , and no superconducting transition for TaB_2 , NbB_2 and AlB_2 above 1.8 K.

The soft X-ray emission and absorption spectroscopies were performed at BL-8.0.1 of Advanced Light Source (ALS) in LBNL. The resolutions of emission and absorption spectra are 0.3 and 0.1 eV, respectively. In order to calibrate energy, XAS by TEY were also measured at the well calibrated beam line BL- 6.3.2 of the ALS. The XAS for all MB_2 compounds obtained by TEY shows a sharp peak at about 193.8 eV, which is attributed to boron oxides, [22] while the XAS obtained by TFY shows no detectable peak at about 194 eV. These results indicate that there is a small amount of boron oxide only on the surface, but not inside the bulk. Here, we present the XAS obtained by TFY, so the presented results are free from the influence of boron oxides.

Figure 1(a) shows XES ($\circ$) and XAS ($\bullet$) of MgB_2 . The sharp decrease of XES and XAS at about 186.3 eV is attributed to the Fermi energy measured from 1s core level. The solid line in Fig. 1(b) is the boron PDOS obtained from a band structure calculation [9], where we have taken into account the effect of the instrumental resolution by gaussian broadening. The intensities of experimental XES and XAS in Fig. 1(a) are scaled to the theoretical PDOS in the energy region, $E \leq 182$ eV for XES and $187 \text{ eV} \leq E \leq 191$ eV for XAS. The sum of the experimental XES and XAS are also plotted in Fig. 1(b). It can be seen that the overall feature of both XES and XAS, including the existence of a large PDOS around the Fermi energy, are remarkably well reproduced by the band structure calculation, enabling us to attribute each observed structure to $p\pi$ and/or $p\sigma$ states. Namely, the existence of peaks A and B, which is consistent with recent studies [2,3], are characteristic of bonding $p\sigma$ states. [9,11] The region C in the energy range from 187 to 191 eV is attributed to the $p\pi$ states. A sharp peak D at about 192 eV in XAS is reported to be a resonance peak of $p\pi^*$ state [3], and also corresponds to antibonding $p\sigma^*$ state predicted by a band calculation. Thus peak D contains both the $p\sigma^*$ and resonance state of $p\pi^*$ states.

Figure 2(a) shows XES and XAS of AlB_2 . The intensity of XES is normalized so that the area intensity coincides with that for MgB_2 below E_F , while the intensity of XAS is scaled so that the intensity in the high energy region, $E \geq 198$ eV, coincides with that for MgB_2 . In the high energy region, XAS shows no strong characteristic peaks. A broad tail of XES below 183 eV is similar to that of MgB_2 , but the value of E_F shifts to be 187.5 eV. The form of XES of AlB_2 is broad compared to that of MgB_2 . Figure 2(b) shows experimental PDOS

derived from the sum of XES and XAS. A dip is observed at about 188 eV near the Fermi energy, indicating that the B 2p PDOS around the Fermi energy is drastically reduced compared to that in MgB_2 . This is the major difference between MgB_2 and AlB_2 .

This difference can be understood from results of the band calculation for AlB_2 . [12] Namely, there are several factors that make the boron 2p PDOS around the Fermi level in AlB_2 much smaller than in MgB_2 . First of all, the bonding σ bands, whose tops are located above the Fermi level in MgB_2 , are fully filled in AlB_2 . Secondly, the Fermi level is located at a point where the top of the bonding and bottom of the antibonding π bands touch with each other at the K point. If the system were purely two-dimensional, this would be a point where the DOS vanishes linearly as a function of energy. Although the π band is three dimensional, the above two-dimensional property remains because the system is anisotropic.

The difference between MgB_2 and AlB_2 can qualitatively be understood within a simple rigid band model, namely by simply shifting the Fermi energy as mentioned above. To be more precise, there are some quantitative differences, whose origin seems to lie beyond a rigid band picture. Namely, in AlB_2 , the intensity of XAS just above the dip is larger than that in MgB_2 , while the intensity of peaks A and D is suppressed. Looking again into the band calculation results, these features may be attributed to the increase of three dimensionality in AlB_2 .

The XES and XAS of TaB_2 are similar to those for AlB_2 except for a shift in the Fermi energy [Fig. 3] up to 188.6 eV, owing to a larger band filling compared with AlB_2 . The B 2p PDOS at the Fermi energy is similar to that for AlB_2 , so if TaB_2 is indeed superconducting, the difference between these two compounds should lie elsewhere.

Figure 4 shows XES and XAS of NbB_2 . The Fermi energy is almost the same as that of TaB_2 , but a considerable amount of DOS below the Fermi energy is observed. A dip is also observed at ~ 187 eV and is lower than the Fermi energy. The form of the XAS indicates a flat PDOS above 189 eV and shows a small peak D. The PDOS around the Fermi energy is not so small. The character of the states near the Fermi energy cannot be identified from the present results.

To summarize, the most characteristic feature in MgB_2 as compared to other related materials is the large B 2p PDOS around the Fermi level. Since this is partially attributed to the existence of the $p\sigma$ bonding band at the Fermi level, one may be tempted to consider that the $p\sigma$ band plays a crucial role in the occurrence of superconductivity in MgB_2 . [4] This is indeed probable, but is not necessarily the case because the $p\pi$ band filling is also different between MgB_2 and other materials as mentioned above, which should result in a large difference in the shape of the $p\pi$ band Fermi surfaces. Let us note that the shape of the Fermi surfaces can play an essential role in the occurrence of superconductivity. For example, in those mechanisms that exploit nesting between the Fermi

surfaces of bonding and antibonding π bands, [23–25] the shape of the Fermi surfaces (namely the π band filling) is crucial. We believe that further studies are necessary to clarify this point.

We express our thanks to Dr. H. Takenaka of NTT-AT, Dr. Y. Muramatsu of SPring8, Japan Atomic Energy Research Institute (JAERI) and Dr. E. Gullikson of CXRO-LBNL for their helpful support with spectroscopic measurements. We thank Professor S. Suzuki for sending ref. [12] prior to publication. We also thank Professor K. Kohn of Waseda University for the support susceptibility measurement. We would like to thank Professor K. Asai of University of Electro-Communications and Professor J. Akimitsu of Aoyama Gakuin University for useful discussions. This work was supported by Office of Basic Energy Science of the Department of Energy under contract Nos. DE-AC03-76SF00098 and W-7405-Eng-48 and National Science Foundation (NSF) Grant No. DMR-9017996 to the University of Tennessee. D.L.E. and T.A.C. also wish to acknowledge support from NSF Grant DMR-9801804.

FIG. 1. (a) The observed XES (○) and XAS (●) spectra of MgB_2 . (b) The sum of XES and XAS (□) and the theoretical PDOS (solid line) derived from FLAPW method broadened with experimental resolution.

FIG. 2. (a) The observed XES (○) and XAS (●) spectra of AlB_2 . (b) The sum of XES and XAS (□).

FIG. 3. The observed XES (○) and XAS (●) spectra of TaB_2 .

FIG. 4. The observed XES (○) and XAS (●) spectra of NbB_2 .

-
- [1] J. Nagamatsu, N. Nakagawa, T. Muranaka, Y. Zenitani and J. Akimitsu: Nature (London) **410** (2001) 63.
 - [2] Z. Kurmaev, I.I. Lyakhovskaya, J. Kortus, N. Miyata, M. Demeter, M. Neumann, M. Yanagihara, M. Watanabe, T. Muranaka, J. Akimitsu, cond-mat/0103487.
 - [3] T.A. Callcott, L. Lin, G.T. Woods, G.P. Zhang, J.R.Thompson, M. Paranthaman, D.L. Ederer, cond-mat/0103593.
 - [4] There are several proposals of superconducting mechanism that consider the σ band crucial, i.e., M. Imada, cond-mat/0103006.
 - [5] S.L. Bud'ko, G. Lapertot, C. Petrovic, C.E. Cunningham, N. Anderson, and P.C. Canfield, Phys. Rev. Lett. **86**, 1877 (2001).
 - [6] H. Schmidt, J.F. Zasadzinski, K.E. Gray, and D.G. Hinks, Phys. Rev. B **63**, 220504 (2001).
 - [7] J. Kortus, I.I. Mazin, K.D. Belashchenko, V.P. Antropov, L.L. Boyer, Phys. Rev. Lett. **86**, 4656 (2001).
 - [8] K. D. Belashchenko, M. van Schilfgaarde, and V. Antrov, cond-mat/0102290.
 - [9] G. Satta, G. Profeta, F. Bernardini, A. Continenza and S. Massidda, cond-mat/0102358.
 - [10] M. An and W. E. Pickett, Phys. Rev. Lett. **86**, 4366 (2001).
 - [11] A. Reyes-Serrato and D.H. Galvan, cond-mat/0103477.
 - [12] S. Suzuki, S. Higai, and K. Nakao, cond-mat/0102484, to be published in J. Phys. Soc. Jpn. No.5 (2001).
 - [13] Y. Kong, O.V. Dolgov, O. Jepsen and O.K. Andersen: Phys. Rev. B **64**, 020501 (2001).
 - [14] Y. Wang, T. Plackowski, and A. Junod, cond-mat/0103181.
 - [15] S. Tsuda, T. Yokoya, T. Kiss, Y. Takano, K. Togano, H. Kitou, H. Ihara, and S. Shin, cond-mat/0104489.
 - [16] J.S. Slusky, N. Rogado, K.A. Regan, M.A. Hayward, P. Khalifah, T. He, K. Inumaru, S.M. Loureiro, M.K. Haas, H.W. Zandbergen, R.J. Cava, Nature(London) **410** (2001) 343.
 - [17] D. Kaczorowski, A.J. Zaleski, O.J. Zogal, J. Klamut, cond-mat/0103571.
 - [18] V.A. Gasparov, N.S. Shidorov, I.I. Zver'kova, and M.P. Kulakov, cond-mat/0104323.
 - [19] A.S. Cooper, E. Corenzwit, L.D. Longinotti, B.T. Matthias, and W.H. Zachariasen, Proc. Nat. Acad. Sci. **67**, 313 (1970).
 - [20] J. Akimitsu et al., Abstract for 2001 Annual meeting of Physical Society of Japan, Vol 3. p.533.
 - [21] L. Leyarovskaya and E. Leyarovski, J. Less Common Met. **67**, 249 (1979).
 - [22] J.J. Jia, J.H. Underwood, E.M. Gullikson, T.A. Callcott, and R.C.C. Perera, J. Elec. Spec. and Related Phen. **80**, 509 (1996).
 - [23] It has been argued in K. Kuroki and R. Arita, to be published in Phys. Rev. B (cond-mat/0101427), that inter-Fermi-surface nesting may in general lead to high T_c superconductivity.
 - [24] N. Furukawa, cond-mat/0103184.
 - [25] K. Yamaji, cond-mat/0103431.

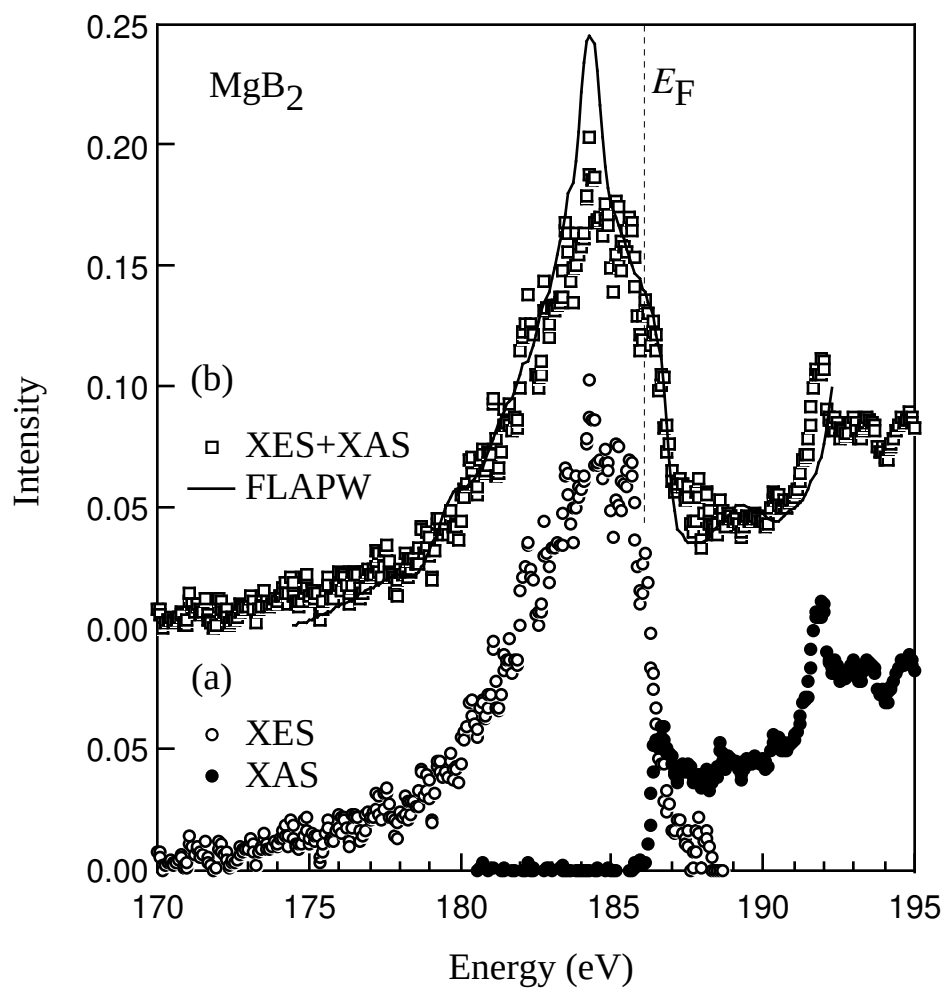


Fig. 1

J. Nakamura et al.

Title: Soft x-ray spectroscopy experiments on the near K-edge of B in MB₂ (M=Mg, Al, Ta, and Nb)

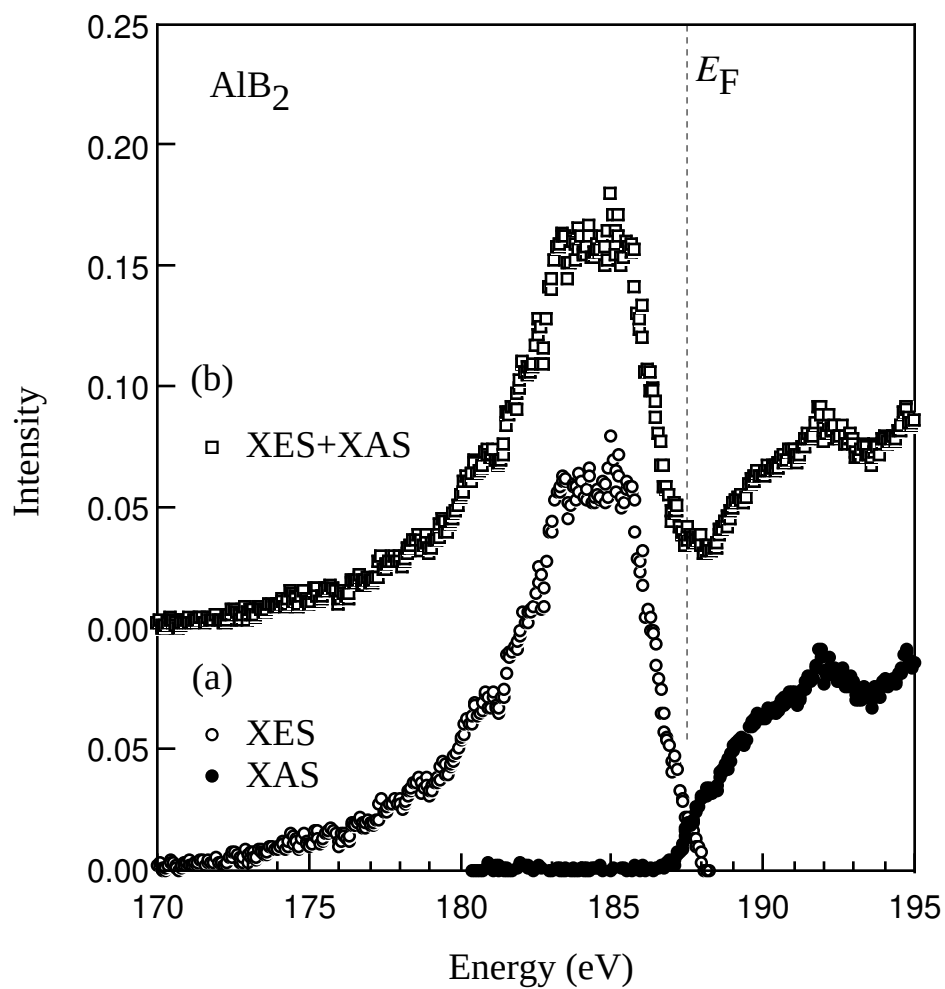


Fig. 2

J. Nakamura et al.

Title: Soft x-ray spectroscopy experiments on the near K-edge of B in MB_2 (M=Mg, Al, Ta, and Nb)

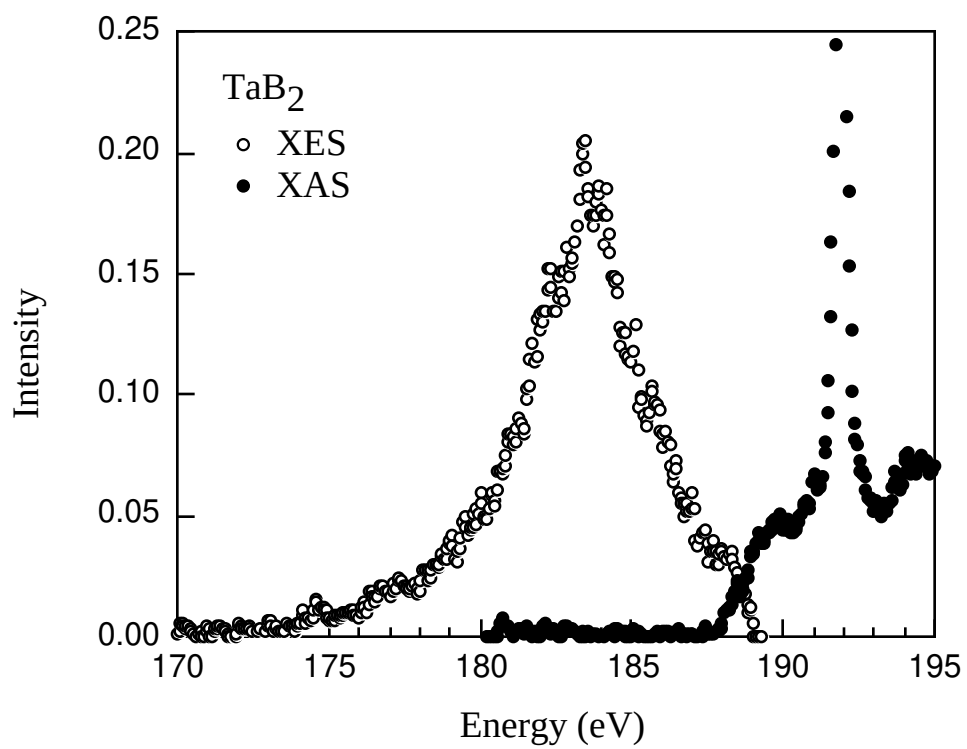


Fig. 3

J. Nakamura et al.

Title: Soft x-ray spectroscopy experiments on the near K-edge of B in MB₂ (M=Mg, Al, Ta, and Nb)

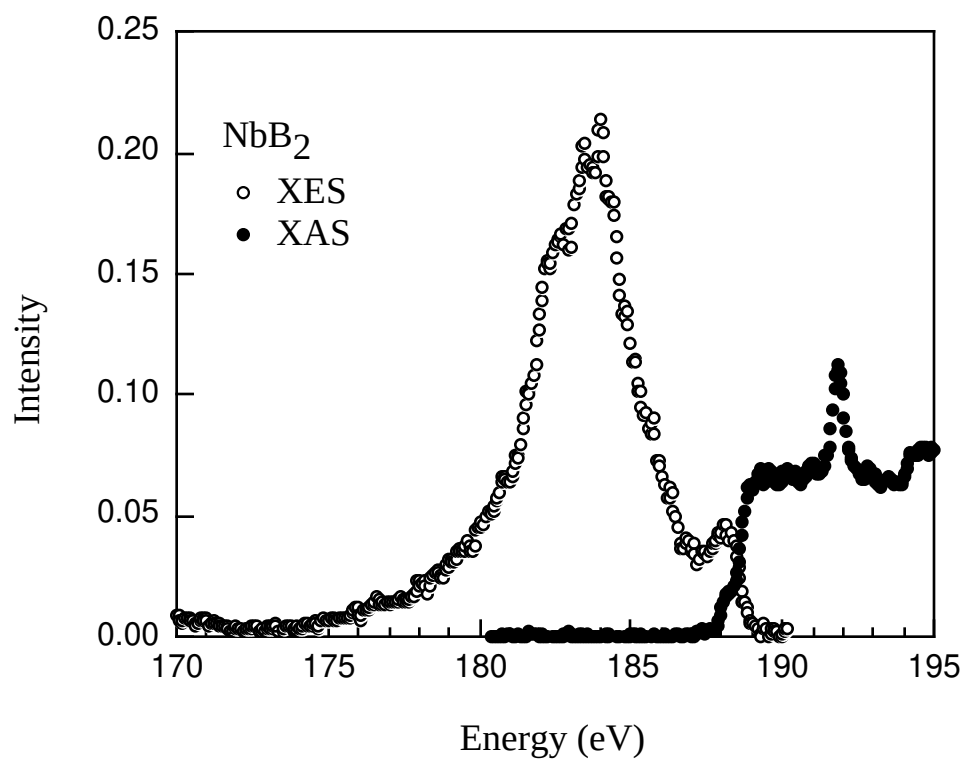


Fig. 4

J. Nakamura et al.

Title: Soft x-ray spectroscopy experiments on the near K-edge of B in MB₂ (M=Mg, Al, Ta, and Nb)