Coupling to haloform molecules in intercalated C_{60} ?

Erik Koch* and Olle Gunnarsson

Max-Planck Institut für Festkörperforschung, Heisenbergstraße 1, 70569 Stuttgart, Germany

(Dated: July 24, 2002)

For field-effect-doped fullerenes it was reported that the superconducting transition temperature T_c is markedly larger for $C_{60} \cdot 2CHX_3$ (X=Cl, Br) crystals, than for pure C_{60} . Initially this was explained by the expansion of the volume per C_{60} -molecule and the corresponding increase in the density of states at the Fermi level in the intercalated crystals. On closer examination it has, however, turned out to be unlikely that this is the mechanism behind the increase in T_c . An alternative explanation of the enhanced transition temperatures assumes that the conduction electrons not only couple to the vibrational modes of the C_{60} -molecule, but also to the modes of the intercalated molecules. We investigate the possibility of such a coupling. We find that, assuming the ideal bulk structure of the intercalated crystal, both a coupling due to hybridization of the molecular levels, and a coupling via dipole moments should be very small. This suggests that the presence of the gate-oxide in the field-effect-devices strongly affects the structure of the fullerene crystal at the interface.

PACS numbers: 74.70.Wz

In a series of papers Schön and collaborators announced a number of amazing results: Doping pure C_{60} using a field-effect device, they found superconductivity up to temperatures of 11 K for electron¹ and 52 K for hole-doping.² Replacing pure C_{60} by crystals intercalated with chloroform (CHCl₃) and bromoform (CHBr₃), they reported transition temperatures of about 18 and 25 K for electron-doping, and 80 and 117 K for hole-doping, respectively.³ Initially it was speculated that this increase in T_c was due to the expansion of the lattice upon intercalation of the CHX₃-molecules and the correspondingly larger density of states (DOS) at the Fermi level³— a mechanism similar to that seen in the alkali doped fullerenes.⁴

While the alkali doped fullerenes are bulk superconductors, the induced charge in the field-effect-doped materials is believed to be essentially confined to a single C_{60} -monolayer.⁵ This monolayer is believed to be a [111]-layer for pure C_{60} and a [010]-layer for $C_{60} \cdot 2CHX_3$. Analyzing the low-temperature phase of the haloform intercalated fullerenes shows, that the expansion of the unit cell volume induced by the intercalated molecules mainly results from an increase in the distance between these lay-

ers, while the density of states in these layers does not correlate with the observed T_c .⁶

It was proposed that the transition temperature increases not because of an enhanced density of states at the Fermi level, but because of an additional coupling to the intercalated CHX₃ (X=Cl, Br) molecules.⁷ Here we ask if indeed there is such a coupling. Possible mechanisms are (i) hybridization of the molecular levels with the HOMO/LUMO of C₆₀ and (ii) coupling via the dipole moment or the polarizability of the intercalated molecules. We find that the overlap between the states of the intercalated molecules with the relevant orbitals of C_{60} (h_u for hole- and t_{1u} for electron-doping) is very small. Moreover, group theory puts rather strong constraints on this type of coupling. The second coupling mechanism also does not seem to be viable, as electrostatic interactions should be strongly reduced by the efficient screening found in the fullerenes.^{8,9} Since our results were obtained for the ideal bulk structure, the experimental results^{1,2,3} may imply that the presence of the gate oxide in the field-effect-device strongly affects the structure of the fullerene crystal at the interface.

Hybridization: To understand the electron-phonon coupling to the intercalated haloform molecules, we calculate the coupling constant 10 for a molecular solid with more than one molecule per unit cell:

$$\lambda = \frac{2}{N(0)} \sum_i \sum_{\nu_i,q} \frac{1}{2M_{\nu_i}\Omega_{\nu_i,q}^2} \sum_{n,m;k} |\langle n,k|V_{\nu_i,q}|m,k+q\rangle|^2 \delta(\varepsilon_{n,k}) \delta(\varepsilon_{m,k+q} - \Omega_{\nu_i,q}).$$

Here N(0) is the total density of states per spin at the Fermi level, i runs over the different molecules in the unit cell, ν_i labels the vibrational modes of molecule i, and q is the phonon wave vector. Expanding the Bloch function $|n,k\rangle$ in molecular orbitals α_j on molecule j at position r_j in unit cell R

$$|n,k\rangle = \frac{1}{\sqrt{N}} \sum_{R,j} e^{ik(R+r_j)} \sum_{\alpha_j} c_{\alpha_j}^n(k) |\Phi_{R,j,\alpha_j}\rangle,$$

the electron-phonon matrix element is given by a sum over the matrix elements $\langle \Phi_{R,j,\alpha_j} | V_{\nu_i,q} | \Phi_{R',j',\alpha'_{j'}} \rangle$. For a

molecular solid we can neglect the intermolecular electron-phonon coupling 11 and thus obtain

$$\langle n, k | V_{\nu_i, q} | m, k + q \rangle = \frac{1}{\sqrt{N}} \sum_{\alpha_i, \alpha'_i} \overline{c_{\alpha_i}^n(k)} \, c_{\alpha'_i}^m(k + q) \, V_{\alpha_i, \alpha'_i}(\nu_i),$$

where $V_{\alpha_i,\alpha_i'}(\nu_i)$ is the electron-vibration matrix element on molecule i. Writing the partial density of states as

$$n_{\alpha,\alpha'}(\varepsilon) = \frac{1}{N} \sum_{n,k} \overline{c_{\alpha}^{n}(k)} \, c_{\alpha'}^{n}(k) \, \delta(\varepsilon - \varepsilon_{n,k}),$$

we finally obtain

$$\lambda = \frac{2}{N(0)/N} \sum_{i} \sum_{\nu_{i}} \frac{1}{2M_{\nu_{i}} \Omega_{\nu_{i}}^{2}} \sum_{\alpha_{i}, \alpha', \alpha'', \alpha'''} \overline{V_{\alpha_{i}, \alpha'_{i}}(\nu_{i})} V_{\alpha''_{i}, \alpha'''_{i}}(\nu_{i}) n_{\alpha_{i}, \alpha''_{i}}(0) n_{\alpha'_{i}, \alpha'''_{i}}(\Omega_{\nu_{i}}).$$

Thus a vibrational mode of a molecule only contributes to the electron-phonon coupling, if (i) there is a molecular orbital that contributes significantly to the density of states at the Fermi level and (ii) the electron-vibration matrix element does not vanish. In the case of C_{60} , the relevant orbitals are the t_{1u} (h_u) for electron (hole) doping and the non-vanishing electron-vibration matrix elements matrix are found by reduction of the symmetric tensor product $t_{1u} \otimes_s t_{1u} = A_g \oplus H_g$ ($h_u \otimes_s h_u = A_g \oplus G_g \oplus 2H_g$).

To estimate the contribution of the molecular levels of the CHX₃-molecules to the density of states at the Fermi level we have performed all-electron density functional calculations using the Gaussian-orbital code NRLMOL, 12 employing the PBE functional. 13 The basis set is 4s3p1d for H, 5s4p3d for C, 6s5p3d for Cl, and 7s6p4d for Br. The position of the energy levels of CHX₃ (X=Cl, Br, I) compared to those of C_{60} are shown in figure 1. While the levels of the chloroform molecule are fairly distant from the HOMO/LUMO levels of C₆₀, the levels of bromoform and, in particular, iodoform move much closer. This implies that the contribution of the haloform orbitals to the density of states at the Fermi level should increase when replacing chlorine by bromine, suggesting an explanation of the increase in transition temperature.

To estimate the actual contribution of the CHX₃ levels to the density of states at the Fermi level, we perform calculations both for an isolated C₆₀-molecule and for a system consisting of a C₆₀-molecule and the twelve closest neighboring CHX₃-molecules at the experimentally determined positions.⁶ We then calculate $\sum_{m,n} \langle \Psi_m | \Phi_n \rangle \langle \Phi_n | \Psi_m \rangle$, where the Ψ_m are the t_{1u} (h_u) derived orbitals for the C₆₀-molecule with the neighboring CHX₃-molecules and the Φ_n are the t_{1u} (h_u) orbitals of the isolated C₆₀-molecule. If there were no hybridization between C₆₀ and CHX₃, the overlap would be equal to the number of C₆₀-derived orbitals considered (3 for t_{1u} and 5 for h_u). The deviation from this number is a measure of the hybridization between C₆₀ and CHX₃.

As shown in table I, we find that the deviation is very small for both $\mathrm{CHCl_3}$ and $\mathrm{CHBr_3}$, i.e., there is essentially no hybridization of the haloform-levels with the $\mathrm{HOMO/LUMO}$ of the $\mathrm{C_{60}\text{-}molecule}$: Less than 3% for $\mathrm{C_{60}\text{-}2CHBr_3}$ and less than 1.5% for $\mathrm{C_{60}\text{-}2CHCl_3}$. Only the g_g and h_g levels that are well below the Fermi level show appreciable hybridization, as could be expected from the energetic proximity of these levels and the occupied levels of $\mathrm{CHCl_3}$ and $\mathrm{CHBr_3}$. Therefore, the contribution of the $\mathrm{CHX_3}$ -levels to the electron-phonon coupling should be very small.

The situation changes, of course, in the field-doped layer. There will be an additional electrostatic potential, which can lead to a shift in the relative positions of the electronic levels of the C_{60} and the intercalated haloform molecules. One might then speculate that for a certain external field one can line up the HOMO or LUMO of the different molecules, thereby maximizing the mixing and consequently a possible coupling to the haloform modes. For that field one would then expect to find the maximum transition temperature. Since the energetic positions of the molecular levels of CHCl₃ and CHBr₃ are quite different (cf. figure 1), the fields required for bringing say the HOMO of CHCl₃ in line with that of C_{60} is substantially larger than that required for CHBr₃. Hence one would expect that the transition temperature for $C_{60} \cdot 2CHCl_3$ peaks at a gate-voltage significantly different from that for $C_{60} \cdot 2CHBr_3$. Since the gate-voltage also corresponds to the induced charge carrier density, from the above scenario one would expect that the transition temperatures for the different crystals would show a maximum at different doping levels – contrary to the experimental finding reported in reference 3.

In addition group theory puts further constraints on this coupling via selection rules for the electronvibration matrix elements. As seen from figure 1, the HOMO/LUMO levels of the haloform molecules are singly degenerate of symmetry a_2 and a_1 , respectively. Decomposing the (symmetric) tensor product of these irreducible representations, we find that they can only couple to the molecular vibrations of symmetry A_1 , not to the two-fold degenerate E modes (cf. tables II and III). Only the two-fold degenerate molecular levels of symmetry e, which are even further away from the Fermi level than the HOMO/LUMO, can couple to all the modes. Hence even if there is some contribution of the HOMO/LUMO levels of the CHX₃ molecules to the density of states at the Fermi level, coupling to the majority of molecular modes would be forbidden by symmetry.

Electrostatic coupling: Due to the dipole moment of the haloform molecules $(3.4 \, 10^{-30} \text{ Cm for CHCl}_3 \text{ and}$ $3.3\,10^{-30}$ Cm for CHBr₃) one might speculate that there is coupling to the intercalated molecules due to electrostatic interactions. An analogous scenario was put forward for the case of the alkali-doped fullerene A₃C₆₀, where it was suggested early on that the superconductivity is mediated by coupling to the vibrations of the alkali ions. 15 Experimentally, however, no isotope effect was found for the alkalis. 16 This could be explained as a consequence of the efficient screening in the alkalidoped fullerenes, which leads to a strong reduction in the coupling to the alkali-modes.^{8,9} A similar mechanism should be at work in the field-doped fullerenes, reducing the coupling to the dipole moments of the haloform molecules. In addition, one would expect, that even the unscreened coupling to dipoles (haloform molecules) should be weaker than the coupling to monopoles (alkali ions). Moreover, the dipole moments of CHCl₃ and CHBr₃ are very similar, while, because of the lattice expansion, the bromoform molecules are more distant from the C_{60} than the chloroform molecules. Based on a coupling to the dipole moment, one would therefore expect that T_c in C_{60} ·2CHBr₃ should be lower than in C_{60} ·2CHCl₃ – contrary to the experimental finding. A coupling via the dipole moments thus seems very unlikely.

Conclusions: In most of the arguments we have given above, we have assumed that the structure and symmetry of the bulk crystal is also relevant in the region under the gate oxide. Our results show that with this assumption it seems hard to understand the observed increase in transition temperature of the haloform intercalated fullerenes. This then suggests that the crystal structure under the gate oxide must be markedly different from the bulk structure. Possible effects are a different orientation of the molecules at the interface, a reduction of the symmetry, some bonding to the oxide, some additional screening due to the presence of the oxide, or a reorientation of the haloform molecules in the strong electric field used for in field-doping. It therefore seems that a correct picture that allows to understand the experimental results reported in reference 3 must involve more than just assuming that a monolayer of the ideal crystal is doped with charge carriers.

Acknowledgments We would like to thank A. Burkhard for helpful discussions and M.R. Pederson and J. Kortus for their support in using the NRLMOL code.

^{*} Electronic address: E.Koch@fkf.mpg.de

¹ J.H. Schön, Ch. Kloc, R.C. Haddon, and B. Batlogg, Science **288**, 656 (2000).

² J.H. Schön, Ch. Kloc, and B. Batlogg, Nature **408**, 549 (2000).

³ J.H. Schön, Ch. Kloc, and B. Batlogg, Science **293**, 2432 (2001).

⁴ O. Gunnarsson, Rev. Mod. Phys. **69**, 575 (1997).

⁵ S. Wehrli, D. Poilblanc, and T.M. Rice, Eur. Phys. J. B 23, 345 (2001).

⁶ R.E. Dinnebier, O. Gunnarsson, H. Brumm, E. Koch, P.W. Stephens, A. Huq, and M. Jansen, Science **296**, 109 (2002).

A. Bill and V.Z. Kresin, Eur. Phys. J. B 26, 3 (2002); A. Bill, R. Windiks, B. Delley, and V.Z. Kresin, Int. J. Mod. Phys. 16, 1533 (2002).

⁸ M. Schlüter, M. Lannoo, M. Needels, G.A. Baraff, and D. Tománek, J. Phys. Chem. Solids **53**, 1473 (1992).

⁹ E. Koch, O. Gunnarsson, and R.M. Martin Phys. Rev. Lett. 83, 620 (1999).

¹⁰ D. Rainer, Prog. Low Temp. Phys. **10**, 371 (1986).

¹¹ M. Lannoo, G.A. Baraff, M. Schlüter, and D. Tomanek, Phys. Rev. B **44**, 12106 (1991).

^{M.R. Pederson and K.A. Jackson, Phys. Rev. B. 41, 7453 (1990); K. Jackson and M.R. Pederson, Phys. Rev. B. 42, 3276 (1990); M.R. Pederson and A.A. Quong, Phys. Rev. B 46, 13584 (1992); A.A. Quong, M.R. Pederson, and J.L. Feldman, Solid State Commun. 87, 535 (1993); D. Porezag and M.R. Pederson, Phys. Rev. A. 60, 2840 (1999).}

¹³ J.P. Perdew, K. Burke and M. Ernzerhof, Phys. Rev. Lett. **77**, 3865 (1996).

 $^{^{14}}$ Landoldt-Börnstein, Vol. I/2, table 14145 IX b), Springer, Heidelberg, 1951.

¹⁵ F.C. Zhang, M. Ogata, and T.M. Rice, Phys. Rev. Lett. **67**, 3452 (1991).

¹⁶ B. Burk, V.H. Crespi, A. Zettl, and M.L. Cohen, Phys. Rev. Lett. **72**, 3706 (1994).

TABLE I: Overlap $\sum_{m,n} \langle \Psi_m | \Phi_n \rangle \langle \Phi_n | \Psi_m \rangle$ between the molecular orbitals Ψ_m of \mathcal{C}_{60} with the twelve closest neighboring CHX₃ (X=Cl, Br) molecules and the molecular orbitals Φ_n of the isolated \mathcal{C}_{60} molecule. The first column gives $\sum_{m,n} \langle \Phi_m | \Phi_n \rangle \langle \Phi_n | \Phi_m \rangle$, the degeneracy of the levels.

МО	C_{60}	CHBr ₃	CHCl ₃	
t_{1g}	3	0.97	2.93	
$t_{1g} \ t_{1u}$	3	2.91	2.96	LUMO
h_u	5	4.88	4.95	HOMO
g_g	4	2.30	3.20	
$g_g h_g$	5	1.61	4.04	

TABLE II: Vibrational modes of CHX_3 molecules and their symmetry. 14

meV	E	A_1	A_1	E	E	A_1
$CHCl_3$	32.5	45.4	82.8	94.4	150.8	374.4
CHBr_3	19.1	27.5	66.8	81.3	141.6	374.9

TABLE III: Electron-phonon coupling for the HOMO and LUMO of the CHX_3 molecule: reduction of the symmetric tensor product into irreducible representations. Coupling between different molecular orbitals: reduction of the tensor product. The electrons can only couple to the two-fold degenerate vibrational modes (E) when a two-fold degenerate molecular level (e) is involved.

	C_{3v}	E	$2C_3$	$3c_v$	
LUMO	$a_1 \otimes_s a_1$	1	1	1	A_1
HOMO	$a_2 \otimes_s a_2$	1	1	1	A_1
	$e\otimes_s e$	3	0	1	$A_1 \oplus E$
	$a_1\otimes a_1$	1	1	1	A_1
	$a_1 \otimes a_2$	1	1	-1	A_2
	$a_1\otimes e$	2	-1	0	E
	$a_2\otimes a_2$	1	1	1	A_1
	$a_2\otimes e$	2	-1	0	E
	$e\otimes e$	4	1	0	$A_1 \oplus A_2 \oplus E$

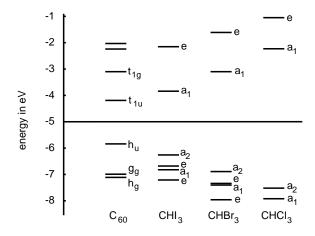


FIG. 1: Molecular levels of C_{60} and CHX₃ (X=Cl, Br, I). Note that the HOMO and LUMO of the haloform molecules are singly degenerate (irreducible representations a_1 or a_2 of the symmetry group C_{3v}).