Thermodynamic relevance of nanoscale inhomogeneities in Bi₂Sr₂CaCu₂O_{8+δ}

T. Schneider Physik-Institut der Universität Zürich, Winterthurerstrasse 190, CH-8057 Zürich, Switzerland

Using finite size scaling we analyze specific heat and London penetration depth data to estimate the spatial extent of the superconducting grains in so called high-quality $\mathrm{Bi_2Sr_2CaCu_2O_{8+\delta}}$ single crystals. Contrary to the previously investigated type II superconductors, $\mathrm{YBa_2Cu_3O_{7-\delta}}$, $\mathrm{MgB_2}$, $\mathrm{2H\text{-}NbSe_2}$ and $\mathrm{Nb_{77}Zr_{23}}$, where the lower bound for the length scale of the grains ranges from 182 A to 814 A, our analysis uncovers nanoscale superconducting grains. This clarifies the relevance of the spatial variations in the electronic characteristics observed in underdoped $\mathrm{Bi_2Sr_2CaCu_2O_{8+\delta}}$ with scanning tunnelling microscopy for bulk and thermodynamic properties and establishes their spatial extent.

Since the discovery of superconductivity in cuprates by Bednorz and Müller [1] a tremendous amount of work has been devoted to their characterization. Bismuth based cuprates deserved special attention due to their potential for applications. The issue of inhomogeneities and their characterization is essential for several reasons, including: First, if inhomogeneity is an intrinsic property, a re-interpretation of experiments, measuring an average of the electronic properties, is unavoidable. Second, inhomogeneity may point to a microscopic phase separation, i.e. superconducting grains, embedded in a nonsuperconducting matrix. Third, there is neutron spectroscopic evidence for nanoscale cluster formation and percolative superconductivity in various cuprates [2,3]. Fourth, nanoscale spatial variations in the electronic characteristics have been observed in underdoped $Bi_2Sr_2CaCu_2O_{8+\delta}$ with scanning tunnelling microscopy (STM) [4–7]. They reveal a spatial segregation of the electronic structure into 3nm diameter superconducting domains in an electronically distinct background. On the contrary, a large degree of homogeneity has been observed by Renner and Fischer [8]. As STM is a surface probe the relevance of these observations for bulk and thermodynamic properties remains to be clarified. Fifth, in $YBa_2Cu_3O_{7-\delta}$, MgB_2 , $2H-NbSe_2$ and $Nb_{77}Zr_{23}$ considerably larger grains have been established. The magnetic field induced finite size effect revealed lower bounds ranging from L = 182 to 814A [9]. This letter concentrates on the Bismuth- and Thallium based cuprates and addresses these issues by providing clear evidence for the existence of superconducting grains with spatial nanoscale extent.

It is well-known that systems of finite extent, i.e. isolated superconducting grains, undergo a rounded and smooth phase transition [10]. As in an infinite and homogeneous system the transition temperature T_c is approached the correlation length ξ increases strongly and diverges at T_c . However, when superconductivity is restricted to grains with length scale L, ξ cannot grow beyond L. In type II superconductors, exposed to a magnetic field H, there is an additional limiting length scale $L_H = \sqrt{\Phi_0/(aH)}$ with $a \approx 3.12$, related to the average distance between vortex lines [9]. Indeed, as the magnetic field increases, the density of vortex lines becomes greater, but this cannot continue indefinitely, the limit is roughly set on the proximity of vortex lines by the overlapping of their cores. Due to these limiting length scales the phase transition is rounded and occurs smoothly. As a remnant of the singularity in the thermodynamic quantities of the homogeneous system at T_c , these quantities exhibit a so called finite size effect, i.e. a maximum or an inflection point at T_p , where $\xi(T=T_p)=L_m$ and $L_m = L$ when $L < L_H$, while $L > L_H$ for $L_m = L_H$. We have shown that in $YBa_2Cu_3O_{7-\delta}$, MgB_2 , $2H-NbSe_2$ and Nb₇₇Zr₂₃, in the range of attained fields, the condition $L > L_H$ is satisfied. As the experimental data do not extend to low fields, the actual extent of the grains may exceed the resulting lower bounds ranging from L = 182 to 814A [9]. On the contrary, the specific heat measurements reveal that in the Bismuth- and Thallium based cuprates T_p does not shift up to 14T, for fields applied parallel or perpendicular to the c-axis [11–13]. Thus, in these materials the condition $L < L_H =$ $\sqrt{\Phi_0/(aH)} = 69$ A applies, uncovering nanoscale superconducting grains, consistent with the length scale of the inhomogeneities observed with STM spectroscopy [4–7].

To refine this rough estimate we perform a detailed finite size scaling analysis of the specific heat [13] and the London penetration depth data [14] of Bi₂Sr₂CaCu₂O_{8+δ} single crystals. It uncovers isolated superconducting grains with length scale $L_c \approx 92 \mathrm{A}$ along the c-axis and $L_{ab} \approx 68$ A in the ab-plane. The latter value is comparable with the spatial segregation of the electronic structure into 30A diameter superconducting domains in an electronically distinct background observed with STM spectroscopy [4–7]. As STM is a surface probe, our analysis establishes that these grains are not merely an artefact of the surface, but a bulk property with spatial extent, giving rise to a rounded thermodynamic phase transition which occurs smoothly. While there are many questions to be answered about the intrinsic or extrinsic origin of the inhomogeneity, the existence and the nature of

a macroscopic superconducting state, we establish that a finite size scaling analysis yields spatial extent of the inhomogeneity which prevents the occurrence of a homogeneous and macroscopic superconducting phase.

Approaching T_c from below the transverse correlation length ξ_i^t in direction i increases strongly. However, due to the limiting length scales L_i and $L_{H_i} = \sqrt{\Phi_0/(aH_i)}$, it is bounded and cannot grow beyond

$$\xi_{i}^{t}(t_{p}) = \xi_{0i}^{t} |t_{p}|^{-\nu} = \left\{ \begin{array}{l} \sqrt{L_{j}L_{k}}, \ i \neq j \neq k \\ \sqrt{\Phi_{0}/(aH_{i})} = L_{H_{i}} \end{array} \right\}, \quad (1)$$

where $t_p = 1 - T_p/T_c$ and ν denotes the critical exponent of the transverse correlation length. Beyond the meanfield approximation it differs from $\nu = 1/2$ and $a \approx 3.12$ is a universal constant [9]. As a remnant of the singularity at T_c the thermodynamic quantities exhibit a so called finite size effect, i.e. a maximum or an inflection point at T_p . Two limiting regimes, characterized by

$$L_{H_i} = \sqrt{\frac{\Phi_0}{aH_i}} = \left\{ \begin{cases} <\sqrt{L_j L_k} \\ > \sqrt{L_j L_k} \end{cases}, i \neq j \neq k \right\}, \tag{2}$$

can be distinguished. For $L_{H_i} < \sqrt{L_j L_k}$ the magnetic field induced finite size effect limits ξ_i^t to grow beyond L_{H_i} , while for $L_{H_i} > \sqrt{L_j L_k}$ the superconducting grains set the limiting length scales. Since L_{H_i} can be tuned by the strength of the applied magnetic field, both limits are experimentally accessible. $L_{H_i} < \sqrt{L_j L_k}$ is satisfied for sufficiently high and $L_{H_i} > \sqrt{L_j L_k}$ for low magnetic fields. Thus, the occurrence of a magnetic field induced finite size effect requires that the magnetic field and the length scales of the superconducting grains satisfy the lower bound $H_i > \Phi_0/(aL_iL_i)$.

To derive detailed estimates we analyze the single crystal data for the specific heat coefficient of Junod et~al. [13] for $\mathrm{Bi_{2.12}Sr_{1.71}Ca_{1.22}Cu_{1.95}O_{8+\delta}}$. In Fig.1 we displayed the data for fields applied parallel to the c-axis. In zero field there is a broad peak around $T_p=85.1\mathrm{K}$, establishing the existence of superconducting grains. Furthermore, T_p does not appear to shift with increasing magnetic field up to $H=14\mathrm{T}$. Indeed, a background independent definition of T_p is the temperature at which (c(H,T)-c(H=0,t))/T is minimum. This definition leads to the conclusion that T_p does not change up to 14T [13]. Noting that the same behavior was found for fields perpendicular to the c-axis, inequality (2) yields for the spatial extent of the superconducting grains the upper bounds

$$L_{ab} < 69A, \ \sqrt{L_{ab}L_c} < 69A.$$
 (3)

Another striking feature is the reduction of the peak height with increasing field, applied parallel to the c-axis, while for fields applied parallel to the layers there is a minor reduction only [13].

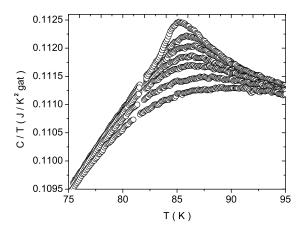


FIG. 1. Specific heat coefficient of a $\mathrm{Bi}_{2.12}\mathrm{Sr}_{1.71}\mathrm{Ca}_{1.22}\mathrm{Cu}_{1.95}\mathrm{O}_{8+\delta}$ single crystal versus temperature taken from Junod *et al.* [13]. The magnetic field is parallel to the c-axis (from top to bottom: 0, 0.5, 1, 2, 4, 8 and $14\mathrm{T}$.

To elucidate this behavior we invoke close to T_c the scaling form [9,15]

$$\frac{c\left(t,H_{i}\right)}{T} = \frac{c\left(t\right)}{T}G\left(z\right) + B^{\pm}, \quad z = \frac{H_{i}\left(\xi_{i}^{t}\right)^{2}}{\Phi_{0}},\tag{4}$$

where

$$\frac{c(t)}{T} = \frac{A^{\pm}}{\alpha} |t|^{-\alpha} \tag{5}$$

is the zero field contribution. G(z) is a universal scaling function of its argument and G(0) = 1 [9,15]. α denotes the critical exponent and A^{\pm} the critical amplitude of the specific heat, where $\pm = sign(1-T_c/T)$ and B^{\pm} accounts for the regular background. Strictly speaking this scaling form applies to a neutral superfluid. However, there is strong evidence that for the accessible temperature range cuprates fall effectively into this 3D-XY universality class [9,15,16]. At T_p the transverse correlation length is fixed by $\xi_i^t(t_p) = \sqrt{L_j L_k}(\text{Eq.}(1))$. Accordingly, $H_i \to 0$ corresponds to limit $z \to 0$. Here the scaling function G(z)adopts the form [15], $G(z) = 1 + cz(-1 + \ln(z))$, where cis a universal constant. At T_p and for fields applied along the c-axis the relative reduction of the specific heat coefficient, $\Delta \gamma (t_p, H_c) = (c(t_p, H_c) - c(t_p, H_c = 0))/T_p$ adopts then the scaling form

$$\Delta \gamma \left(t_p, H_c \right) = bH_c \left(-1 + \ln \left(dH_c \right) \right), \tag{6}$$

where

$$b = \frac{A^{-}cL_{a}L_{b}}{T_{p}\alpha\Phi_{0}}|t_{p}|^{-\alpha}, \quad dH_{c} = z = \frac{H_{c}L_{a}L_{b}}{\Phi_{0}}.$$
 (7)

Hence the reduction is controlled by the length scales of the superconducting grains in the ab-plane. As this scaling form applies in the limit $H_c \to 0$, we restricted the fit to the experimental data displayed in Fig.2 to the low field data points. The fit yields $b = 8 \ 10^{-5} \text{J/(K}^2 \text{gatT)}$ and $d = 0.012 \ \text{T}^{-1}$ so that

$$\sqrt{L_a L_b} = 50 A, \tag{8}$$

consistent with the upper bound, $L_{ab} < 69 \text{A}$ (Eq.(3)), derived from the absence of a shift of T_p up to 14T. When the magnetic field is applied parallel to the a-axis, the scaling variable is $z = \left(H_a \left(\xi_a^t\right)^2\right)/\Phi_0 \approx \left(H_a \left(\xi_{ab}^t\right)^2\right)/\Phi_0 = \left(H_a \left(\xi_c^t/\gamma^2\right)^2\right)/\Phi_0$, where γ , defined by $\gamma^2 = \xi_c^t/\xi_{ab}^t = \left(\lambda_c/\lambda_{ab}\right)^2$, measures the anisotropy. Thus, in this field direction the scaling variable entering Eq.(6) is $z = H_{ab}L_{ab}^2/\left(\gamma^4\Phi_0\right)$. As Bi₂Sr₂CaCu₂O_{8+ δ} is highly anisotropic ($\gamma > 100$) the reduction should be very small. This behavior, reflecting the large anisotropy, was also found experimentally [13].

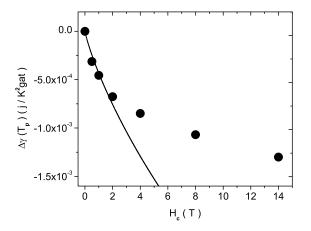


FIG. 2. $\Delta \gamma (t_p, H_c)$ versus magnetic field H_c applied parallel to the c-axis of a Bi_{2.12}Sr_{1.71}Ca_{1.22}Cu_{1.95}O_{8+ δ} single crystal, derived from Junod *et al.* [13]. The solid line is Eq.(6) with the parameters listed in the text.

Next we turn to the zero field transition to estimate the critical correlation volume $V_c^t=\xi_{0a}^t\xi_{0b}^t\xi_{0c}^t$. This quantity is essential to derive, in combination with the volume of the superconducting grains, $V_{gr}=L_aL_bL_c$, an independent estimate of the reduced temperature t_p , where the finite size effect sets in. In Fig.3 we compare the measured temperature dependence of the zero field specific heat coefficient with the expected critical behavior of the homogenous counterpart. The solid lines in Fig.3 are Eqs.(4) and (5) with H=0 and the parameters $T_c=85.7$ K, $\tilde{A}^-=A^-/(T_c\alpha)=-0.0472$, $B^-=0.15693$, $B^+=0.16022$ in J/K²gat, $A^+/A^-=1.07$ and $\alpha=-0.013$.

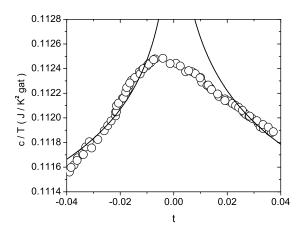


FIG. 3. Zero field specific heat coefficient of a ${\rm Bi}_{2.12}{\rm Sr}_{1.71}{\rm Ca}_{1.22}{\rm Cu}_{1.95}{\rm O}_{8+\delta}$ single crystal derived from Junod *et al.* [13]. The solid lines are Eq.(5) with the parameters listed in the text.

To estimate the correlation volume we note that $A^- = T_c \alpha \ \tilde{A}^-$, $A^-(\text{cm}^{-3}) = (10^4/k_B/V_{gat}) A^-(\text{mJ/K/cm}^3)$ and $V_{gat} = 9.1 \text{cm}^3$ gives for the critical amplitude of the specific heat the estimate $A^- = 4.2 \ 10^{-3} \text{A}^{-3}$. The universal relation [9], $A^- \xi_{0a}^t \xi_{0b}^t \xi_{0c}^t = A^- V_c^t = (R^-)^3$, where $R^- = 0.815$, yields then the correlation volume $V_c^t \approx 129 \text{A}^3$ compared to 680A^3 , the value for optimally doped YBa₂Cu₃O_{7-\delta} [9].

Finally we turn to the finite size effect in the London penetration depth. Considering again the 3D-XY critical point, extended to the anisotropic case, the penetration depths and transverse correlation lengths in directions i and j are universally related by [15,17]

$$\frac{1}{\lambda_i(T)\lambda_j(T)} = \frac{16\pi^3 k_B T}{\Phi_0^2 \sqrt{\xi_i^t(T)\xi_j^t(T)}}.$$
 (9)

When the superconductor is inhomogeneous, consisting of superconducting grains with length scales L_i , embedded in a nonsuperconducting medium, ξ_i^t does not diverge but is bounded by $\xi_i^t \xi_j^t \leq L_k^2$, where $i \neq j \neq k$. The resulting finite size effect is clearly seen in the microwave surface impedance data for $\lambda_{ab}^2 \left(T=0\right)/\lambda_{ab}^2\left(T\right)$ versus T of Jacobs et al. [14], displayed in Fig.4. The solid curve indicates the leading critical behavior of the homogeneous system. A characteristic feature of this finite size effect is the occurrence of an inflection point at $T_p \approx 87 \mathrm{K}$, giving rise to an extremum in $d \left(\lambda_{ab}^2 \left(T=0\right)/\lambda_{ab}^2\left(T\right)\right)/dT$. Here Eq.(9) reduces to

$$\frac{1}{\lambda_{ab}^{2}\left(T_{p}\right)} \approx \frac{1}{\lambda_{a}\left(T_{p}\right)\lambda_{b}\left(T_{p}\right)} = \frac{16\pi^{3}k_{B}T_{p}}{\Phi_{0}^{2}L_{c}}.$$
 (10)

With $\lambda_{ab}\left(T=0\right)=1800\mathrm{A}$ as obtained from $\mu\mathrm{SR}$ measurements [18], $T_{p}\approx87\mathrm{K}$ and $\lambda_{ab}^{2}\left(T=0\right)/\lambda_{ab}^{2}\left(T_{P}\right)=0.066$ we find

$$L_c \approx 68A,$$
 (11)

compared to $L_{ab} \approx 50 \,\mathrm{A}$ (Eq.(8)) and consistent with the upper bound $\sqrt{L_{ab}L_c} < 69 \,\mathrm{A}$ (Eq.(3)). This yields for the volume of the superconducting grains, V_{gr} , the estimate $V_{gr} = L_{ab}^2 L_c \approx 1.7 \, 10^5 \,\mathrm{A}^3$. Together with the correlation volume $V_c^t \approx 129 \,\mathrm{A}^3$ we find for the reduced temperature t_p , where rounding and shifting of the transition sets in, the value $|t_p| = \left(V_c^t/V_{gr}\right)^{1/3\nu} \approx \left(V_c^t/V_{gr}\right)^{1/2} \approx 0.027$, consistent with the rounding of the peak in the specific heat coefficient displayed in Fig.3. Thus, although the superconducting grains are of nanoscale only, the very small correlation volume makes the critical regime attainable. Clear evidence for 3D-XY critical behavior was also observed in epitaxially grown Bi2212 films [16].

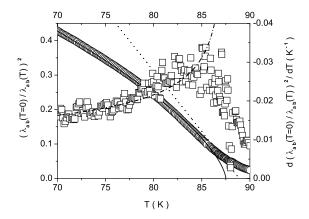


FIG. 4. Microwave surface impedance data for $\lambda_{ab}^2 \left(T=0\right)/\lambda_{ab}^2 \left(T\right)$ (\bigcirc) and $d\left(\lambda_{ab}^2 \left(T=0\right)/\lambda_{ab}^2 \left(T\right)\right)/dT$ (\square) versus T of a high-quality $\mathrm{Bi}_2\mathrm{Sr}_2\mathrm{CaCu}_2\mathrm{O}_{8+\delta}$ single crystal taken from Jacobs et~al. [14]. The solid line is $\lambda_{ab}^2 \left(T=0\right)/\lambda_{ab}^2 \left(T\right)=1.2\left(1-T/T_c\right)^{2/3}$ and the dash-dot line its derivative with $T_c=87.5\mathrm{K}$, indicating the leading critical behavior of the homogeneous system. The dotted line is the tangent to the inflection point at $T_p\approx87\mathrm{K}$, where $d\left(\lambda_{ab}^2 \left(T=0\right)/\lambda_{ab}^2 \left(T\right)\right)/dT$ is maximum.

In contrast to YBa₂Cu₃O_{7- δ}, MgB₂, 2H-NbSe₂ and Nb₇₇Zr₂₃, where the lower bounds for the length scale L of the superconducting grains ranges from 182 A to 814 A [9], we have seen that the data for Bi₂Sr₂CaCu₂O_{8+ δ} single crystals uncovers the existence of nanoscale superconducting grains. This finding is consistent with the spatial variations in the electronic characteristics observed in underdoped Bi-2212 with STM [4–7]. However, our analysis has shown that nanoscale superconducting grains are not merely an artefact of the surface, but a bulk property with spatial extent, giving rise to finite size effects and with that to a rounded thermodynamic phase transition which occurs smoothly. While there are many questions to be answered about the intrinsic or extrinsic origin of the inhomogeneity, the existence and the nature

of a macroscopic superconducting state, we established that a finite size scaling analysis yields the spatial extent of the inhomogeneity which prevents the occurrence of a homogeneous and macroscopic superconducting phase.

The author is grateful to A. Furrer, A. Junod, H. Keller, M. Kugler, J. Loram and K.A. Müller for very useful comments and suggestions on the subject matter.

- [1] G. Bednorz and K. A. Muller, Z. Phys. B 64, 189 (1986)
- [2] J. Mesot, P. Allensbach, U. Staub and A. Furrer, Phys. Rev. Lett. **70**, 865 (1993)
- [3] A. Furrer et al., Physica C 235-240, 261 (1994)
- [4] J. Liu, J. Wan, A. Goldman, Y. Chang and P. Jiang, Phys. Rev.Lett. 67, 2195 (1991)
- [5] A. Chang, Z. Rong, Y. Ivanchenko, F. Lu and E. Wolf, Phys. Rev. B 46, 5692 (1992)
- [6] T. Cren, D. Roditchev, W. Sacks, J. Klein, J.-B. Moussy, C. Deville-Cavellin, and M. Laguës, Phys. Rev. Lett. 84, 147 (2000)
- [7] K. M. Lang, V. Madhavan, J. E. Hoffman, E. W. Hudson, H. Eisaki, S. Uchida and J. C. Davis, Nature 415, 413 (2002)
- [8] Ch. Renner and Ø. Fischer, Phys. Rev. B 51, 9208 (1995)
- [9] T. Schneider, cond-mat/0210702
- [10] M. E. Fisher, in Critical Phenomena, Proceedings of the 1970 International School of Physics Enrico Fermi, Course 51, edited by M. S. Green (Academic, New York, 1971), p. 1
- [11] A. Junod, A. Erb and Ch. Renner, Physica C 317-318, 333 (1999)
- [12] A. Mirmelstein, A.Junod, G.Triscone, K.-Q.Wang and J.Muller, Physica C 248, 335 (1995)
- [13] A. Junod et al., Physica C 229, 209 (1994)
- [14] T. Jacobs, S. Sridhar, Q. Li, G. D. Gu, N. Koshizuka, Phys. Rev. Lett. 75, 4516 (1995)
- [15] T. Schneider and J. M. Singer, Phase Transition Approach To High Temperature Superconductivity, Imperial College Press, London, 2000
- [16] K. D. Osborn, D. J. Van Harlingen, Vivek Aji, N. Goldenfeld, S. Oh and J. N. Eckstein, cond-mat/0204417
- [17] P. C. Hohenberg, A. Aharony, B. I. Halperin and E. P. Siggia, Phys. Rev. B 13, 2986 (1976)
- [18] S. F. Lee et al., Phys. Rev. Lett. **71**, 3862 (1993)