

Enhanced thermoelectric properties of Na_xCoO_2 whisker crystals

G. Peleckis, T. Motohashi, M. Karppinen, and H. Yamauchi*

*Materials and Structures Laboratory,
Tokyo Institute of Technology,
Yokohama 226-8503, Japan*

(Dated: November 17, 2018)

Single-crystalline whiskers of thermoelectric cobalt oxide, Na_xCoO_2 , have been grown by an unconventional method from potassium-containing compositions, and their transport properties, and chemical compositions were determined. The growth mechanism was analyzed and interpreted by means of thermogravimetric analysis. At 300 K, electrical resistivity ρ and thermoelectric power S of the whisker are $102 \mu\Omega \text{ cm}$ and $83 \mu\text{V/K}$, respectively. The power-factor, S^2/ρ , thus is enhanced up to $\sim 68 \mu\text{W/K}^2 \text{ cm}$.

Thermoelectric materials that can convert heat flow directly to electric flow/current and vice versa are considered to play a key role in “clean” energy utility of the next generation [1]. However, requirements for high-efficiency thermoelectric materials are not easily satisfied. The thermoelectric efficiency is evaluated by the following figure-of-merit: $Z = S^2/\rho\kappa$, where S , ρ , and κ denote thermoelectric power, electrical resistivity, and thermal conductivity, respectively. Therefore, large S values and small ρ and κ values are simultaneously required to realize high thermoelectric efficiency. For the last few years thermoelectric oxides have been widely investigated owing to their high chemical stability at temperatures higher than $\sim 800 \text{ K}$. The sodium-cobalt oxide, Na_xCoO_2 , is one of the most promising candidates among the thermoelectric oxides. Terasaki *et al.* [2] found that this compound (originally expressed as NaCo_2O_4) exhibits simultaneously high thermoelectric power and low resistivity ($S \approx 100 \mu\text{V/K}$ and $\rho \approx 200 \mu\Omega \text{ cm}$ at 300 K). However, due to its two-dimensional crystal structure, the compound has large electromagnetic anisotropy [2], and thus polycrystalline samples always show higher resistivity values ($\rho \approx 3 \text{ m}\Omega \text{ cm}$ at 300 K [3]). For reducing the resistivity and thereby enhancing the Z value of Na_xCoO_2 , it is indispensable to develop a method to prepare textured or single-crystalline materials.

Whisker-type single crystals are of significant importance due to the following reasons: (1) the one-dimensional shape of whiskers should be favorable for some synthetic textures, and (2) whiskers may be convenient for some tiny-dimensional applications such as natural “thermoelectric wires” taking advantage of their characteristic shape. It was shown that whiskers of $\text{Bi}_2\text{Sr}_2\text{Co}_2\text{O}_y$ [4, 5] exhibit significantly enhanced thermoelectric properties as compared with polycrystalline

samples. Moreover, whiskers are known to be high-quality single crystals with low defect densities. Therefore, precise investigations on the crystal structure and physical properties of Na_xCoO_2 can be made using whisker crystals. In this letter we report thermoelectric properties of Na_xCoO_2 whiskers prepared using an original growth technique.

It is known that Na_xCoO_2 forms plate-like crystals when NaCl is used as a flux. To obtain Na_xCoO_2 whiskers we used potassium-containing compositions. Dry powders of Na_2CO_3 , K_2CO_3 , and Co_3O_4 were mixed with cation ratios, $\text{Na} : \text{K} : \text{Co} = 0.525 : 0.225 : 1.00$, and calcined at 750°C in air employing a “rapid heat-up” technique [6] to avoid evaporation of the alkali metals. The calcined powder was ground, pressed into pellets, and fired at 900°C for 12 h in air. During the firing, partial melting apparently occurred, and whiskers were found to form at the surface of the pellets (Fig. 1).

Figure 2 shows an x-ray powder diffraction pattern (measured with $\text{CuK}_{\alpha 1}$ radiation) for pulverized whiskers. All the peaks in the pattern can be indexed according to the $\gamma\text{-Na}_x\text{CoO}_2$ phase [7]. Crystal structure analysis using a four-circle diffractometer and synchrotron radiation revealed that the whiskers possess a hexagonal structure with space group, $P6_3/mmc$ (No. 194) [8], being in agreement with the neutron diffraction data for a polycrystalline sample of $\text{Na}_{0.74}\text{CoO}_2$ [9]. The grown whiskers are up to 1.6 mm in length, 15 - 40 μm in width, and 1.5 - 4.0 μm in thickness: the shape is strongly one-dimensional in noticeable contrast to plate-like crystals grown by a NaCl-flux method [2, 10]. The growth direction of the whiskers was found to be along the ab plane, while the smallest dimension is along the c axis.

Electrical resistivity (ρ) and thermoelectric power (S) of the whiskers were measured: ρ was measured using a four-point-probe apparatus (Quantum Design; PPMS) with a dc current of 5 mA along the growth (i.e. in-plane) direction, and S using a steady-state technique with a typical temperature gradient of 0.5 K/cm. Figure *refr-and-S(a)* shows the dependence of ρ on temperature for a Na_xCoO_2 whisker. The ρ value decreases with decreasing temperature, exhibiting typical metallic behavior (i.e.

*Corresponding author: Prof. Hisao Yamauchi
Materials and Structures Laboratory, Tokyo Institute of Technology
4259 Nagatsuta, Midori-ku, Yokohama 226-8503, Japan
Phone: +81-45-924-5315, Fax: +81-45-924-5365
Electronic mail: yamauchi@msl.titech.ac.jp

$d\rho/dT > 0$) in the whole temperature range. This is in accordance with the results reported for single crystals in previous works [2, 10]. An anomaly in resistivity is observed at $T_t \approx 290$ K, which is considered to be related to a first-order transition [11], while such an anomaly has not been observed for single-crystalline samples of Na_xCoO_2 [2, 10]. The absolute value of resistivity for the present whiskers is by a factor of two smaller than that for single crystals of Na_xCoO_2 grown with the NaCl flux method (cf. $\rho \approx 200 \mu\Omega \text{ cm}$ at 300 K) [2]. Figure 3(b) shows the dependence of S on temperature for a Na_xCoO_2 whisker. Both the absolute value and the dependence on temperature of S are in good agreement with those previously reported for single-crystalline and polycrystalline samples [2, 3]. The values of ρ and S at 300 K for the present whisker crystal are $102 \mu\Omega \text{ cm}$ and $83 \mu\text{V/K}$, respectively. The power-factor (S^2/ρ) is then calculated at $\sim 68 \mu\text{W/K}^2 \text{ cm}$, being as large as that for a crystal grown by the NaCl-flux method [2] and by a factor of ~ 30 larger than that for polycrystalline samples [3].

In order to determine the chemical composition of grown whiskers, we performed ICP-AES (Seiko Instruments: SPS-1500VR) and SEM-EDS (Hitachi: S-4500) analyses. In Table I, the actual cation composition of the whiskers as determined by the two independent analysis methods is given together with those of the calcined powder and the fired pellets. Neither the whiskers nor the pellets contained potassium, whereas the actual composition of the calcined powder was nearly the same as the nominal one. This result indicates that fast evaporation of potassium occurs during firing (at $\sim 900^\circ\text{C}$), which is apparently essential for the growth of whiskers. The chemical formula determined for the whisker (in terms of cation composition) is $\text{Na}_{0.5}\text{CoO}_2$, being highly sodium deficient and free from potassium.

To investigate the whisker formation mechanism, thermogravimetric (TG) measurements were performed. A powder mixture of raw materials of 4.295 mg was heated with a rate of 3.2°C/min in a thermobalance (Perkin Elmer: Pyris 1) with an isothermal heating period of 12 h at 900°C . The TG curve is shown in Fig. 4. Since K_2CO_3 is highly hygroscopic, the first weight loss about 100°C is attributed to the evaporation of water. The second weight loss is seen starting about 500°C . This is most likely due to the decarbonation process, though the total weight loss in this region ($\sim 6.4\%$) is a little too large to be explained with decarbonation (5.8 %) only. Therefore it is considered that a small amount of alkali metal(s) evaporates as well. The two weight drops about

100°C and 500°C were also seen for the potassium-free sample of $\text{Na}_{0.55}\text{CoO}_2$ [6]. After the large weight drop due to decarbonation, a temperature window was found to appear about the calcination temperature ($650\text{--}830^\circ\text{C}$) where the TG curve is relatively flat. This should correspond to the stability region of the $\text{Na}_x\text{K}_y\text{CoO}_2$ phase. In fact, x-ray diffraction measurements showed that the powder product after calcination at 750°C is of single phase of hexagonal $\text{Na}_x\text{K}_y\text{CoO}_2$ phase, whereas chemical analyses for the cation composition revealed essentially no deviation from the nominal potassium content (see Table I). Upon increasing the temperature up to 900°C an additional weight loss is seen indicating that the fast evaporation of potassium from the $\text{Na}_x\text{K}_y\text{CoO}_2$ phase starts to occur in this temperature range. In the inset of Fig. 4 the normalized weight is plotted against time. During the isothermal heating period of 12 hours at 900°C the weight loss continues until potassium completely gets depleted from the sample: the evaporation rate of potassium from $\text{Na}_x\text{K}_y\text{CoO}_2$ was estimated at $\approx 6.5 \text{ mol\%/h}$. The TG result is in good agreement with the ICP analysis data (Table I), according to which no potassium was found to remain in both the pellets and the whiskers. Taking into account the results of TG and ICP-AES analyses, it is most likely that a large amount of potassium evaporation induces partial melting at the surface of the pellet, and the partially-melted surface plays an essential role in the whisker growth.

In summary, we have developed an unconventional method to grow whisker single crystals of Na_xCoO_2 . Using potassium-containing compositions, whisker crystals of Na_xCoO_2 are found to form after firing at 900°C . At 300 K, ρ and S of the whiskers are $102 \mu\Omega \text{ cm}$ and $83 \mu\text{V/K}$, respectively. Calculated power factor (S^2/ρ) at this temperature shows a record-high value of $\sim 68 \mu\text{W/K}^2 \text{ cm}$ for the sodium-cobalt-oxide system. From ICP-AES and SEM-EDS analyses, it has been revealed that the grown whiskers are highly sodium deficient ($x \approx 0.50$) and free of potassium. Increasing sodium content up to 0.75 can probably lead to even higher thermoelectric power (S^2/ρ) values, therefore preparation of whiskers with higher sodium contents are on the way in our laboratory.

We are grateful to Prof. I. Terasaki of Waseda University for his contribution in thermoelectric power measurements. The present work was supported by Grants-in-aid for Scientific Research (Contract Nos. 11305002 and 14038219) from the Ministry of Education, Culture, Sports, Science and Technology of Japan.

-
- [1] G. Mahan, B. Sales, and J. Sharp, *Phys. Today* **50**, 42 (1997).
 - [2] I. Terasaki, Y. Sasago, and K. Uchinokura, *Phys. Rev. B* **56**, R12 685 (1997).
 - [3] I. Terasaki, in *Proceedings of the 18th International Con-*

ference on Thermoelectrics (ICTf99), Baltimore, MD, USA 1999 (IEEE, Piscataway, 2000), pp. 569-576.

- [4] R. Funahashi, and I. Matsubara, *Appl. Phys. Lett.* **79** 362 (2001).
- [5] R. Funahashi, and M. Shikano, *Appl. Phys. Lett.* **81** 1459

- (2002).
- [6] T. Motohashi, E. Naujalis, R. Ueda, K. Isawa, M. Karppinen, and H. Yamauchi, Appl. Phys. Lett. **79**, 1480 (2001).
 - [7] C. Fouassier, G. Matejka, J.-M. Reau, and P. Hagemuller, J. Solid State Chem. **6**, 532 (1973).
 - [8] T. Hanashima, G. Peleckis, T. Motohashi, S. Sasaki, M. Karppinen, and H. Yamauchi, unpublished work at Tokyo Institute of Technology (2002).
 - [9] R.J. Balsys and R.L. Davis, Solid State Ionics **93**, 279 (1996).
 - [10] K. Fujita, T. Mochida, and K. Nakamura, Jpn. J. Appl. Phys. **40**, 4644 (2001).
 - [11] T. Tojo, H. Kawaji, T. Atake, Y. Yamamura, M. Hashida, and T. Tsuji, Phys. Rev. B **65**, 052105 (2002).

TABLE I: Chemical compositions of calcined powder, pellets after firing at 900°C, and grown whiskers as determined by ICP-AES and SEM-EDS analyses. The given values are normalized by cobalt content.

Sample	Nominal		ICP-AES		SEM-EDS	
Calcined powder	Na	0.525	Na	0.540	—	
	K	0.225	K	0.240		
Pellet	Na	0.525	Na	0.547	Na	0.532
	K	0.225	K	<0.001	K	<0.001
Whisker	Na	0.525	Na	0.523	Na	0.487
	K	0.225	K	<0.001	K	<0.001

FIG. 1: Scanning electron micrograph of the grown Na_xCoO_2 whiskers.

FIG. 2: X-ray powder diffraction pattern for pulverized whisker crystals of Na_xCoO_2 .

FIG. 3: (a) Temperature dependence of resistivity (ρ) for a Na_xCoO_2 whisker. An anomaly is seen at $T_i \approx 290$ K. (b) Temperature dependence of thermoelectric power (S) for a Na_xCoO_2 whisker.

FIG. 4: Thermogravimetric curve of a raw material powder mixture (with cation ratios, Na : K : Co = 0.525 : 0.225 : 1.00) upon heating in flowing O_2 gas. (1 - Evaporation of H_2O ; 2 - Decarbonation process; 3 - Fast K evaporation) The inset represents the same thermogravimetric data with respect to time.

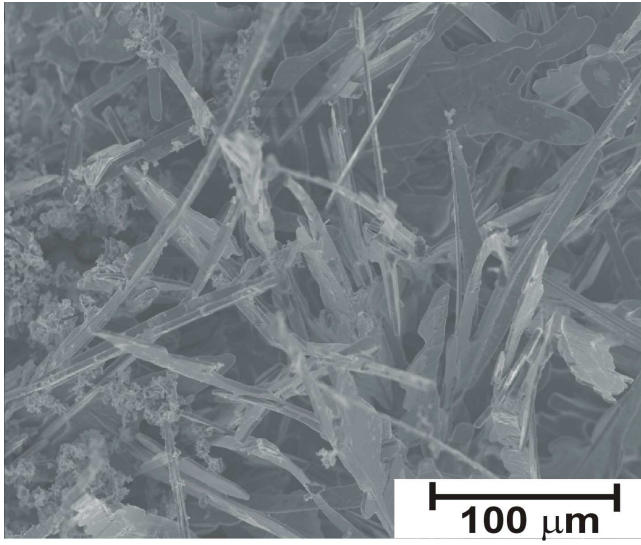


Fig. 1: Peleckis *et al.*, APL

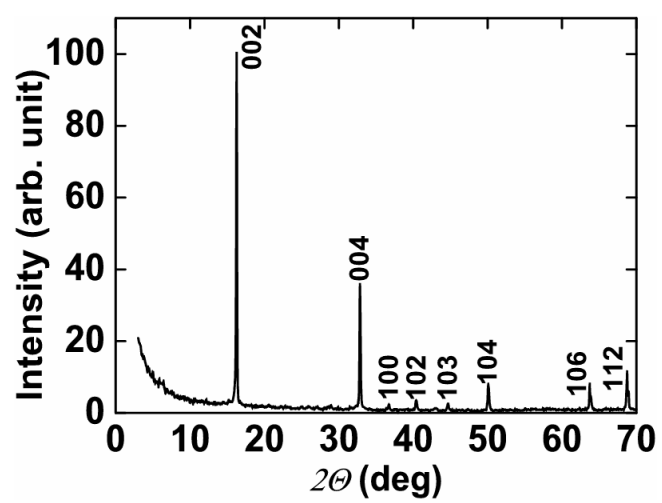


Fig. 2: Peleckis *et al.*, APL

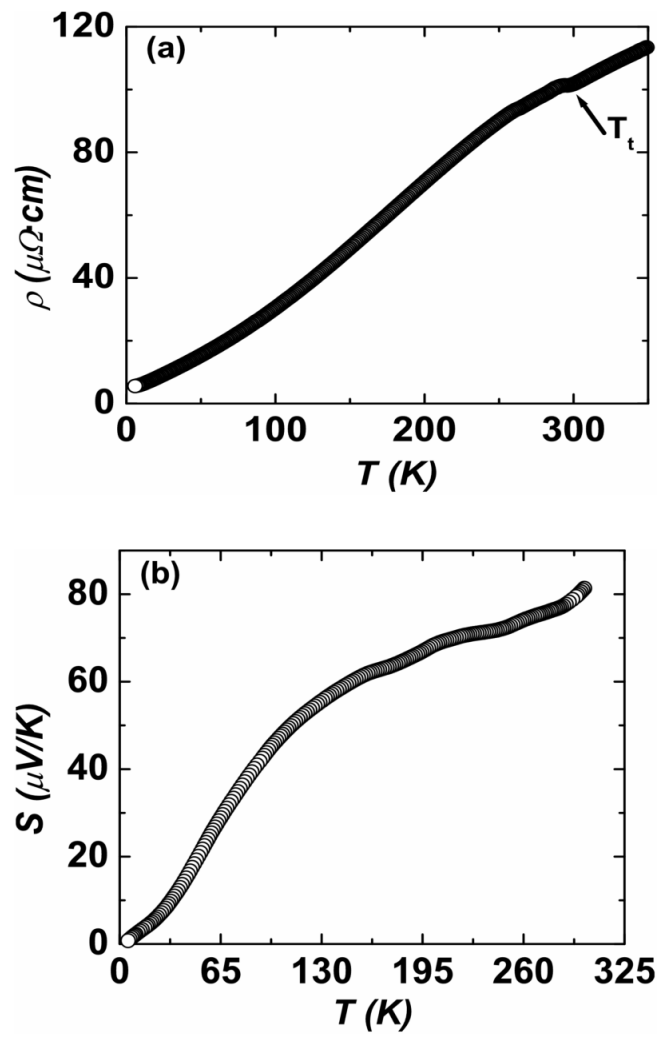


Fig 3: Peleckis *et al.*, APL

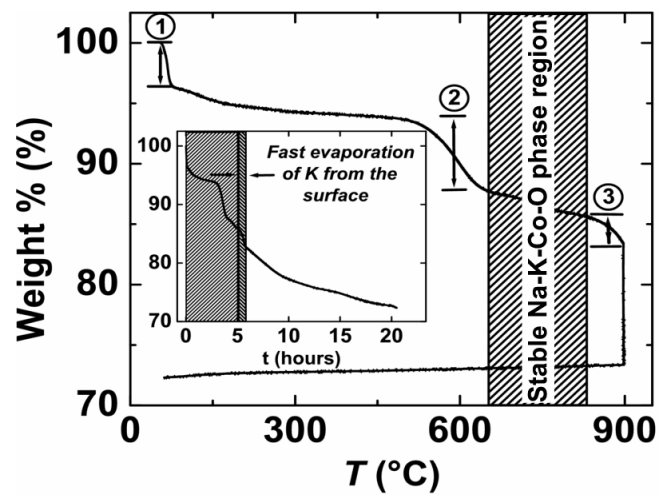


Fig 4: Peleckis *et al.*, APL