

# Spin correlations among the charge carriers in an ordered stripe phase

A.T. Boothroyd,<sup>1,\*</sup> P.G. Freeman,<sup>1</sup> D. Prabhakaran,<sup>1</sup> A. Hiess,<sup>2</sup> M. Enderle,<sup>2</sup> J. Kulda,<sup>2</sup> and F. Altorfer<sup>3</sup>

<sup>1</sup> *Department of Physics, Oxford University, Oxford, OX1 3PU, United Kingdom*

<sup>2</sup> *Institut Laue-Langevin, BP 156, 38042 Grenoble Cedex 9, France*

<sup>3</sup> *Laboratory for Neutron Scattering, ETH Zurich and PSI Villigen, CH-5232 Villigen PSI, Switzerland*

(Dated: June 5, 2018)

We have observed a diffuse component to the low-energy magnetic excitation spectrum of stripe-ordered  $\text{La}_{5/3}\text{Sr}_{1/3}\text{NiO}_4$  probed by neutron inelastic scattering. The diffuse scattering forms a square pattern with sides parallel and perpendicular to the stripe directions. The signal is dispersive, with a maximum energy of  $\sim 10$  meV. Probed at 2 meV the scattering decreases in strength with increasing temperature, and is barely visible at 100 K. We argue that the signal originates from dynamic, quasi-one-dimensional, antiferromagnetic correlations among the stripe electrons.

PACS numbers: 75.40.Gb, 71.45.Lr, 75.30.Et, 75.30.Fv

The occurrence of stripe correlations in superconducting cuprates and other doped antiferromagnets is well established from extensive experimental studies [1] following earlier theoretical work [2]. The stripe phase is characterized by a segregation of charge carriers into narrow channels that act as antiphase domain walls separating antiferromagnetic regions of the host spins. Several theoretical scenarios have been presented in which a spin gap and pairing instabilities appear among the stripe electrons, opening the door to superconductivity [3]. These findings suggest that stripes could play an important role in the physics of high- $T_c$  superconductivity.

Given the characteristic spin and charge correlations associated with local stripe order it is natural to search the spin excitation spectrum for clues to the relationship between stripes and superconductivity. Neutron inelastic scattering has revealed a number of interesting features in the spin dynamics of the cuprate superconductors, some of which, e.g. excitations at incommensurate wavevectors [4], have been interpreted as evidence for dynamic stripe correlations [5]. At the same time, the characteristic spin excitation spectrum of ideal stripes has been probed in studies of non-superconducting compounds with well defined stripe order, especially  $\text{La}_{2-x}\text{Sr}_x\text{NiO}_{4+\delta}$  [6, 7]. In none of these previous studies, however, has any evidence been found for spin correlations among the stripe electrons themselves.

In this paper we report neutron inelastic scattering measurements on  $\text{La}_{5/3}\text{Sr}_{1/3}\text{NiO}_4$  which reveal a pattern of inelastic diffuse scattering consistent with the existence of quasi-one-dimensional (1D) antiferromagnetic (AF) correlations parallel to the stripe direction. The correlations are found to be dynamic, with a maximum energy  $\sim 10$  meV. The results provide the first evidence for spin correlations among the charge carriers in a stripe phase.

The experiments were performed on single crystals of  $\text{La}_{5/3}\text{Sr}_{1/3}\text{NiO}_4$  grown by the floating-zone method [8]. Neutron inelastic scattering data were collected on the triple-axis spectrometers IN8, IN20 and IN22 at the Institut Laue-Langevin, and RITA-II at the Paul Scherrer

Institut. Most of the data reported here were obtained with a fixed scattered neutron energy  $E_f = 14.7$  meV and with a graphite filter installed after the sample to suppress higher orders. The exception is the inelastic scan shown in Fig. 2(a), which was measured with an incident energy  $E_i = 14.7$  meV and with the filter before the sample. The incident and final neutron energies were selected by Bragg reflection from the (002) planes of graphite. When neutron polarization analysis was required Heusler (111) was used for the monochromator and analyzer.

Stripe ordering in  $\text{La}_{5/3}\text{Sr}_{1/3}\text{NiO}_4$  is observed below  $T_{\text{SO}} \simeq 200$  K, and consists of parallel lines of doped holes separating AF-ordered bands of  $\text{Ni}^{2+}$  spins ( $S = 1$ ) [9]. The stripes run diagonally across the square lattice formed by the Ni sites on the  $\text{NiO}_2$  layers. As there is no reason to favour one diagonal over the other a bulk sample contains an equal proportion of spatially-separated domains with stripes along each diagonal.

Previous measurements have shown that the spin excitation spectrum of  $\text{La}_{5/3}\text{Sr}_{1/3}\text{NiO}_4$  is dominated by sharp propagating modes of the host  $\text{Ni}^{2+}$  spins [7]. These spin-wave-like excitations are highly 2D in nature, and extend in energy up to  $\sim 80$  meV. They disperse from the stripe superlattice zone centres, which have 2D wavevectors  $\mathbf{Q}_s = (h + \frac{1}{2}, k + \frac{1}{2}) \pm (\frac{1}{6}, \frac{1}{6})$  for one stripe domain and  $(h + \frac{1}{2}, k + \frac{1}{2}) \pm (-\frac{1}{6}, \frac{1}{6})$  for the other, where  $h$  and  $k$  are integers indexed with respect to the body-centred tetragonal lattice (cell parameters  $a = 3.8$  Å and  $c = 12.7$  Å).

In the present work we explored the low energy part of the spectrum over a more extended region of reciprocal space. Fig. 1(a) shows the variation in scattered intensity over a rectangular portion of the  $(h, k, 0)$  plane in reciprocal space, measured at an energy of 2.5 meV and at a temperature of 2 K. The region of reciprocal space covered by the measurements is shown in Fig. 1(b). The intensity map contains localized ‘hot spots’ of intensity centred on  $\mathbf{Q}_s$  points such as  $(\frac{1}{3}, \frac{2}{3})$ ,  $(\frac{2}{3}, \frac{2}{3})$ , etc, marked as circles on Fig. 1(b). This scattering is from spin wave excitations of the host  $\text{Ni}^{2+}$  spins, as described above.

More interestingly, the data in Fig. 1(a) also show a

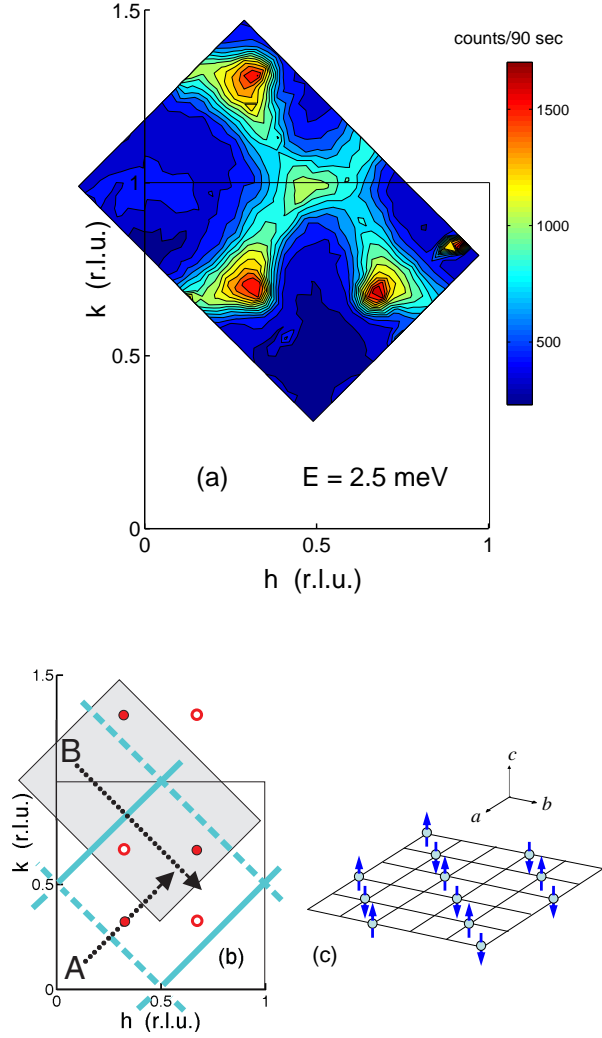


FIG. 1: (Color online). Diffuse neutron inelastic scattering from  $\text{La}_{5/3}\text{Sr}_{1/3}\text{NiO}_4$ . (a) Contour plot of the intensity in the  $(h, k, 0)$  plane in reciprocal space at an energy transfer 2.5 meV. The plot is derived from a  $25 \times 35$  rectangular grid of data points. (b) Diagram of the  $(h, k, 0)$  plane in reciprocal space. Circles are stripe superlattice zone centres. Diagonal lines indicate where diffuse scattering would be observed if the stripes behaved as 1D AF chains. Filled circles and full line are for  $[1, -1, 0]$  stripe domains; open circles and broken line are for  $[1, 1, 0]$  stripe domains. The dotted lines marked A and B are scan directions used in the experiment. (c)  $[1, 1]$  stripe domain showing the square lattice of Ni sites with local 1D AF correlations on the stripes, as proposed here.

pattern of diffuse scattering distributed around the diagonal lines drawn on Fig. 1(b). The diffuse scattering does not pass through the stripe zone centres, and is in fact separated from them. This is illustrated in Fig. 2(a) which contains two scans measured along a line equivalent to that marked A in Fig. 1(b). In the 2 meV scan there are two resolved peaks, one centred on  $(0.27, 0.27)$  from the diffuse scattering, and the other centred on

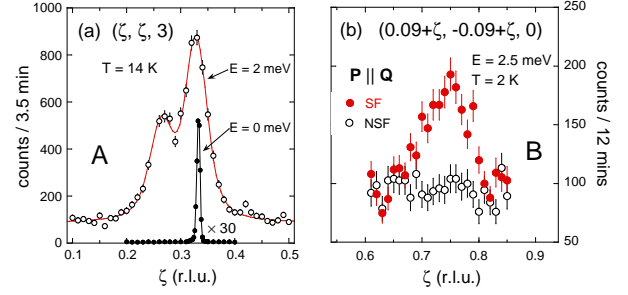


FIG. 2: (Color online). Constant-energy scans along lines equivalent to those marked A and B in Fig. 1(b). The polarized-neutron data in (b) show the spin-flip (SF) and non-spin-flip (NSF) channels recorded with the neutron polarization parallel to the scattering vector.

$(\frac{1}{3}, \frac{1}{3})$  from spin wave excitations of the stripe superlattice. The other scan in Fig. 2(a) records elastic scattering along the same line, and contains only the Bragg peak due to the ordered stripe superlattice. This scan shows that the diffuse scattering does not have a static component. We have also scanned the 2.5 meV diffuse inelastic scattering parallel to the  $(0, 0, l)$  direction at fixed in-plane wavevector (not shown). The intensity was found to decrease monotonically away from  $l = 0$  without any detectable modulation with  $l$ .

We next describe two measurements made with neutron polarization analysis. First, we performed scans along lines equivalent to A and B at a constant energy of 2.5 meV, recording the spin-flip (SF) and non-spin-flip (NSF) scattering with the neutron polarization  $\mathbf{P}$  parallel to the scattering vector  $\mathbf{Q}$ . The B data are shown in Fig. 2(b). In both scans the diffuse scattering feature was observed only in the SF channel. We conclude from this that the diffuse scattering is magnetic in origin [10].

Second, we analyzed the polarization of the 2.5 meV diffuse scattering at two different wavevectors,  $\mathbf{Q}_1 = (0.25, 0.25, 3.5)$  and  $\mathbf{Q}_2 = (0.75, 0.75, 0)$ . Neutrons scatter from spin fluctuation components perpendicular to  $\mathbf{Q}$ , so at  $\mathbf{Q}_1$  the signal is mainly from in-plane fluctuations and at  $\mathbf{Q}_2$  the signal comes equally from in-plane and  $c$ -axis components. For each  $\mathbf{Q}$  we measured the SF intensity with  $\mathbf{P} \parallel \mathbf{Q}$  and with  $\mathbf{P} \perp \mathbf{Q}$  in two orthogonal directions. Because SF scattering arises from spin fluctuations perpendicular to  $\mathbf{P}$  these measurements allow us to determine the spin fluctuation anisotropy [10]. From the  $\mathbf{Q}_1$  data we found that the spin fluctuations are isotropic within the  $\text{NiO}_2$  layers to within the experimental error of 20%. The  $\mathbf{Q}_2$  measurements revealed that the  $c$ -axis component of the magnetic response is a factor  $2.3 \pm 0.4$  larger than the in-plane response. In other words, the fluctuating spin components that give rise to the diffuse scattering are anisotropic, with a strong tendency to fluctuate towards the crystal  $c$  axis. This conclusion is consistent with the observation of a decrease in scattering

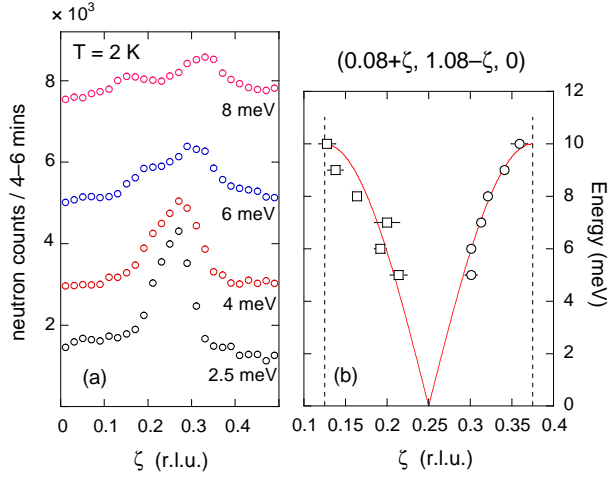


FIG. 3: (Color online). (a) Constant-energy scans along the line marked B in Fig. 1(b). Successive scans have been displaced vertically by 2000 counts for clarity. (b) Dispersion of the peak positions from a series of constant-energy scans including those shown in (a). The line is the lower bound to the excitation spectrum of a spin- $\frac{1}{2}$  Heisenberg AF chain calculated from Eq. (1) with  $J = 3.2$  meV. The vertical dotted lines indicate one period of the lower bound curve.

intensity in the out-of-plane direction mentioned earlier.

What can we infer from the results described so far for energies of 2–2.5 meV? The existence of ridges of inelastic magnetic scattering running along the diagonals of the  $(h, k)$  reciprocal lattice plane implies the existence of dynamic spin fluctuations with a short correlation length along the ridge direction and a relatively long correlation length perpendicular to the ridge. The absence of any out-of-plane modulation in the scattering means the correlations along the  $c$  axis are extremely weak. Hence, the spin fluctuations are quasi-1D, with the strongest correlations parallel to the diagonals of the square lattice, i.e. parallel to the stripe directions.

To understand the local pattern of spins responsible for the diffuse scattering we consider an array of 1D AF chains running parallel to the direction  $\mathbf{d} = [1, 1, 0]$  with spins attached to the vertices of the square lattice — Fig. 1(c). In the absence of inter-chain correlations most of the spectral weight is concentrated near the lower bound of the spin excitation spectrum, which in the case of a spin- $\frac{1}{2}$  Heisenberg chain is given by [11]

$$E(\mathbf{Q}) = \pi J |\sin(2\pi \mathbf{Q} \cdot \mathbf{d})|, \quad (1)$$

where  $J$  is the exchange energy per spin. At vanishingly small energies, the scattering cross-section is largest when  $\mathbf{Q} \cdot \mathbf{d}$  is half an odd integer, and zero when  $\mathbf{Q} \cdot \mathbf{d}$  is an integer. Therefore, we expect the low-energy ( $E \ll 4JS$ ) scattering to be strongly peaked along the broken lines shown in Fig. 1(b), which intersect the scan direction marked A at  $\mathbf{Q} = (\frac{1}{4}, \frac{1}{4}, 0)$ ,  $(\frac{3}{4}, \frac{3}{4}, 0)$ , etc. Similarly, the low-energy scattering from spin chains oriented along the

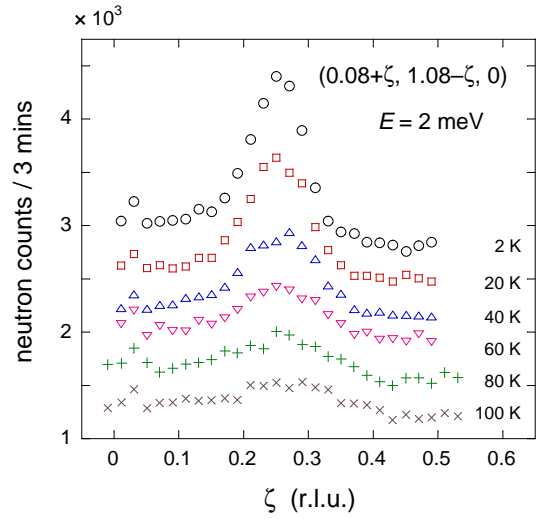


FIG. 4: (Color online). Temperature dependence of the diffuse scattering measured in a scan along line B in Fig. 1(b). The energy was fixed at 2 meV. Successive scans have been displaced vertically by 400 counts for clarity.

other diagonal  $\mathbf{d}' = [1, -1, 0]$  would lie along the solid diagonal lines in Fig. 1(b).

It can be seen that the distribution of diffuse scattering we have observed is consistent with this model. The main discrepancy is a slight meandering of the diffuse scattering shown in Fig. 1(a). For example, the peak position in the 2 meV scan shown in Fig. 2(a) is not quite at  $h = \frac{1}{4}$ . Looking in detail we find that the diffuse scattering closely follows the stripe superlattice zone boundary [7], which suggests the spin chains are weakly coupled and have the same periodicity as the stripes.

We now discuss measurements showing how the diffuse scattering varies with energy and temperature. In Fig. 3(a) we plot some of the raw data from a series of wavevector scans along line B, each scan having a fixed energy. The scan coordinate  $\zeta$  corresponds to  $(\mathbf{Q} \cdot \mathbf{d}')/2$  for a spin chain parallel to  $\mathbf{d}'$ . With increasing energies above  $\sim 4$  meV one can clearly observe two peaks separating from the 1D AF wavevector  $\zeta = \frac{1}{4}$ . On Fig. 3(b) we have plotted the dispersion of these two peaks. The peak centres were obtained by fitting each of the scans in Fig. 3(a) with two Gaussians on a linear background. The data are consistent with a dispersion described by Eq. (1) with a maximum energy of 10 meV.

Fig. 4 displays the temperature dependence of diffuse scattering at an energy of 2 meV, measured once again in a scan along line B in Fig. 1(b). With increasing temperature the intensity of the peak decreases and the width increases. These data show that the spin correlations become weaker with temperature, and are almost wiped out above 100 K.

The measurements reported here show that the new spin fluctuations we have found behave very differently

from the low-energy spin excitations of the host  $\text{Ni}^{2+}$  spins studied previously [7]. The latter are localized in  $\mathbf{Q}$ , have in-plane polarization below an anisotropy gap of  $\sim 5$  meV, and remain correlated up to the magnetic ordering temperature of  $\sim 200$  K [12]. The diffuse scattering, on the other hand, is spread out in  $\mathbf{Q}$ , shows predominant out-of-plane anisotropy, and survives only to  $\sim 100$  K.

These differences imply that the diffuse scattering does not arise from the AF ordered  $\text{Ni}^{2+}$  spins located between the charge stripes, but instead originates from AF correlations in the charge stripes themselves. Our central conclusion, therefore, is that there exist quasi-1D AF fluctuations among the stripe electrons. These fluctuations are dynamic on the timescale probed by neutron scattering [13], and from the half-width of the diffuse scattering ridge we estimate the correlation length of the fluctuations along the stripes to be  $\sim 15$  Å. The charges are thought to be localized on  $\text{Ni}^{3+}$  ions [14], which means they would carry a spin  $S = \frac{1}{2}$  in the strong crystal field limit. Hence, we can estimate the AF exchange parameter  $J$  by fitting Eq. (1) to the data in Fig. 3(b). The result is  $J \approx 3.2$  meV.

Attempts to explore the properties of stripe phases theoretically typically model the stripes as 1D electron liquids coupled via pair hopping or spin exchange to an insulating AF background [3]. These models commonly predict a spin gap in the spectrum of the stripe electrons, allowing various instabilities to occur, including superconductivity, depending on the model parameters. The results described here represent the first measurements of the spin dynamics of stripe electrons, and are important because they provide data with which to constrain the above-mentioned charge-stripe models. Hence, this is a step towards understanding the role of stripes in the problem of cuprate high- $T_c$  superconductivity.

Of course, one should be aware that stripes in the nickelates and cuprates differ somewhat in character. In the nickelates the stripes are very stable and are aligned along the diagonals of the square lattice, whereas in the superconducting cuprates the stripes are more dynamic and are aligned horizontally and vertically [5]. Also, the 1D band formed by the stripe electrons is half-filled in the nickelates (hence insulating stripes) [16], but is quarter-filled in the cuprates (metallic stripes). Nevertheless, the discovery of AF correlations among the stripe electrons in a nickelate (in contrast to theoretical predictions of ferromagnetic stripes [16]) raises general questions about the mechanism of intra-stripe spin exchange and about the coupling between the stripe electrons and the surrounding AF region. A grasp of these phenomena in a simple reference material such as  $\text{La}_{5/3}\text{Sr}_{1/3}\text{NiO}_4$  could contribute towards a better understanding of the stripe phase in other systems. Looking ahead, our results suggest it would be well worthwhile conducting a search for

spin correlations among the stripe electrons in a stripe-ordered cuprate.

We thank L.-P. Regnault for help with the experiments on IN22. This work was supported by the Engineering & Physical Sciences Research Council of Great Britain, and was performed in part at the Swiss Spallation Neutron Source SINQ, Paul Scherrer Institute (PSI), Villigen, Switzerland.

---

\* Electronic address: a.boothroyd1@physics.ox.ac.uk;  
URL: <http://xray.physics.ox.ac.uk/Boothroyd>

- [1] C. H. Chen, S-W. Cheong, and A. S. Cooper, Phys. Rev. Lett. **71**, 2461 (1993); J. M. Tranquada *et al.*, Phys. Rev. Lett. **73**, 1003 (1994); S. Mori, C.H. Chen, and S-W. Cheong, Nature **392**, 473 (1998).
- [2] J. Zaanen and O. Gunnarsson, Phys. Rev. B **40**, 7391 (1989); K. Machida, Physica C **158**, 192 (1989); V. J. Emery and S. A. Kivelson, Physica (Amsterdam) **209C**, 597 (1993); D. Poilblanc and T. M. Rice Phys. Rev. B **39**, 9749 (1989); H. L. Schultz, J. Phys. (Paris) **50**, 2833 (1989).
- [3] V. J. Emery, S. A. Kivelson, and O. Zachar, Phys. Rev. B **56**, 6120 (1997); Yu. A. Krotov, D. -H. Lee, and A. V. Balatsky, Phys. Rev. B **56**, 8367 (1997); H. Johannesson and G. I. Japaridze, cond-mat/0301585.
- [4] T. R. Thurston *et al.*, Phys. Rev. B **40**, 4585 (1989); S-W. Cheong *et al.*, Phys. Rev. Lett. **67**, 1791 (1991); P. Dai, H. A. Mook, and F. Dögan, Phys. Rev. Lett. **80**, 1738 (1998); H. A. Mook *et al.*, Nature **404**, 729 (2000).
- [5] J. M. Tranquada *et al.*, Nature **375**, 561 (1995).
- [6] S. M. Hayden *et al.*, Phys. Rev. Lett. **68**, 1061 (1992); J. M. Tranquada, P. Wochner, and D. J. Buttrey, Phys. Rev. Lett. **79**, 2133 (1997); K. Nakajima and Y. Endoh, J. Phys. Soc. Jpn. **67**, 1552 (1998); S.-H. Lee *et al.*, Phys. Rev. Lett. **88**, 126401 (2002); P. Bourges, *et al.*, Phys. Rev. Lett. **90**, 147202 (2003).
- [7] A.T. Boothroyd *et al.*, Phys. Rev. B **67**, 100407(R) (2003).
- [8] D. Prabhakaran, P. Isla, and A. T. Boothroyd, J. Cryst. Growth **237**, 815 (2002).
- [9] S-W. Cheong *et al.*, Phys. Rev. B **49**, 7088 (1994); H. Yoshizawa *et al.*, Phys. Rev. B **61**, R854 (2000); C-H. Du *et al.*, Phys. Rev. Lett. **84**, 3911 (2000); S.-H. Lee *et al.*, Phys. Rev. B **63**, 060405 (2001).
- [10] R. M. Moon, T. Riste, and W. C. Koehler, Phys. Rev. **181**, 920 (1969).
- [11] J. des Cloizeaux and J. J. Pearson, Phys. Rev. **128**, 2131 (1962).
- [12] S. -H. Lee and S-W. Cheong, Phys. Rev. Lett. **79**, 2514 (1997).
- [13] Preliminary high-resolution measurements show a reduction in diffuse scattering intensity below  $\sim 1$  meV, indicative either of a spin gap of  $\sim 0.5$  meV or a quasielastic response with a width  $\Gamma \sim 1$  meV.
- [14] J. Li *et al.*, Phys. Rev. B **67**, 012404 (2003).
- [15] G. Müller *et al.*, Phys. Rev. B **24**, 1429 (1981).
- [16] J. Zaanen and P. B. Littlewood, Phys. Rev. B **50**, 7222 (1994).