

Aging and scaling laws in β -hydroquinone-clathrate

Maikel C. Rheinstädter* and Klaus Knorr

Technische Physik, Universität des Saarlandes, PSF 1551150, 66041 Saarbrücken, Germany

Heiko Rieger

Theoretische Physik, Universität des Saarlandes, PSF 1551150, 66041 Saarbrücken, Germany

(Dated: November 19, 2018)

The dielectric permittivity of the orientational glass methanol($x=0.73$)- β -hydroquinone-clathrate has been studied as function of temperature and waiting time using different temperature-time-protocols. We study aging, rejuvenation and memory effects in the glassy phase and discuss similarities and differences to aging in spin-glasses. We argue that the diluted methanol-clathrate, although conceptually close to its magnetic pendants, takes an intermediate character between a true spin-glass and a pure random field system.

PACS numbers: 75.50.Lk, 77.22.Gm, 75.40.Gb, 64.70.Pf

I. INTRODUCTION

The long time evolution of the response functions of glassy systems has attracted a lot of attention and gave and gives rise to many discussions^{1,2,3}. The basic observation is that the behavior of the physical response functions, like magnetization, polarization or the corresponding susceptibilities, is time and waiting time dependent. It depends on a waiting time t_w spent before a perturbation (a magnetic or electric field) has been applied or after it has been switched off. A spin-glass can even memorize some of the features of the way the system had been prepared. While in the beginning theoretical and experimental work on *physical aging* mainly concentrated on aging phenomena in polymer glasses⁴, a lot of effort has been made to carry out and understand experiments in other glassy systems, like spin-glasses⁵, pure and disordered ferromagnets⁶, supercooled organic liquids such as glycerol⁷, relaxor ferroelectrics⁸ and (crystalline) dipolar glasses^{9,10}. The differences and the things in common between aging in these systems are still intensively discussed. It is not clear which ingredients on a microscopic scale have to be included to observe aging, rejuvenation- and memory-effects. In the present paper we present aging, rejuvenation and memory experiments in a dipolar glass, namely methanol($x=0.73$)- β -hydroquinone-clathrate.

The quinol $\text{HO-C}_6\text{H}_4\text{-OH}$ molecules form a hydrogen bonded $R\bar{3}$ lattice with almost spherical cavities of 4.2 Å diameter. The host lattice tolerates methanol concentrations down to $x=0.35$ without collapsing, x being the ratio of filled to available cavities. Whereas the higher concentrated methanol-clathrates undergo a first order phase transition into an antiferroelectrically ordered low-temperature phase, the clathrates with lower concentrations ($x \leq 0.76$) freeze into dipolar glass states^{11,12}. In methanol($x=0.73$)- β -hydroquinone-clathrate, the freezing of the dipoles is at least to some part a collective process as the molecules do not only see the crystal field of the cavity but also a contribution from the electric interaction between the dipoles^{11,12}. In this sense the

methanol($x=0.73$)-clathrate is conceptually close to its magnetic pendants, the spin-glasses. Within the hexagonal basal plane, the dipoles ("pseudospins") are arranged on a triangular lattice. Together with the quasi-antiferroelectric long-ranged dipole-dipole interaction in the basal plane, the dilution leads to strong frustration and to a large number of metastable states. Although there is no clear transition into a glassy phase, we find slow glassy dynamics at low temperatures.

Our first investigation¹³ of aging phenomena in methanol-hydroquinone-clathrates produced qualitative evidence for aging, rejuvenation and memory effects. In the present article we investigate the frequency dependence of isothermal aging (Sect. II A and II B) and study rejuvenation and aging in a more quantitative way by following special time-temperature protocols in Sect. II C.

II. EXPERIMENTAL RESULTS

Single crystals of methanol($x=0.73$)- β -hydroquinone-clathrate have been grown from a saturated solution of quinol, methanol and n-propanol at 313 K. The propanol molecules are not incorporated into the lattice but merely control the percentage of void cavities. The samples were prepared in the form of thin parallel plates ($d \sim 0.5$ mm) with faces perpendicular to the hexagonal c -axis. With gold electrodes deposited on these faces they formed capacitors with a capacitance of about 0.4 pF. For the measurement of the frequency-dependent permittivity, a Solartron impedance analyzer FRA 1260 in combination with an interface (Chelsea) has been employed. The samples were placed into a closed-cycle refrigerator with a temperature stability of some mK.

We measured real and imaginary part of the dielectric constant, $\epsilon'_c(\nu)$ and $\epsilon''_c(\nu)$, along the hexagonal c -axis for frequencies from $\nu = 0.2$ Hz up to $\nu = 200$ Hz. Figure 1 shows the temperature dependence of the imaginary part, $\epsilon''_c(\nu)$. The relaxation processes are characterized by a rather broad distribution of relaxation times τ and obey an Arrhenius law $\tau^{-1} \sim \tau_0^{-1} \exp(-E_A/T)$ (with

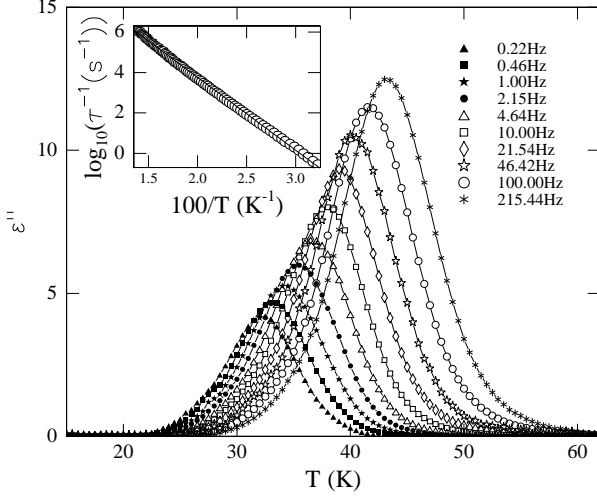


FIG. 1: Temperature dependence of the imaginary part of the dielectric permittivity, $\varepsilon''(\nu)$. (From [13]). The inset shows the inverse average relaxation time τ^{-1} as a function of $1/T$ (determined from the temperature of maximum ε'').

the "pseudospin" flip-rate $\tau_0^{-1} = 9 \cdot 10^{10} s^{-1}$ and an energy barrier $E_A = 828$ K) rather than a Vogel-Fulcher-behavior, see inset of Fig. 1. Although there is no clear transition into a dipolar glass state we find glassy dynamics at low temperatures. The effective energy barrier E_A decomposes into a contribution of the crystal field (E_{loc}) and a contribution of the interaction between the dipoles, $E_A \approx E_{loc} + 4J_c$, J_c being a coupling parameter¹¹. In our sample, the freezing is dominated by random interactions ($E_{loc} \approx 210$ K, $4J_c \approx 620$ K) and should be close to spin-glass-like. Figure 2 shows the real part of the dielectric constant $\varepsilon'_c(\nu)$ for selected frequencies ν from $\nu=0.1$ Hz to $\nu=1$ MHz. As can be seen from this figure it is only below about 40 K that the 0.1 Hz and the 1 Hz curves split. Thus the 0.1 Hz curve represents the static dielectric response for temperatures above 40 K. The maximum at about 55 K is a property of the static permittivity that signals the onset of short range antiferroelectric ordering.

A. Isothermal aging

The first experiments refer to isothermal aging and serve to characterizing the isothermal time evolution of the dielectric constant. The system was heated to a high temperature $T = 80$ K to erase a possible thermal history. We then cooled down with a fast rate of $|\Delta T/\Delta t| = 7$ K/min to the measurement temperature T_a . We chose $T_a = 30$ K, 32 K and 34 K, where $\varepsilon''_c(\nu)$ has reasonable high values for the selected frequencies between $\nu = 0.2$ Hz and 200 Hz. The temperature was then kept constant for the aging time $t_a = 3$ days. During the aging process, $\varepsilon'_c(\nu)$ and $\varepsilon''_c(\nu)$ were continuously measured for frequen-

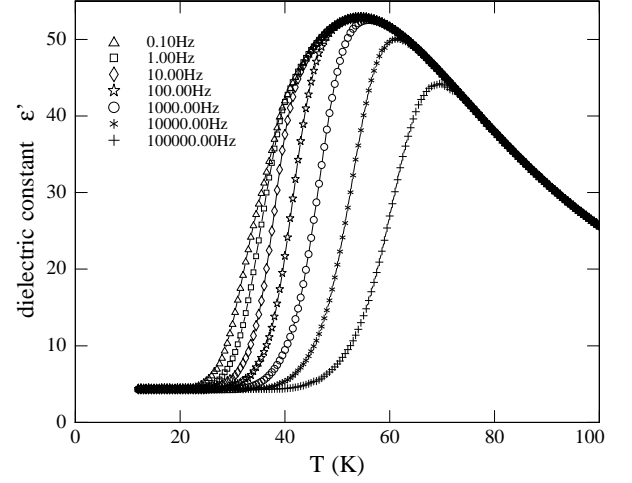


FIG. 2: Temperature dependence of the real part of the dielectric constant, $\varepsilon'_c(\nu)$.

cies from $\nu = 0.2$ Hz to $\nu = 200$ Hz. From their measurements on the dipolar glass $K_{1-x}Li_xTaO_3$ Alberici *et al.*^{9,10,14,15} find that the time evolution of the dielectric constant is well described by a power law

$$\varepsilon'(\nu, t) = \varepsilon'(\nu, \infty) + \Delta\varepsilon' \left(\frac{t_w + t_0}{t_0} \right)^{-\alpha}. \quad (1)$$

$\varepsilon'(\nu, \infty)$ is the asymptotic limit at infinite time, $\Delta\varepsilon'$ measures the magnitude of the time dependent part and α characterizes the decay. Because cooling, heating and stabilizing the temperature always takes some time, the start of an aging experiment is not well defined. The time $t_0 (> 1)$ takes into account a possible delay of the equilibrium of the temperature across the sample and the sample cell. The evolution of both imaginary and real part of the permittivity for all frequencies and all temperatures is well described by Eq. (1). See Table I for the fit parameters and Fig. 3 for the $\nu=0.2$ Hz-data on the real and imaginary part of the permittivity measured at $T_a=30, 32, 34$ K. For each combination of T and ν we obtain about the same values of t_0 and α from fits to $\varepsilon'(t)$ and $\varepsilon''(t)$. On the other hand t_0 and α depend strongly on T (and slightly on ν). t_0 varies from about 900 s at 34 K to 5000 s at 30 K. The temperature equilibration time of our setup is of the order of some minutes. t_0 is clearly larger than that. Obviously the equilibration between the thermal bath and the polar degrees of freedom of the sample takes somewhat longer. The exponent α of the power law decay increases with decreasing T . A fit of a linear T -dependence

$$\alpha(T) = A|(T_c - T)/T| \quad (2)$$

(with a parameter A of $A=-0.05$.) to the data (Fig. 4) suggests a characteristic temperature T_c of about 38 K above which aging no longer occurs. Also experimen-

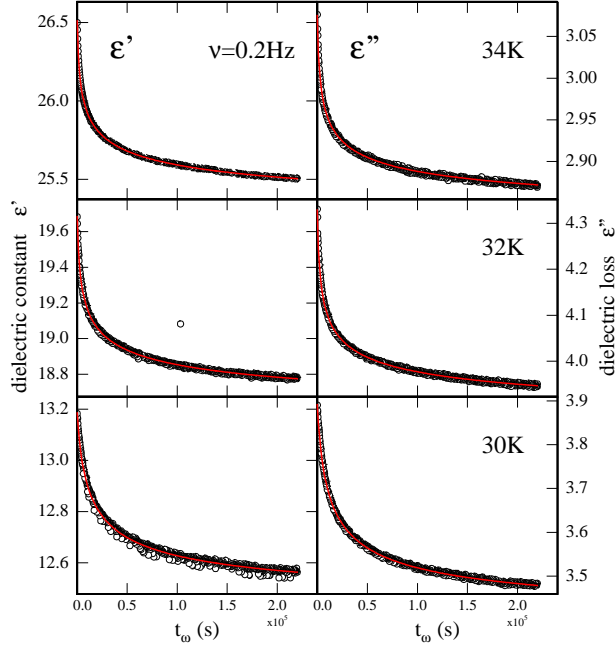


FIG. 3: (Color online) Isothermal time evolution of the imaginary part of the 0.2 Hz-permittivity after quenching the sample from 80 K to $T_a = 30$ K, 32 K and 34 K, respectively. Solid lines are fits after Eq. (1).

T (K)	ν (Hz)	ϵ'_∞	$\Delta\epsilon'$	α'	t'_0	ϵ''_∞	$\Delta\epsilon''$	α''	t''_0
30	0.2	12.37	0.81	0.37	4800	3.37	0.53	0.40	4800
	2	7.95	0.25	0.41	4750	2.28	0.24	0.42	5250
	20	5.67	0.05	0.35	5250	1.24	0.08	0.37	5250
32	0.2	18.40	1.28	0.24	1400	3.83	0.49	0.28	1400
	2	11.8	0.50	0.22	1600	3.97	0.39	0.27	1600
	20	7.22	0.12	0.24	1600	2.27	0.15	0.23	1500
34	0.2	24.96	1.56	0.19	900	2.79	0.29	0.22	900
	2	18.09	1.01	0.15	900	5.36	0.47	0.20	900
	20	10.31	0.26	0.19	900	4.01	0.30	0.16	700

TABLE I: Fitparameter for the frequencies $\nu=0.2$ Hz, 2Hz and 20 Hz for temperatures $T=30$ K, 32 K and 34 K. The ϵ' -values indicate results for the real-, the ϵ'' -values for the imaginary part. $\delta=\Delta\epsilon''/(\epsilon''_\infty + \Delta\epsilon'')$ gives the relative strength of the aging process in the imaginary part.

tally we find a temperature of about $T=38$ K above which we do not observe aging behavior. This is confirmed by direct observation: Fig. 5 shows an aging experiment at $T=40$ K for frequencies ν of $\nu=2$ Hz, 20 Hz and 200 Hz where the dielectric loss remains constant in time. Because the effect of aging is more pronounced in the imaginary part $\epsilon''_c(\nu)$, we will in the following experiments concentrate on this.

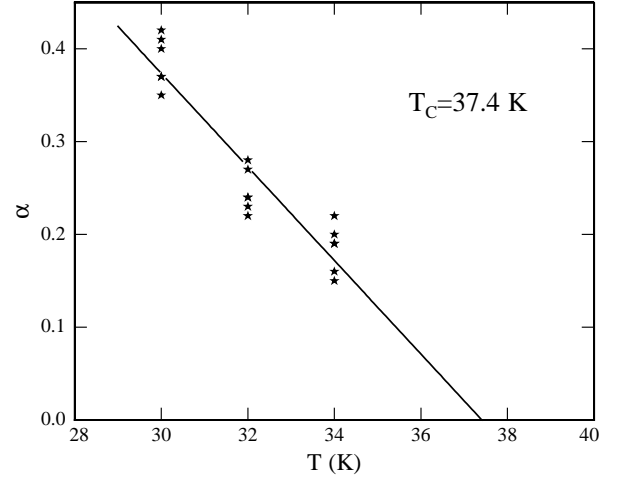


FIG. 4: Temperature dependence of the exponent α of the power law for isothermal aging (Eq. (1)). The symbols (*) indicate the values fitted for α' and α'' from Table I for the different frequencies for the respective temperature. The linear fit points to a critical temperature of $T_c=37.4$ K.

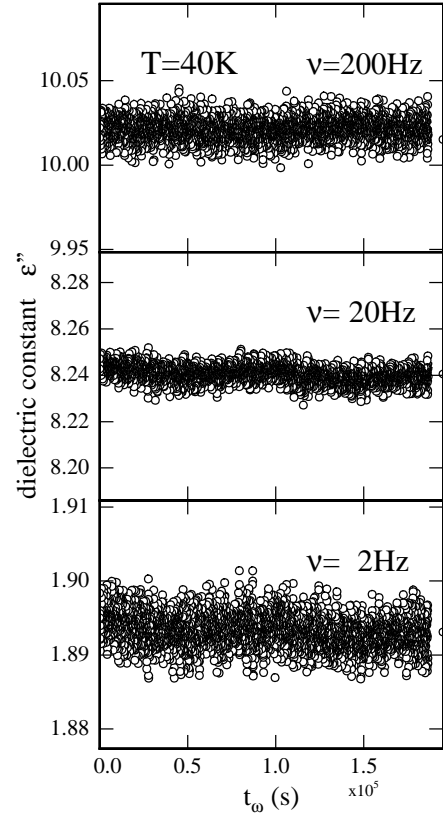


FIG. 5: Time evolution of the dielectric loss ϵ'' at $T=40$ K for $\nu=2$ Hz, 20 Hz and 200 Hz. ϵ'' stays constant in time and there is no aging behavior.

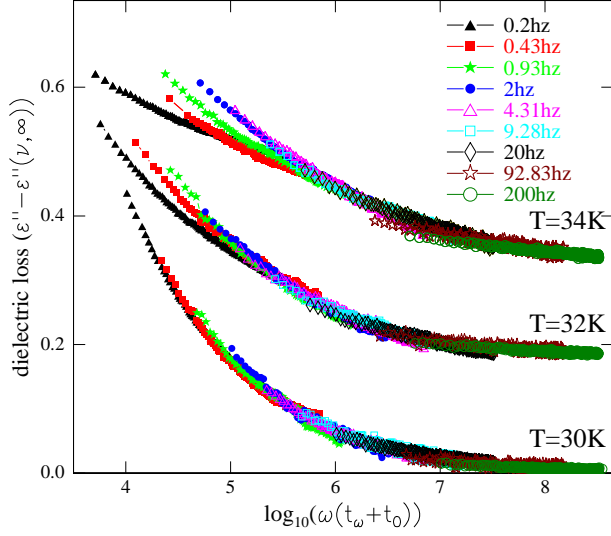


FIG. 6: (Color online) $\varepsilon'' - \varepsilon''(\nu, \infty)$ vs. $\omega(t_w + t_0)$ in a linear-logarithmic scale (ωt_w -scaling) for the temperatures $T_a = 30$ K, 32 K und 34 K and frequencies from ν von 0.2 Hz to $\nu = 200$ Hz.

B. Scaling experiments

In spin-glasses an ωt_w scaling is observed, i.e. the aging curves for different frequencies fall on a single master curve if the waiting time t_w is multiplied by the applied angular frequency ω , ($\omega = 2\pi\nu$). In orientational glasses there often is a deviation from ωt_w -scaling, indicating that microscopic time scales are still relevant for the aging process. In Fig. 6, $\varepsilon'' - \varepsilon''(\nu, \infty)$ is plotted versus $\omega(t_w + t_0)$ in a linear-logarithmic scale. The values for $\varepsilon''(\nu, \infty)$ and t_0 are the ones obtained from the fits of Eq. (1) to the data. For $T_a = 32$ and 34 K the data taken at lower frequencies still do show aging but no longer obey ωt_w -scaling, the deviations increase with decreasing ν . The Arrhenius law of Fig. 1 translates into a boundary $\nu_0(T)$ in the T, ν -plane separating the regimes in which the dipoles are mobile or frozen in the sense that they can or cannot follow the oscillations of the applied electric field (Fig. 7). ν_0 is the most probable relaxation rate at the chosen temperature. Since the distribution of relaxation rates extends over several decades¹² the crossover from mobile to frozen states is rather gradual and we still observe aging for ν, T combinations well below the $\nu_0(T)$ boundary, that is deep in the mobile regime. It is only at temperatures above about 38 K that aging effects can no longer be resolved in the frequency range of the present study. See Fig. 5 for $T = 40$ K. For the ωt_w -scaling, however, the distinction of frozen and mobile states given by the $\nu_0(T)$ boundary appears to be quite reliable. At 30 K all measuring frequencies chosen fall into the frozen regime, $\nu > \nu_0(T)$, thus the ωt_w -scaling holds for all measuring frequencies used. For 32 and 34 K only data with

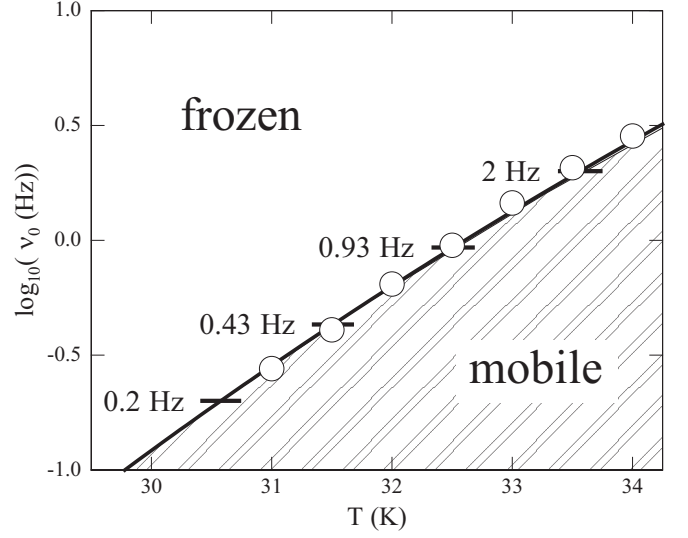


FIG. 7: Freezing line that separates frozen from mobile states. The solid line is the Arrhenius-law after Fig. 1, the points are corresponding experimental data. Measurement frequencies are marked.

$\nu > \nu_0(T)$ obey scaling.

C. Rejuvenation and memory

If the system has aged at a temperature T_1 in the frozen regime and the temperature is changed thereafter to a new value T_2 , it may forget that it has aged at T_1 . This is rejuvenation. For perfect rejuvenation the values of the quantity of interest (here ε'') at T_2 are the same with and without aging at T_1 . Returning to T_1 the system may remember that it has aged at this temperature before. In case of perfect memory the value of ε'' after returning to T_2 is identical to the final value of the previous aging at this temperature. If T_2 is well in the mobile regime, rejuvenation and the loss of memory is complete and on returning to T_1 the system is re-initialized. Thus the effects of rejuvenation and memory are typically probed by a temperature-time protocol consisting of isothermal aging over time periods t_1, t_2, t_3 at temperatures T_1, T_2, T_1 with $T_2 = T_1 + dT$. In the clathrate the ν, T -regime in which the dipole system is frozen but where on the other hand $\varepsilon''(T, \nu)$ is sufficiently large such that the slight changes of ε'' brought forth by aging can be studied with a reasonable resolution is rather narrow. We have chosen $\nu = 0.2$ Hz, $T_1 = 30$ K and $dT = +2, +1, -1, -2$ K in combination with periods $t_1 = t_2 = t_3 = 30$ h (and realize that for $dT = 2$ K, $T_2 = 32$ K the system is already mobile if one strictly refers to the $\nu_0(T)$ boundary of Fig. 7). The results are shown in Fig. 8, including a reference curve where aging has not been interrupted by a T -excursion, that is with $dT = 0$. The initial state at the beginning of the first period has been approached by rapid cooling out of the

mobile regime at 80 K by cooling down with a rate of 7 K/min. For the changes from T_1 to T_2 and back to T_1 the rate was 1 K/min. The t_2 -section of the curves has been shifted vertically by arbitrary amounts in order to present the results on a sufficiently expanded scale, but the absolute values of ε'' in this interval can be recovered since the start values are indicated in the Figs. The results on the t_1 -interval are of course independent on the subsequent value of the temperature excursion dT and reproduce what has been shown already in Fig. 3. The start values of the t_2 -interval are close but not quite identical to what is obtained by measuring the dielectric response on continuous heating or cooling. ε'' at $T=32$ K for $\nu=0.2$ Hz may serve as an example. Without previous aging a value of about 4.3 is obtained as shown in Fig. 3. After aging at 30 K for 30 h, ε'' recovers from a value of about 3.5 at the end of 30 K-aging t_1 -period to 4.1 at 32 K. Thus there is rejuvenation, but rejuvenation is not complete meaning that the age of the system at the temperature T_2 depends somewhat on the former aging at the temperature T_1 . As shown already in Ref. [13] complete rejuvenation is only observed for T -changes dT large enough. Bringing the sample back to $T_1=30$ K in Fig. 8 after the excursion to T_2 the response is not re-initialized but the system remembers that it has aged at this temperature before. In fact the aging curves of the t_3 -interval are quite close to the reference curve for which aging has not been interrupted by a temporary T -excursion. This statement holds independent of whether dT and the change $d\varepsilon''$ of ε'' induced by changing the temperature from T_1 to T_2 is positive or negative. A closer inspection shows however that the curves of the t_3 -interval are slightly shifted with respect to the reference curve, upward for $dT<0$, $d\varepsilon<0$ and downward for $dT>0$, $d\varepsilon>0$. Note that the sign of shift is opposite to that of $d\varepsilon$. Thus there is memory not only of the t_1 -period but also a residual one of the t_2 -period. Surprisingly it is not the sign of $d\varepsilon''$ what the system remembers. We propose to refer instead to the age at the temperature T_1 being modified by the excursion to the temperature T_2 . For this purpose the curves of the t_3 -interval are shifted horizontally until they coincide with the reference curve. For $dT<0$ this shift is about $0.5 \cdot 10^5$ s to the left. Thus intermediate aging at temperatures somewhat lower than T_1 contributes to the age at T_1 but is only about half as effective as the aging at T_1 . For $dT>0$ aging at T_2 is more effective than aging at T_1 for the same time span, the effective age is increased by $t=6.5 \cdot 10^4$ s for $dT=1$ K and by $1.1 \cdot 10^5$ for $dT=2$ K.

Figure 9 shows analogous data for a slightly higher base temperature T_1 of 32 K. Most temperatures of relevance for this experiment are already in the mobile regime of Fig. 7. Nevertheless the results are quite similar to those shown in Fig. 8, except that the starting value of the t_3 -interval after an excursion to 34 K is higher than the final value of the t_1 -interval. Obviously an excursion to such a high temperature has partially erased the memory and has lead to first traces of re-initialization.

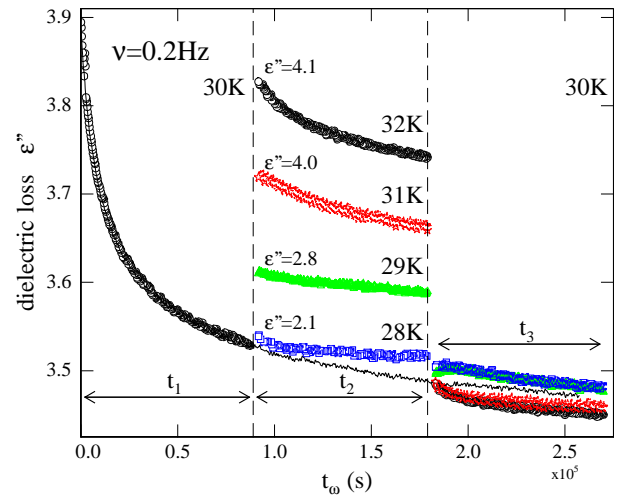


FIG. 8: (Color online) Temperature-cycling-experiment for $\nu = 0.2$ Hz and starting temperature $T = 30$ K. The curves in interval t_2 are shifted by arbitrary values of ε'' , the original values are given in the Figure.

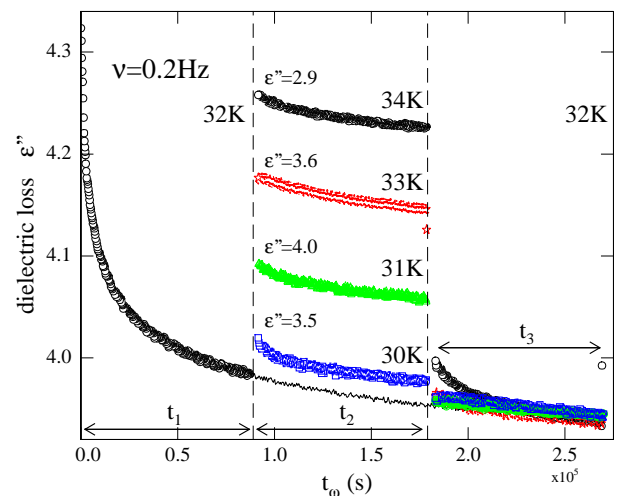


FIG. 9: (Color online) Analogous to Fig. 8 with a base temperature of $T_1=32$ K.

III. DISCUSSION

We find aging, rejuvenation and memory in methanol-($x=0.73$)- β -hydroquinone-clathrate similar to the effects in spin-glasses. Although there is no experimental evidence for a sharp glass *transition* in our system, we observe a strong increase in the relaxation time with decreasing temperature. Below 32K our system is out of equilibrium for all relevant experimental time scales and the dynamics has pronounced glassy features: In temperature cycle experiments we observed rejuvenation as well as memory effects. Since our system is randomly diluted

the dipolar interactions between the moments lead to the presence of a strong frustration due to a random mixture of ferro- and antiferroelectric interactions.

Two different theoretical explanations for the aging phenomena were put forward in the context of spin-glasses: In the droplet theory¹⁶ rejuvenation is explained by the assumption of a finite overlap length beyond which two equilibrium configuration at different temperatures are decorrelated — a scenario that also goes under the name *chaos in spin-glasses*^{16,17}. Strong rejuvenation effects necessitate in this simplified picture a very small overlap length: If it would be much larger than the length-scales that have been equilibrated during a particular waiting time, the chaotic rearrangements due to the temperature shift become invisible. However, there still might be some effect due to dangerously irrelevant droplets whose free energy gaps are quite small, as discussed in^{18,19,20,21}.

An alternative picture is the one presented in^{3,22,23}. Here rejuvenation after a negative temperature shift comes from fast modes equilibrated at T_1 , but fall out of equilibrium and are slow at T_2 . Therefore, one should expect to see this phenomenon if the equilibrated regions (on length scales $\leq L_{T_1}(t_w)$) are sufficiently different at the two temperatures. This mechanism is obviously qualitatively different from the interpretation involving the notion of temperature chaos (see above), which implies that length scale smaller than the overlap length are essentially unaffected by the temperature shift, while larger length scales are completely reshuffled by the shift.

Moreover, within this picture the memory effect that we observe in our temperature cycle experiments is a simple consequence of the separation of time and length scales. When the system is at $T_2 < T_1$, rejuvenation involves very small length scales as compared to the length scales involved in the aging at T_1 . Thus when the temperature is shifted back to T_1 , the correlation of length scale $L_{T_2}(t'_s)$ nearly instantaneously re-equilibrate at T_1 . The memory is just stored in the intermediate length scales, between $L_{T_2}(t'_s)$ and $L_{T_1}(t_s)$.

The latter model accounts well for the aging effects observed in spin-glasses. Strong random fields presumably destroy the spin-glass character. In orientational glasses, in which the dipole dynamics is usually strongly influenced by local crystal fields, which are randomly distributed from site to site ("random fields"), aging effects might be more appropriately described by a slow domain growth, where the domain wall movement is impeded by the inhomogeneous crystal fields. In this case the objects that are subject to reconformations due to temperature changes are only the domain walls whereas in spin glasses one expects that it is the whole bulk of the domains.

In the present case local random fields arise from the partial occupation. The neighborhood of statistically empty and filled cavities leads to a random distortion of the crystal field in the cages. Considering this special feature of dipolar glasses, aging in the dipolar glass $K_{1-x}Li_xTaO_3$ has been explained by Alberici *et al.*^{9,10}

by a domain model. They assume the existence of polarization domains, i.e. regions of strongly coupled dipoles (even though the interaction is random and the *domains* will not be comparable to ordered domains as e.g. in a ferromagnet). During the process of domain growth the domain walls have to overcome energy barriers via thermal activation, in close analogy what is supposed to happen in random field systems²⁴ as well as in the droplet theory for spin glasses¹⁶. Only molecules in the domain walls contribute to the dielectric response, molecules from inside the domains are already frozen. The dielectric response ϵ'' is inversely proportional to the domain size R , $\epsilon'' \propto 1/R(t)$, as the volume fraction of wall molecules reduces when domains grow. For each temperature T there is an equilibrium domain size $\xi(T)$. ξ is the larger the lower the temperature, $\xi(T) \propto 1/\sqrt{T}$. All domains grow towards their equilibrium size; the evolution stops when they have reached $\xi(T)$. When the temperature is increased the equilibrium correlation length decreases and it might happen that some of the domains have grown beyond this lengths scale and have to adjust, i.e. shrink. For domains with size $R(t, T)$ larger than $\xi(T)$ shrinking would be a very slow process because they have to overcome large energy barriers. A more efficient scenario would be the nucleation of small domains (with sizes of the order of the lattice spacing) within the larger domains and a rapid initial growth. In this way nucleation would generate new domain walls giving rise to the overshoot of the dielectric response in time interval t_3 of the temperature cycling experiments in Fig. 8.

Matsuo and Suga²⁵ find for β -hydroquinone-clathrates with various polar guest molecules a proportionality between the transition temperature, where the dipole system orders, and the square of the dipole moment, i.e. between the thermal energy and the energy of the dipolar interaction between the guest molecules. This suggests that the dipole-dipole interaction between the guest molecules plays the leading role for the dielectric behavior. From measurements of the methanol($x=0.97$), ($x=0.84$) and ($x=0.79$) samples¹¹, the (hypothetical) transition temperature of the methanol($x=0.73$)- β -hydroquinone-clathrate can be estimated to about $T=38$ K, where molecular reorientations should slow down drastically. The critical temperature T_c that arises from the dielectric experiments agrees quite well with the experimental finding suggesting that the collective dipolar interactions lead to aging, memory and rejuvenation.

IV. CONCLUSIONS

We present dielectric measurements with different temperature-time protocols to study aging effects in the dipolar glass methanol($x=0.73$)- β -hydroquinone-clathrate. We find aging, rejuvenation and memory effects, although there is no experimental evidence for a sharp glass transition. The diluted methanol clathrate is

conceptually close to its magnetic pendants, the spin-glasses. The electrical behavior is dominated by the dipole-dipole interactions of the guest molecules but the coupling of the pseudospins to random fields is not negligible. We argue that the diluted methanol-clathrate takes an somehow intermediate character between a true spin-glass and a pure random field system. The influence of random fields can not be neglected as the effects are much broader than the corresponding effects in spin glasses (e.g. in $\text{CdCr}_{1.7}\text{In}_{0.3}\text{S}_4$, see Ref. [5]) and the overshoot in the time interval t_3 is well explained by

the domain model. Furthermore, memory is preserved at moderate temperature increase opposed to the observations in spin-glasses. On the other hand the ωt_w -scaling at low temperatures and the temperature dependence of the fitting parameter α resemble the effects found in spin-glasses and suggest a random bond dominated system. Aging, rejuvenation and memory effects can just be observed below a temperature at which the dipolar motions are expected to slow down and collective dipolar interactions become dominant.

-
- * Present address: Institut Laue-Langevin, 6 rue Jules Horowitz, BP 156, 38042 Grenoble Cedex 9, France; Electronic address: rheinstaedter@ill.fr
- ¹ E. Vincent, J. Hammann, M. Ocop, J. Bouchaud, and L. Cugliandolo, *Complex behaviour of glassy systems* (Springer Verlag Lecture Notes in Physics Vol.492, 1998), chap. Slow dynamics and aging in spin-glasses, pp. 184–219.
 - ² J. Bouchaud, L. Cugliandolo, J. Kurchan, and M. Ézard, *Spin Glasses and Random Fields* (World Scientific, Singapore, 1997), chap. Out of equilibrium dynamics in spin-glasses and other glassy systems.
 - ³ J. Bouchaud, *Soft and Fragile Matter: Nonequilibrium Dynamics, Metastability and Flow* (IOP Publishing, Bristol and Philadelphia, 2000), chap. Aging in glassy systems: new experiments, simple models and open questions, pp. 285–304.
 - ⁴ L. Struik, *Physical Aging in Amorphous Polymers and other materials* (Elsevier, North-Holland, 1978).
 - ⁵ K. Jonason, E. Vincent, J. Hammann, J. Bouchaud, and P. Nordblad, Phys. Rev. Lett. **81**, 3243 (1998).
 - ⁶ E. Vincent, V. Dupuis, M. Alba, J. Hamman, and J. Bouchaud, Europhys. Lett. **50**, 674 (2000).
 - ⁷ R. Leheny and S. Nagel, Phys. Rev. B **57**, 5154 (1998).
 - ⁸ E. Colla, L. Chao, M. Weissman, and D. Viehland, Phys. Rev. Lett. **85**, 3033 (2000).
 - ⁹ F. Alberici-Kious, J. Bouchaud, L. Cugliandolo, P. Doussineau, and A. Levelut, Phys. Rev. Lett. **81**, 4987 (1998).
 - ¹⁰ F. Alberici-Kious, J. Bouchaud, L. Cugliandolo, P. Doussineau, and A. Levelut, Phys. Rev. B **62**, 14766 (2000).
 - ¹¹ H. Woll, M. Enderle, A. Klöpperpieper, M. Rheinstädter, K. Kiefer, Kruchten, and K. Knorr, Europhys. Lett. **51**, 407 (2000).
 - ¹² H. Woll, M. Rheinstädter, F. Kruchten, K. Kiefer, M. Enderle, A. Klöpperpieper, J. Albers, and K. Knorr, Phys. Rev. B **63**, 224202 (2001).
 - ¹³ A. Kityk, M. Rheinstädter, K. Knorr, and H. Rieger, Phys. Rev. B **65**, 144415 (2002).
 - ¹⁴ F. Alberici, P. Doussineau, and A. Levelut, Europhys. Lett. **39**, 329 (1997).
 - ¹⁵ F. Alberici, P. Doussineau, and A. Levelut, J. Phys. I France **7**, 329 (1997).
 - ¹⁶ D. Fisher and D. Huse, Phys. Rev. B **38**, 373 and 386 (1988).
 - ¹⁷ A. Bray and M. Moore, Phys. Rev. Lett. **58**, 57 (1987).
 - ¹⁸ H. Yoshino, K. Hukushima, and H. Takayama, Phys. Rev. B **66**, 064431 (2002).
 - ¹⁹ P. Jönsson, H. Yoshino, and P. Nordblad, Phys. Rev. Lett. **89**, 097201 (2002).
 - ²⁰ P. Jönsson, H. Yoshino, and P. Nordblad, Phys. Rev. Lett. **90**, 059702 (2003).
 - ²¹ H. Yoshino, K. Hukushima, and H. Takayama, cond-mat/0202110 (2002).
 - ²² L. Cugliandolo and J. Kurchan, Phys. Rev. B **60**, 922 (1999).
 - ²³ L. Berthier and J.-P. Bouchaud, Phys. Rev. B **66**, 054404 (2002).
 - ²⁴ D. Fisher, Phys. Rev. Lett. **56**, 472 (1986).
 - ²⁵ T. Matsuo and H. Suga, J. Incl. Phen. **2**, 49 (1984).