Electronic band structure of novel 18-K superconductor Y_2C_3 as compared with YC and YC₂.

I.R. Shein* and A.L. Ivanovskii

Institute of Solid State Chemistry, Ural Branch of the Russian Academy of Sciences, 620219, Ekaterinburg, Russia

The electronic band structure of yttrium sesquicarbide Y_2C_3 (Pu₂C₃ structural type) reported by Akimitsu et al. (2003) as a novel 18-K superconductor is investigated using the first-principle full-potential LMTO method and compared with those of yttrium mono- and dicarbide: cubic YC and 4-K superconductor YC₂ (CaC₂ structural type). Our results show that the enhanced T_c of Y₂C₃ as compared with YC₂ may be interpreted by the electronic factors: the near-Fermi DOS for Y₂C₃ was found to be about 70 % higher that for YC₂, and the contribution from the C2p states increases. The Fermi level of the "ideal" bcc Y₂C₃ is located near the local DOS minimum, and the superconducting properties of Y₂C₃-based materials would be very sensitive to synthesis conditions and the presence of impurities and lattice vacancies. We suppose that by changing these factors it is possible to vary T_c for the yttrium sesquicarbide.

* E-mail: shein@ihim.uran.ru

PACS numbers: 74.70.-b,71.20.-b

I. Introduction.

Metal carbides represent a technologically important group of materials with interesting properties including extreme hardness, high melting temperatures, and superconductivity¹.

Among superconducting binary compounds, metal carbides are known as conventional low-temperature BCS superconductors (SC) and have long been examined². Comparison of different classes of binary carbides: semi- (M_2C) , mono- (MC), sesqui- (M_2C_3) , and disarbides (MC_2) shows (reviews^{2,3}) that the majority of the known superconductors are found among cubic compounds with a rock-salt structure (B1), in which C and M atoms are in octahedral surrounding. Among these phases, the maximum values of transition temperatures T_c belong to Ta (10.2), W (10 K), Nb (11.1), and Mo (14.3 K) monocarbides³. Using the first-principle band structure calculations results, it was proposed that B1-MoC (isoelectronic and isostructural to the 16.6-K superconductor NbN³) was the prime candidate for the "highest-temperature" SC among all familiar metal carbides with a predicted transition temperature of about 20 K^4 .

The superconducting state is much less pronounced for the dicarbides, in which C atoms are in the form of isolated C_2 pairs. Among metal dicarbides, the low-temperature SC was observed only for three compounds MC_2 (M = Y, La, Lu) with the highest T_c value of 3.9 K for YC_2 ³. In addition, some superconducting metal sesquicarbides have been also described, for example several compounds with T_c of about 11 K (La₂C_{2.7} and Y_2C_3) and 15 K (Lu₂C₃)³.

The interest in the properties of the yttrium carbide systems increased in the past years due to the discovery of superconductivity with transition temperatures up to 11.6 K in the layered yttrium carbide halides $Y_2C_2I_2$ ($T_c = 9.97$ K) and $Y_2C_2Br_2$ ($T_c = 5.04$ K)⁵ and

also because of the observation of superconductivity with T_c ~ 15-23 K^{6,7} in more complex systems: Y-Ni and Y-Pd-based borocarbides, see also reviews^{8,9,10}. In this context, binary and quasi-binary Y carbides (especially Th-doped yttrium dicarbide $(Y_{1-x}Th_x)C_2^{13}$) also attracted particular attention since their T_c values are close to those of A15 compounds^{2,3}.

Quite recently, Akimitsu et al 12 have carried out a high-pressure synthesis of a novel superconducting phase in the Y-C system with T_c of about 18 K and assumed that this 18-K SC originated in the yttrium sesquicarbide Y_2C_3 with the body-centered cubic (bcc) Pu_2C_3 -type crystal structure.

The value of T_c for Y_2C_3 obtained in magnetic measurements¹⁴ was reported earlier to be 11 K. It was pointed out¹³ that the superconductivity in the Y-C vttrium system is very sensitive to the synthesis conditions, for instance pressure and heat treatment. In particular, the effect of carbon nonstoichiometry was observed. In Ref. 14, the bcc Y₂C₃ has been synthesized by arc-melting and high-pressure techniques. Magnetic susceptibility showed that the material exhibited superconductivity with variable T_c ranging from 6 K to 11.5 K. In Ref. 12, the superconducting Y_2C_3 phase was prepared under high pressure using mixed powders (Y+C) in a BN cell. It is noteworthy that the lattice parameter (a) changes for different sintering processes and exists in the range between 0.8181 and 0.8226 nm¹² as distinct from earlier findings $(0.8214 - 0.8251 \text{ nm})^{13}$. One of the reasons may be the difference in the pressure range (4-5.5¹² compared with 1.5-2.5 GPa¹³). Furthermore, the authors 14 successfully reproduced the result 12 and reported the synthesis of the 18-K phase with some differences in the experimental technique. In addition, a sample with the nominal composition Y₂C_{2.9}B_{0.1} was prepared to check a possible role of boron impurities from the BN cell used in the experiments¹². According to data¹⁴, the 18-K phase coexists with another phase (the 11-K phase reported in¹³) having a trace of a low- T_c phase (4 K). This "impurity" phase is YC_2 . Moreover, the T_c for the boron-doped sample (16.4 K) is lower than that of the "pure" carbide. This means that boron impurities in the C positions play a negative role in the Y-C superconductivity. It was also reported that the magnetization (M-H) curves of the 18-K Y₂C₃ phase showed a type-II superconducting behavior 12. While an explanation for the observed 12,14 behavior in the 18-K material based on a microscopic theory is still lacking, it is necessary to perform comparative studies of the electronic properties of yttrium carbide phases. In this paper, we report the theoretical results related to the electronic band structure of bcc Y₂C₃ in comparison with other yttrium carbide phases, namely the B1 monocarbide YC and 4-K SC YC2. The electronic bands, density of states (DOS) and site-projected l-decomposed DOS near the Fermi energy (E_F) of these carbides are obtained and analyzed as a function of structures and nominal stoichiometry: YC (C/Y=1) > $Y_2C_3 (C/Y=1.5) > YC_2 (C/Y=2).$

II. Models and Method of Calculation.

The yttrium carbides have cubic (YC, Y_2C_3) and tetragonal (YC₂ - space group I4/mmm) crystal struc-The yttrium sesquicarbide crystallizes in a tures. bcc structure of the Pu₂O₃ type (space group I-43d) with the lattice parameter a = 0.8233 nm (ICSD-CC No.86290) and eight formula units per a unit cell¹⁵. The Wyckoff positions for atoms are Y:16c (0.05;0.05;0.05) and C:24d (0.2821;0;1/4). The band structure of the above-mentioned carbides was calculated using the scalar relativistic full-potential linear muffin-tin method (FLMTO)¹⁶ with the generalized gradient approximation (GGA) of Perdew et al. 17. The Y₂C₃ structural parameters are taken from Ref. 15. The equilibrium values of lattice constants obtained from minimum total energy and are a = 0.5076 nm for YC and a = 0.3699nm, c = 0.6140 nm, x = 0.3748 for YC_2 .

III. Results.

In Fig. 1 we show our FLMTO band structure of B1-YC. The YC band structure is very similar to that found for other rock-salt (B1) transition metal carbides, see for example 4,18,19,20 , consist from low-energy C2s band, does not contribute to the bonding. This band exhibits the maximum dispersion (2.35 eV) between Γ and L points. The next bands separated from the C2s band by a gap at about 3.34 eV originate mainly from mixed C2p-Y4d states. The Y4d bands are decomposed into \mathbf{e}_g and \mathbf{t}_{2g} components with energies 1.82 and 3.49 eV in Γ point above the Fermi level (E_F). In B1 carbides, the \mathbf{e}_g -like bands mixed with the C2p states are usually viewed as the bonding part of the d-p hybridization zone, while \mathbf{t}_{2g} - as the antibonding part overlapping the carbon 2p states 4,18,19,20 . The phase instability of

stoichiometric YC may be explained based on band filling²⁰. In YC, the Fermi level intersects the e_q -like bands. As a result, the bonding states remain partially unoccupied as distinct for example from the stable B1-ZrC phase, where all bonding states are occupied, whereas antibonding states, on the contrary, are unfilled. The density of states (per formula unit) at the Fermi level $N(E_F)$ is quite large (Table 1) and comparable with $N(E_F)$ of B1-NbC. At the same time their compositions are different: for YC the contributions from d and C2p states are comparable (Table 1), while the main role in NbC is played by metallic d states. Note also that inter-atomic bonds and charge distribution in B1-YC are quite isotropic, see Fig. 2. The electronic properties of yttrium dicarbide were studied earlier using the tight-binding linear muffin-tin orbital atomic-sphere approximation (TB-LMTO-ASA) calculations ^{11,21}. Our FLMTO YC₂ electronic bands and DOSs are shown in Figs. 3, 4 and agree well with those reported in 11,21 . The two lowest bands (Fig. 3) at about 14.4 and 7.1 eV below E_F are bonding and nonbonding C2s states respectively. The low-lying bonding C2s band with the maximal dispersion of 1.1 eV is separated from the next band group by a gap of about 6.4 eV. The combination of the $C2p_{x,y}$ orbitals forms the quasi-flat bands from Γ to Z with the DOS maximum around -4.2 eV, which are hybridized with the Yd_{xy} orbitals, Fig. 4. The $C2p_z$ states split up into two bands (peaks A, B in the partial DOS picture around -7.3 and -2.2 eV) hybridized with the Yd_{3z^2-1} states. All these bands contribute to the Y-C metal bonding and are completely occupied. The partially filled near-Fermi bands ($Y4_{yz,xz}$ in the region -2.0 eV \div E_F and Y4_{x²-y²} in the region -0.95 eV \div E_F) are strongly dispersive and are hybridized with the antibonding $C2p_{x,y}$ orbitals in the direction of axis c. The Fermi level intersects three bands near Γ , P, and Z points. These bands form the Fermi surface, which contains, in particular, hole sheets (around points Γ and Z), Fig. 5. The composition of $N(E_F)$ includes the contributions from the Yd_{xz,yz,x^2-y^2} , and $C2p_{x,y}$ orbitals, see Table 1. The value of the other Yd, C2p components, as well as of the Yp,s and C2s valence states are negligibly small. Thus the electronic structure and the chemical bonding type in vttrium mono- and dicarbide differ essentially: isotropic Y-C bonds in YC versus anisotropic Y-C and C-C bonds in YC2, see charge-density contour maps in Fig.2.

The calculated bands and DOS for Y_2C_3 are shown in Figs. 6, 7. The valence zone of Y_2C_3 contains four separated band groups (I-IV, Fig. 7). Bands (I) between -14.3 and -13.3 eV are bonding carbon 2s states, whereas antibonding C2s states (with an admixture of $C2p_x$ and Yd,p,s orbitals) form separate bands (II) in the region -7.1 \div -6.4 eV. The higher completely occupied band group (III) between -5.7 and - 2.4 eV comes from Yp,d and C2p orbitals. The Fermi level lies in the middle of bands (IV) composed mostly of Yd-C2p states. The bands intersecting the Fermi level form hole (around H

and N points) and electronic sheets of the Fermi surface. As in YC₂, the partial DOSs of Y₂C₃ demonstrated very anisotropic orbital states distributions (see also Table 1) depending on the non-equivalency of Y-C and C-C bonds (Fig. 8) and the structural peculiarities of the yttrium susquicarbide, which contains carbon pairs in different orientations 15 . Of special interest is a near-Fermi DOS Y₂C₃, since in the conventional BCS-type superconductors the DOS within the interval $E_F \pm h\Theta_D$ (Θ_D - Debye frequency) at the Fermi level is crucial for superconductivity, we show in Fig. 9 the density of states for Y₂C₃ within a small energy interval around E_F . As is seen from Fig. 9, E_F is in the region of DOS minimum between two sharp peaks A and B and falls to a local small DOS peak. Thus, both electronic and hole doping that change the position of E_F may decrease or increase $N(E_F)$ and accordingly T_c .

Simple estimations based on the rigid-band model show that E_F will coincide with maxima A and B, when about 0.7 holes or 0.5 additional electrons are introduced per formula unit of Y_2C_3 . As a result, $N(E_F)$ of these doped systems increases almost twice (by 89 and 98 % respectively in comparison with $N(E_F)$ of the stociometric yttrium sesquicarbide). This effect may be achieved by several means. The most probable approach is to dope the yttrium sublattice with donor or acceptor

dopants. The role of hole dopants may be played also by carbon vacancies. Another important factor $N(E_F)$ of the metastable Y₂C₃ phase may be pressure^{11,12,13}. The immediate prospects of our studies will involve simulation of pressure effects on fine peculiarities of the electronic band structure of Y₂C₃. In summary, our FLMTO calculations of the electronic band structure of the bcc yttrium sesquicarbide indicate that the enhanced transition temperature as compared with YC₂ may be due to electronic factors: the DOS at the Fermi level for Y₂C₃ was found to be about 40 % higher than that for 4-K SC YC₂, Table 1. In addition, the contribution from the C2p states increases appreciably. Since the Fermi level of the "ideal" bcc yttrium sesquicarbide is located near the local DOS minimum, the superconducting properties of Y₂C₃-based materials will be very sensitive to synthesis conditions (for example, pressure and annealing effects) and the presence of lattice defects. By changing these factors it is possible to vary the T_c of the Y-C phase in a wide range.

Acknowledgment.

This work was supported by the RFBR, grant 02-03-32971, and the Russian Foundation for Scientific Schools, grant SS 829.2003.3.

¹ L. E. Toth, Transition Metal Carbides and Nitrides, Academic Press, New York, 1971.

² S. V. Vonsovsky, Yu. A. Izumov, E. Z. Kurmaev, Super-conductivity in Transition Metals, their Alloys and Compounds. Springer-Verlag, Berlin, 1982.

³ C. P. Poople, Jr., Y. A. Farach, J. Supercond. **13** (2000) 47

⁴ G. L. W. Hart, B. M. Klein, Phys. Rev. **B61** (2000) 3151.

⁵ R. W. Henn, W. Schnelle, R. K. Kremer, A. Simon, Phys. Rev. Lett. **77** (1996) 374.

⁶ R. J. Cava, H. Takagi, B. Batlogg, H. W. Zandbergen, J. J. Krajewski, W. F. Peck, Jr., R. B. van Dover, R. J. Felder, T. Siegrist, K. Mizushashi, J. O. Lee, H. Eisaki, S. A. Carter, S. Uchida, Nature (London) 367 (1994) 146.

⁷ R. J. Cava, H. Takagi, H. W. Zandbergen, J. J. Krajewski, W. F. Peck, Jr., T. Siegrist, B. Batlogg, R. B. van Dover, R. J. Felder, K. Mizuhashi, J. O. Lee, H. Eisaki, S. Uchida, Nature (London) **367** (1994) 252.

⁸ A.L. Ivanovskii, Russ. Chem. Rev. **67** 403 (2001).

⁹ S. N. Behera, B. N. Panda, G. C. Rout, P. Entel, Int. J. Modern Phys. **B15** (2001) 2519.

¹⁰ I. S. Yang, M. V. Klein, S. Bud'ko, P. C. Canfield, J. Phys. Chem. Solids. **63** (2002) 2195.

¹¹ Th. Gulden, R. W. Henn, O. Jepsen, R. K. Kremer, W. Schnelle, A. Simon, C. Felser, Phys. Rev. B56 (1997) 9021.

¹² G. Amano, S. Akutagawa, T. Muranaka, Y. Zenitani, J. Akimitsu, cond-mat/0311517 (2003).

¹³ M.C. Krupka, A.L. Giorgi, N.H. Krikorian, E.G. Szklarz, J. Less-Common Metals 17 (1969) 91.

T. Nakane, T. Mochiku, H. Kito, M. Nagao, J. Itoh, H. Kumakura, Y. Takano, cond-mat/0311561 (2003).

V. I. Novokshonov, Russ. J. Inorgan. Chem. 25 (1980) 375.

¹⁶ S.Y. Savrasov, Phys. Rev. **B54** (1996) 16470.

¹⁷ J.P. Perdew, K.Burke, M. Ernzerhof, Phys. Rev. Lett. **77** (1996) 3865.

¹⁸ A. Neckel, P. Rastl, R. Eibler et al., J. Phys. C: Solid State Phys. **9** (1976) 759.

¹⁹ P. Marksteiner, P. Weinberger, A. Neckel, R. Zeller, P. H. Dederichs, Phys. Rev. **B33** (1986) 812.

V. A. Gubanov, A. L. Ivanovskii, V.P. Zhukov. Electronic Structure of Refractory Carbides and Nitrides, University Press, Cambridge, 1994.

²¹ V. P. Zhukov, D.L. Novikov, N.I. Medvedeva, V. A. Gubanov, J. Struct. Chem. **30** (1989) 553.

TABLE I: . Total and site-projected $\ell\text{-decomposed}$ DOSs at the Fermi level (N(E_F), states/eV).

Density of state Partial states on atom Total state on molecule	YC	$YC_{1.5}$	YC_2
C2s	0.0088	0,0076	0.0104
	,	,	-
$C2p_x$	0,3849	$0,\!1856$	
$C2p_y$	0,3849	0,0293	0,0501
$C2p_z$	0,3849	0,0937	0,0089
C2p	1,1546	0,3086	0,1091
Ys	0,0084	0,0260	0,0039
Yp_x	0,0221	0,0153	0,0004
Yp_y	0,0221	0,0153	0,0004
Yp_z	0,0221	0,0153	0,0004
Yp	0,0664	0,0459	0,0011
Yd_{yz}	0,0918	0,0843	0,2048
Yd_{xz}	0,0918	0,0843	0,2048
Yd_{xy}	0,0918	0,0843	0,0060
$\mathrm{Yd}_{x^2-y^2}$	0,1064	0,2059	$0,\!1036$
Yd_{3z^2-1}	0,1064	0,2059	0,0025
Yd	0,4882	0,6647	0.5217
Total	1.7265	1.2107	0.7658

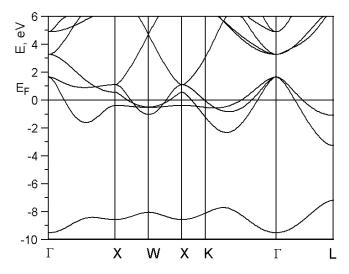


FIG. 1: The band structure of hypothetical B1-YC.

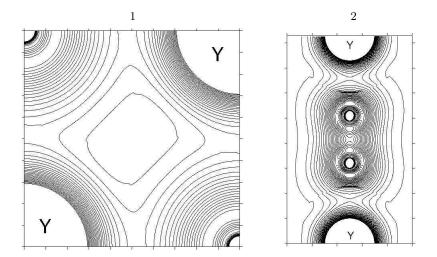


FIG. 2: Constant charge-density contour maps in sections of yttrium mono- (1) - and dicarbide (2) cells illustrating the formation of isotropic Y-C and anisotropic C-C bonds respectively.

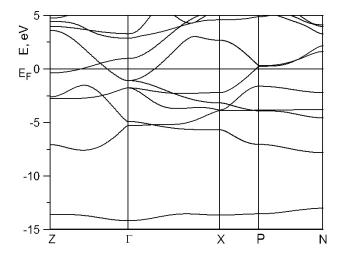


FIG. 3: The band structure of YC_2 .

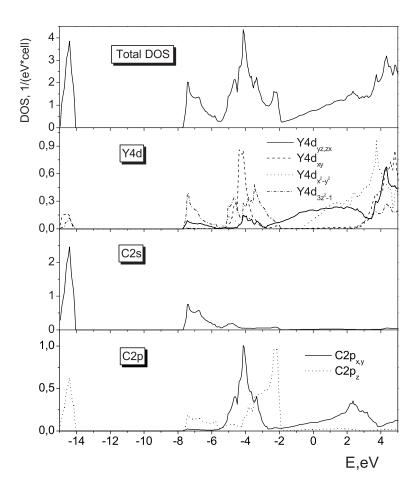


FIG. 4: The total and partial densities of states for YC_2 .

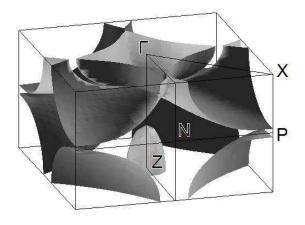


FIG. 5: The Fermi surface for YC_2 .

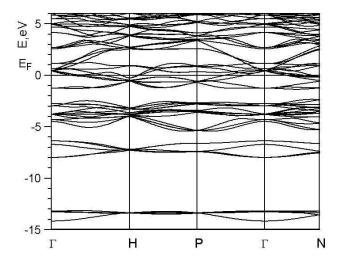


FIG. 6: The band structure of Y_2C_3 calculated with the lattice constants as given in Ref. 15 using the full-potential LMTO method.

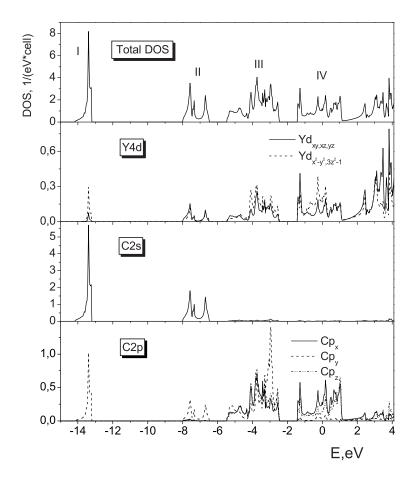


FIG. 7: The total and partial DOSs for Y_2C_3 calculated with the lattice constants as given in Ref. 15 using the full-potential LMTO method.


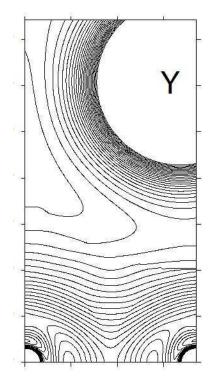


FIG. 8: The charge density map in the section of Y_2C_3 cell illustrating the C-C covalent bond.

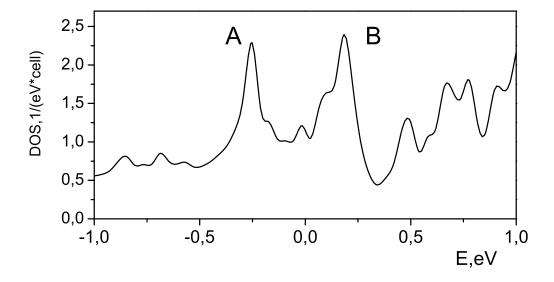

 $FIG. 9: \ \ The total \ density \ of \ states \ of \ Y_2C_3 \ around \ the \ Fermi \ energy \ calculated \ with \ the \ lattice \ constants \ as \ given \ in \ Ref.^{15}.$