

Spin-state transition in LaCoO_3 : direct neutron spectroscopic evidence of excited magnetic states

A. Podlesnyak,¹ S. Streule,¹ J. Mesot,¹ M. Medarde,^{2,1}
E. Pomjakushina,^{2,1} K. Conder,^{2,1} M. W. Haverkort,³ and D. I. Khomskii³

¹*Laboratory for Neutron Scattering,
ETH Zürich & Paul Scherrer Institut, CH-5232 Villigen PSI, Switzerland*

²*Laboratory for Developments and Methods,
Paul Scherrer Institut, CH-5232 Villigen PSI, Switzerland*

³*II Physikalisches Institut, Universität zu Köln,
Zùlpicher Strasse 77, 50937 Köln, Germany*

(Dated: September 13, 2018)

Abstract

A gradual spin-state transition occurs in LaCoO_3 around $T \sim 80 - 120$ K, whose detailed nature remains controversial. We studied this transition by means of inelastic neutron scattering (INS), and found that with increasing temperature an excitation at ~ 0.6 meV appears, whose intensity increases with temperature, following the bulk magnetization. Within a model including crystal field interaction and spin-orbit coupling we interpret this excitation as originating from a transition between thermally excited states located about 120 K above the ground state. We further discuss the nature of the magnetic excited state in terms of intermediate-spin (IS, $t_{2g}^5 e_g^1$, $S = 1$) *vs.* high-spin (HS, $t_{2g}^4 e_g^2$, $S = 2$) states. Since the g -factor obtained from the field dependence of the INS is $g \sim 3$, the second interpretation looks more plausible.

Due to its rich and in many respects puzzling properties, LaCoO_3 keeps attracting attention and remains a controversial topic. It is known that the ground state is nonmagnetic, corresponding to a low-spin (LS) state of Co^{3+} ions (t_{2g}^6 , $S = 0$). However, with increasing temperature (as well as with La \rightarrow Sr substitution) first a crossover into a magnetic, but still insulating state appears at about 80-120 K, followed by another crossover into a "bad metallic", magnetic state at $T \sim 400 - 600$ K. The original interpretation of the low-temperature crossover was done in terms of thermally-induced population of the low-lying high-spin (HS) state [1]; this process is furthermore favorized by thermal expansion, since the HS Co^{3+} has much larger radius (~ 0.75 Å) than the LS state (~ 0.685 Å). Later, especially after LDA+U band structure calculation have become available [2], another interpretation was put forward: within this scenario, the first crossover at ~ 100 K would be due to a transition into an intermediate-spin (IS) state. This interpretation was supported by a number of experimental evidences [3, 4, 5, 6, 7, 8, 9, 10, 11]. None of these arguments however gave a definite proof that the first thermally-excited state is indeed the IS one. Very recent measurements indicate that the first excited state could still be the HS state [12, 13, 14, 15, 16].

Also theoretically the situation is not clear: Hartree-Fock calculations showed that the HS state, or the HS-LS ordered state is more stable than the IS state [17], in contrast to LDA+U calculations [2]. Thereby, model calculations on a CoO_6 cluster explicitly including the Co-O hybridization can not reproduce an IS ground-state [18], indicating that the proposed mechanism why LDA+U finds an IS as first excited state, namely large covalency, is rather questionable.

With this controversy in mind, we undertake a neutron scattering study of LaCoO_3 at different temperatures with the goal of identifying the energy level of the thermally excited state of Co^{3+} . Indeed, we discovered that a rather unusual feature in the spectrum appears with increasing temperature in forms of thermally-induced relatively sharp inelastic peak at an energy-transfer of ~ 0.6 meV [19]. The intensity of this peak strongly increases with T following the behavior of the magnetic susceptibility $\chi(T)$, suggesting that the inelastic scattering occurs between thermally populated magnetic states of LaCoO_3 . The position and the temperature dependence of the intensity of this peak also coincide with the excitations observed in LaCoO_3 by ESR [12, 20]. By analyzing the features of this novel excitation, and combining it with model calculations, we discuss the two possible scenarios mentioned above.

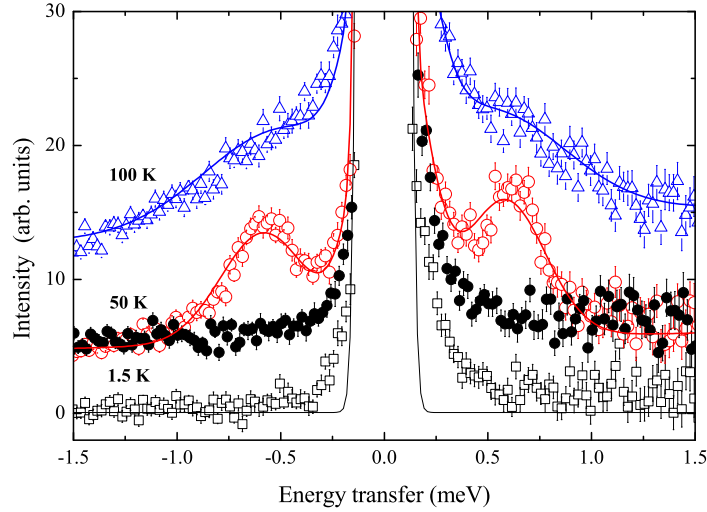


FIG. 1: (Color online) Temperature evolution of the INS profiles measured in LaCoO_3 . The filled circles correspond to the LaAlO_3 nonmagnetic reference compound at $T = 50$ K. The lines are the result of least-squares fits using Gaussian functions to describe the lineshape of the transition. For clarity, an offset has been added to the various curves.

Polycrystalline LaCoO_3 was prepared by standard sintered techniques using La_2O_3 and Co_3O_4 of a minimum purity of 99.99%. The respective amounts of starting reagents were mixed and calcinated at temperatures 1000-1200° C during at least 100 h in air, with several intermediate grindings. The sample was checked by x-ray diffraction and found to be single phase within experimental accuracy. The space group $R\bar{3}c$ and lattice parameters of $a = 5.4433(1)$ Å, $c = 13.0932(4)$ Å are in agreement with previously published data [1, 21, 22]. The inelastic neutron scattering (INS) measurements were performed on the time-of-flight spectrometer FOCUS [23] installed at the spallation neutron source SINQ at Paul Scherrer Institut, Villigen, Switzerland. Zero field experiments were carried out in the temperature interval of 1.5 – 100 K using a conventional helium cryostat. The data were collected using incoming neutron energies of 3.5 and 20 meV, giving an energy resolution at the elastic position [full width at half maximum (FWHM)] of 0.1 and 1.6 meV, respectively. The triple-axis spectrometer TASP with final neutron energy 4.7 meV was used for the measurements in external magnetic field up to $H = 6$ T.

The high-resolution low-energy transfer inelastic spectra for a few selected temperatures

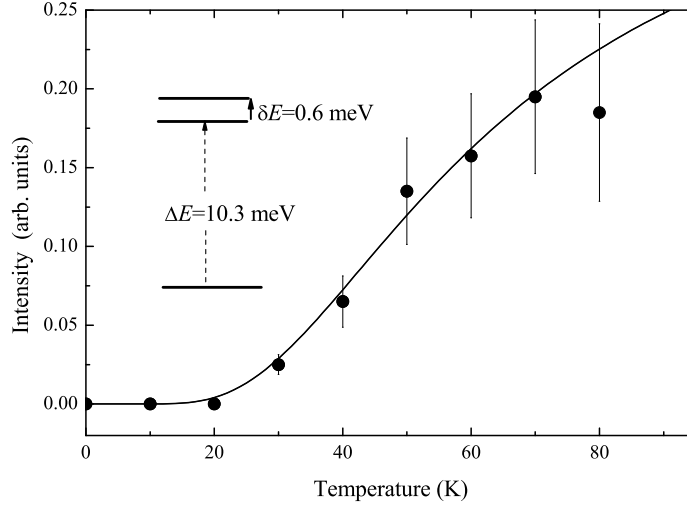


FIG. 2: Observed (circles) and fitted (solid line) temperature dependence of the integral intensity of the INS peak at 0.6 meV. The resulting level scheme is shown in the inset.

are shown in Fig. 1. There are no excitations in the energy window $E < 1.5$ meV for temperatures $T < 30$ K. A single inelastic peak at an energy transfer $\delta E = 0.61 \pm 0.05$ meV was found at intermediate temperatures starting from $T \sim 30$ K. A strong broadening of the transition was observed with increasing temperature. Note that the spectra obtained from a non-magnetic reference compound, LaAlO_3 , remain structureless at all temperatures. The high-energy transfer spectra observed for LaCoO_3 exhibit several broad inelastic peaks at about 10, 14 and 22 meV (not shown). However, all these peaks exhibit clear increase of their intensity with scattering vector and temperature. Therefore we conclude that they are due to phonon scattering, in agreement with previously published data [9]. No evidence for other magnetic excitations was observed in the LaCoO_3 spectra within the available energy window.

For noninteracting ions the thermal neutron cross section for the transition $|\Gamma_i\rangle \rightarrow |\Gamma_j\rangle$ is given in the dipole approximation by [24]

$$\frac{d^2\sigma}{d\Omega d\omega} \sim \frac{1}{Z} \exp\left(-\frac{E_i}{k_B T}\right) F^2(\mathbf{Q}) |\langle \Gamma_j | J_\perp | \Gamma_i \rangle|^2 \delta(E_i - E_j \pm \hbar\omega). \quad (1)$$

Here $F^2(\mathbf{Q})$ is the magnetic form factor, J_\perp is the component of the total angular momentum operator perpendicular to the scattering vector \mathbf{Q} , and Z is the partition function. It follows

from Eq. (1) that the energy gap $\Delta E = E_i - E_0$ between the ground-state and the excited-state can be deduced either directly from the position of the corresponding inelastic peak (in case of nonzero matrix element $|\langle \Gamma_0 | J_\perp | \Gamma_i \rangle|$), or from the temperature dependence of the transition between two excited levels $\delta E = E_j - E_i$ which is governed by Boltzman statistics. Note that the direct transition ΔE out of the ground-state was observed neither in the previous INS experiments [9, 25], nor in our current measurements, most likely due to selection rules. Therefore, in order to determine the energy of the excited state we apply the least-squares fitting procedure to the temperature dependence of the integrated intensity I of the INS signal as shown in Fig. 2. The position of the excited states turns out to be 10.3 ± 1 meV, which coincides well with the results obtained from ESR (12 meV, ref. 12). Our estimation is based on a temperature independent level splitting scheme. Although we can not exclude a slight variation of the position of the excited states due to thermal expansion of the unit cell, a level crossing of the ground- and excited states as suggested from the LDA+U calculations [2] can be excluded, since this would result in a non-monotonic temperature behavior of I around $T < 80$ K, which was not observed in our experiment. Furthermore, the position of the peak at $\delta E = 0.6$ meV is unaltered, suggesting that the trigonal CF remains nearly constant in this temperature range. Thus, our results imply that the first broad peak in magnetic susceptibility at ~ 100 K is due to a gradual thermal population of the excited levels rather than a modification of the level scheme due to a phase transition.

The observed magnetic INS, which was obtained as the difference of the intensities at 50 and 5 K, is shown in Fig. 3. A clear shift of the transition to the higher energy ~ 1.5 meV was observed in magnetic field $H = 6$ T compared to the zero-field spectrum, thus firmly establishing its magnetic origin. Due to weakness of the signal we can not conclude whether the peak is split in the external magnetic field. The change in energy of this peak from 0.6 meV to about 1.5 meV in magnetic field of 6 T is in good agreement with the g -factor measured from ESR experiments [12].

Let us discuss the possible origin of this excited state. There are two possibilities: either high-spin or a intermediate-spin states of Co^{3+} . The HS state with $S = 2$ has, in a cubic CF, the occupation $t_{2g}^4 e_g^2$, i.e., it has half-filled shell of $t_{2g}^3 e_g^2$, say with spins up, and one extra spin-down electron on a triple-degenerate t_{2g} -level, which can be described by an effective orbital moment $\tilde{L} = 1$ [26]. Total multiplicity of this state is $(2S + 1)(2\tilde{L} + 1) = 15$. Spin-

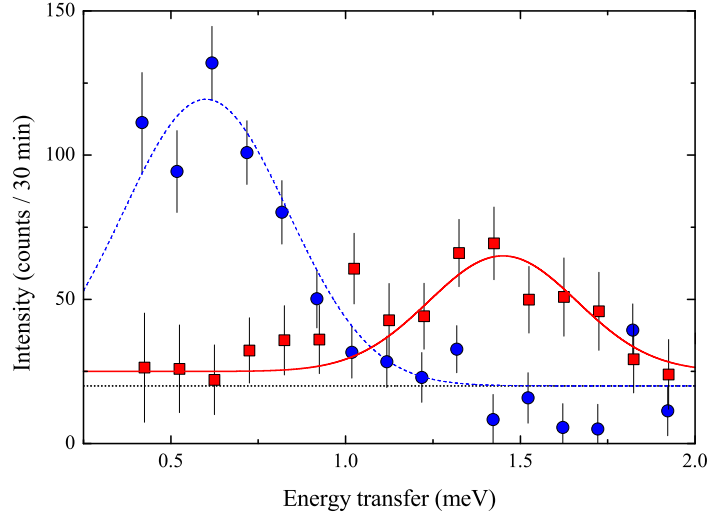


FIG. 3: (Color online) The magnetic inelastic scattering at $T = 50$ K in 0 T (circles) and 6 T (boxes) applied field.

orbit coupling splits this state into the lowest-lying triplet $\tilde{J} = S - \tilde{L} = 1$, next is a quintet $\tilde{J} = 2$, and the highest-lying is state has $\tilde{J} = 3$. If the system is strongly distorted there will be a ground-state orbital singlet and a higher excited orbital doublet. In the left panel of Fig. 4 we show the energy level diagram for the high-spin state as a function of trigonal distortion. This energy level diagram has been calculated for a CoO_6^{9-} cluster, including full multiplet theory, spin-orbit coupling and Co-O hybridization. For the Slater integrals and the spin orbit coupling atomic Hartree-Fock values are used, the hopping parameters are according to Harrison's rules [27]. The calculations have been done with the use of the program XTLS8 [28]. For the HS there are two places in the energy-level diagram, where an excitation of 0.6 meV can happen. If the trigonal crystal field is relatively small, the $\tilde{J} = 1$ triplet will be split by this crystal field. On the other-hand, if it is rather large, the orbital singlet with $S = 2$ will be split due to spin-orbit coupling. In both cases the splitting is governed by second order effects and the resulting splitting is much smaller than the perturbing interaction. The scenario of a small crystal-field with respect to the spin-orbit coupling has been discussed in quite details recently [13]. The scenario of a large crystal-field with respect to the spin-orbit coupling is equivalent to a spin only scenario.

One should also consider what would be the situation if the first excited state is an

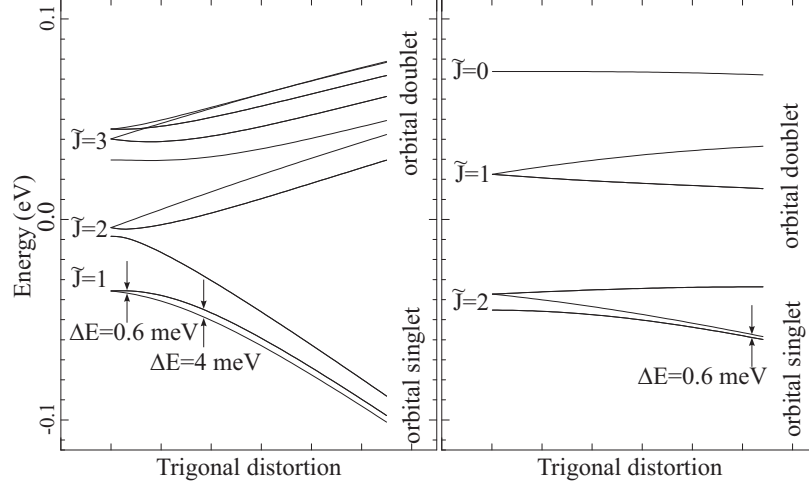


FIG. 4: Schematic diagram of the excitation spectrum of high-spin (left) and intermediate-spin (right) Co^{3+} as a function of trigonal distortion (see text).

IS Co^{3+} , which follows from LDA+U theoretical calculations [2] and which was used to interpret a number of experimental data [3, 4, 5, 6, 7, 8, 9, 10, 11]. This case is actually much more interesting and more difficult to treat theoretically. First thing to note is that in this case we have one electron in the e_g -shell and one hole (t_{2g}^5 occupation) in the t_{2g} -shell. Their Coulomb interaction strongly depends on the particular orbital occupation. The $(x^2 - y^2)$ -electron has strong attraction to the (xy) -hole, so that $(x^2 - y^2)^1(\underline{xy})^1$ state has much lower energy than e.g. $(z^2)^1(\underline{xy})^1$. Thus we can consider the lowest states on a basis of $(x^2 - y^2)^1(\underline{xy})^1$, $(x^2 - z^2)^1(\underline{xz})^1$ and $(xy^2 - z^2)^1(\underline{yz})^1$ [18]. Therefore the total orbital degeneracy of the IS state in a cubic CF is 3 and not 6 ($3t_{2g} \times 2e_g$) as one could have expected. We can thus again describe these states by the effective orbital triplet $\tilde{L} = 1$; but because of the more complicated type of the basis states, the maximum magnitude of the magnetic moment is not 1 but $\frac{1}{2}$ (i.e. $L_z = \{\frac{1}{2}, 0, -\frac{1}{2}\}$ [29]). In other words, one has an effective orbital g -factor of $\frac{1}{2}$. As a result, we are dealing with 9 states $(2\tilde{L} + 1)(2S + 1)$ (with $S = 1$ for IS state), which are split by the spin-orbit coupling into multiplets with $\tilde{J} = 2, 1, 0$. However, in this case the quintet $\tilde{J} = 2$ is the lowest state. Thus, the multiplicity of the IS state in cubic CF is 5. Strong enough distortions, or orbital ordering, modify the energy-level scheme as shown in the right panel of Fig. 4. If the distortions are larger than the spin-orbit coupling constant, the ground-state becomes an orbital singlet. This orbital singlet is split due to second-order spin-orbit interactions into two levels that could very well

be 0.6 meV apart from each other. In cubic symmetry, the $\tilde{J} = 2$ quintet originating from the IS state is however also split due to second order interactions. This splitting seems to be somewhat larger than the measured value of 0.6 meV.

If we now compare our results with other measurements, we notice that from a comparison of the magnetic susceptibility with the anomalous expansion coefficient of LaCoO_3 , Zobel *et al.* [10] concluded that the degeneracy of the first magnetic excited state is 3. This leaves only two possibilities open. The first magnetic excited state in LaCoO_3 can be a HS state with a small non-cubic crystal field, or it can be an IS state with a large non-cubic crystal field or orbital ordering. There is one striking difference between these scenarios: this is the predicted g -factor. The HS state with a small distortion is a triplet with a g -factor of about 3.5 [13, 26], whereas the IS with strong distortion is a triplet with a g -factor of about 2.0. ESR measurements found a g -factor of 3.35 - 3.55 [12], supporting the HS state; this also agrees with our results since we obtained $g \sim 3$ (see Fig. 3). On the other hand a fit to the magnetic susceptibility yields a g -factor of about 2.28 [10], supporting the IS scenario.

To summarize, we observe a novel inelastic excitation in LaCoO_3 which is due a thermally excited magnetic state of Co^{3+} ions. This confirms the presence of thermally induced spin-state transition (or rather crossover) at $T \sim 100$ K from the LS Co^{3+} to a magnetic HS or IS state. We discuss both possibilities theoretically and show that one can explain both our and other results (thermodynamic, ESR) in the framework of a HS-triplet as first excited state, with the g -factor ~ 3.5 , weakly split by small distortions from the cubic symmetry. Another possibility would be the IS state with orbital ordering or strong non-cubic crystal-fields, which however would result in a spin-only system with a g -factor ~ 2.0 , a value difficult to reconcile with our experimental data. Thus the first interpretation (HS excited state) seems to us more plausible.

The experiments have been performed at the Swiss Spallation Neutron Source, Paul Scherrer Institute, Villigen, Switzerland. We are indebted to the Swiss National Science Foundation for financial support through grant 200021-100194 and NCCR MaNEP project. Financial support by the Deutsche Forschungsgemeinschaft via SFB 608 and by the Marie Heim-Vögtlin program (grant No. PMPD2-102504) is also gratefully acknowledged. We would like to thank Arata Tanaka for the kind use of his program XTLS8.

-
- [1] P. M. Raccah and J. B. Goodenough, Phys. Rev. **155**, 932 (1967).
- [2] M. A. Korotin, S. Y. Ezhov, I. V. Solovyev, V. I. Anisimov, D. I. Khomskii, and G. A. Sawatzky, Phys. Rev. B **54**, 5309 (1996).
- [3] S. Masuda, M. Aoki, Y. Harada, H. Hirohashi, Y. Watanabe, Y. Sakisaka, and H. Kato, Phys. Rev. Lett. **71**, 4214 (1993).
- [4] T. Saitoh, T. Mizokawa, A. Fujimori, M. Abbate, Y. Takeda, and M. Takano, Phys. Rev. B **55**, 4257 (1997).
- [5] M. Abbate, J. C. Fuggle, A. Fujimori, L. H. Tjeng, C. T. Chen, R. Potze, G. A. Sawatzky, H. Eisaki, and S. Uchida, Phys. Rev. B **47**, 16124 (1993).
- [6] S. Yamaguchi, Y. Okimoto, and Y. Tokura, Phys. Rev. B **55**, R8666 (1997).
- [7] A. Ishikawa, J. Nohara, and S. Sugai, Phys. Rev. Lett. **93**, 136401 (2004).
- [8] D. Louca, J. L. Sarrao, J. D. Thompson, H. Röder, and G. H. Kwei, Phys. Rev. B **60**, 10378 (1999).
- [9] D. Louca and J. L. Sarrao, Phys. Rev. Lett. **91**, 155501 (2003).
- [10] C. Zobel, M. Kriener, D. Bruns, J. Baier, M. Grüninger, T. Lorenz, P. Reutler, and A. Revcolevschi, Phys. Rev. B **66**, 020402(R) (2002).
- [11] G. Maris, Y. Ren, V. Volotchaev, C. Zobel, T. Lorenz, and T. T. M. Palstra, Phys. Rev. B **67**, 224423 (2003).
- [12] S. Noguchi, S. Kawamata, K. Okuda, H. Nojiri, and M. Motokawa, Phys. Rev. B **66**, 094404 (2002).
- [13] Z. Ropka and R. J. Radwanski, Phys. Rev. B **67**, 172401 (2003).
- [14] Y. Kobayashi, N. Fujiwara, S. Murata, K. Asai, and H. Yasuoka, Phys. Rev. B **62**, 410 (2000).
- [15] T. Kyômen, Y. Asaka, and M. Itoh, Phys. Rev. B **67**, 144424 (2003).
- [16] T. Kyômen, Y. Asaka, and M. Itoh, Phys. Rev. B **71**, 024418 (2003).
- [17] M. Zhuang, W. Zhang, and N. Ming, Phys. Rev. B **57**, 10705 (1998).
- [18] M. W. Haverkort, Ph.D. thesis (2005).
- [19] Similar results were recently obtained also by D. Louca and S.-H. Lee, APS March meeting (2005).
- [20] V. Kataev, private communication.

- [21] K. Asai, A. Yoneda, O. Yokokura, J. M. Tranquada, G. Shirane, and K. Kohn, J. Phys. Soc. Jpn. **67**, 290 (1998).
- [22] G. Thornton, B. C. Tofield, and A. W. Hewat, J. Sol State Chem. **61**, 301 (1986).
- [23] J. Mesot, S. Janssen, L. Holitzner, and R. Hempelmann, J. Neutr. Res. **3**, 293 (1996).
- [24] W. Marshall and S. W. Lovesey, *Theory of Thermal Neutron Scattering* (Oxford University Press, Oxford, 1971).
- [25] K. Asai, P. Gehring, H. Chou, and G. Shirane, Phys. Rev. B **40**, 10982 (1989).
- [26] A. Abragham and B. Bleaney, *Electron paramagnetic resonance of transition ions* (Clarendon, Oxford, 1970).
- [27] W. A. Harrison, *Electronic structure and the properties of solids* (W. H. Freeman and Co., San Francisco, 1980).
- [28] A. Tanaka and T. Jo, J. Phys. Soc. Jpn. **63**, 2788 (1994).
- [29] One can see this by expressing nonorthogonal $(x^2 - y^2)$, $(x^2 - z^2)$ and $(y^2 - z^2)$ through an orthogonal basis $(x^2 - y^2)$, z^2 , so that $(x^2 - z^2)/(y^2 - z^2) = \pm \sqrt{\frac{1}{4}}(x^2 - y^2) - \sqrt{\frac{3}{4}}z^2$