

Magnetic Phase Transition at 88 K in $\text{Na}_{0.5}\text{CoO}_2$, as revealed by ^{23}Na -NMR investigations

B. Pedrini, J. L. Gavilano, S. Weyeneth, E. Felder, J. Hinderer, M. Weller, H. R. Ott, S. M. Kazakov, J. Karpinski

*Laboratorium für Festkörperphysik,
ETH-Hönggerberg, CH-8093 Zürich, Switzerland*

(Dated: February 8, 2020)

$\text{Na}_{0.5}\text{CoO}_2$ exhibits a metal-insulator transition at $T_{\text{MI}} = 53$ K upon cooling. The nature of another transition at $T_X = 88$ K has not been fully clarified yet. We report the results of measurements of the electrical conductivity σ , the magnetic susceptibility χ and ^{23}Na NMR on a powder sample of $\text{Na}_{0.5}\text{CoO}_2$, including the mapping of NMR spectra, as well as probing the spin-lattice relaxation rate $T_1^{-1}(T)$ and the spin-spin relaxation rate $T_2^{-1}(T)$, in the temperature range between 30 K and 305 K. The NMR data reflect the transition at T_X very well but provide less evidence for the metal-insulator transition at T_{MI} . The temperature evolution of the shape of the spectra implies the formation of a staggered internal field below T_X , not accompanied by a rearrangement of the electric charge distribution. Our results thus indicate that in $\text{Na}_{0.5}\text{CoO}_2$, an unusual type of magnetic ordering in the metallic phase precedes the onset of charge ordering, which finally induces an insulating ground state.

PACS numbers: 71.27; 71.30; 75.10; 76.60

Keywords: $\text{Na}_{0.5}\text{CoO}_2$, Strongly correlated electrons, Metal insulator transition, Magnetic ordering, NMR

I. INTRODUCTION

Compounds of the series Na_xCoO_2 ($0.25 < x < 1$) adopt a crystal structure which consists of alternating layers of Na^+ ions and layers of edge-sharing CoO_6 octahedra, with a triangular arrangement of the Co sites [1]. They represent a physical realization of magnetic systems with planar triangular symmetry, in which metallicity is achieved by controlled carrier injection. The simple metallic phase ($x < 0.5$) is separated from the local moment metallic phase ($x > 0.5$) by the insulating phase occurring at $x = 0.5$ [2]. A variety of other interesting phenomena is observed at different values x of Na-concentration upon varying the temperature. The material with composition $x \approx 0.7$ exhibits a large thermoelectric power [3], and indications of a charge instability in the temperature range between 230 and 290 K were observed [4]. A spin-density wave formation at temperatures below 22 K was detected for $x = 0.75$ [5]. Superconductivity is induced at $x = 0.35$, if the CoO_2 -layers are intercalated with water [6].

The richness of the phase diagram of Na_xCoO_2 is argued to be the result of a subtle interplay between electronic and structural degrees of freedom. Neutron scattering measurements [1] revealed a critical dependence of both the shape of the CoO_6 octahedra and the interlayer distance on the Na concentration x and on the distribution of the Na^+ ions in the intervening layers, where two possible sites, Na1 and Na2, are available. The presence of ordered Na^+ ions / Na^+ vacancy superlattices beyond the simple average hexagonal structure was confirmed by means of electron diffraction measurements [7].

It is a peculiarity of the Na_xCoO_2 -series to exhibit an insulating ground state in a very narrow range of values x centered at $x = 0.5$. The metal-insulator transition in $\text{Na}_{0.5}\text{CoO}_2$, occurring at $T_{\text{MI}} = 53$ K [2, 8] upon cooling,

is reflected by anomalies in the temperature dependences of the resistivity $\rho(T)$, the magnetic susceptibility $\chi(T)$ and the specific heat. The insulating character of the low-temperature phase was also confirmed by infrared reflectivity measurements [9]. Unusual features were observed for the thermal conductivity, the thermopower and the Hall resistivity $R_H(T)$ [2]. In addition, $\text{Na}_{0.5}\text{CoO}_2$ shows a pronounced Na superstructure [7, 8], where the Na^+ ions order in zig-zag chains [1, 10] with an alternating occupation of Na1 and Na2 sites. Besides the metal-insulator transition, another transition at $T_X = 88$ K is clearly reflected by an abrupt reduction of $\chi(T)$ upon cooling. This transition is also characterized by a change of sign of $R_H(T)$ [2], which rapidly decreases to large negative values below T_X with decreasing temperature. In Ref.[8] the transition was argued to be of structural type. Subsequent μSR experiments have indicated an antiferromagnetically ordered ground state, but different ordering temperatures of 53 K [11] and 85 K [12] were reported. Very recent ^{59}Co NMR and neutron scattering studies [13] brought evidence of antiferromagnetic order below 87 K. The order was claimed to involve two types of localized Co magnetic moments of $0.34 \mu_B$ and $0.11 \mu_B$, respectively.

The variety of experimentally observed features of Na_xCoO_2 triggered a number of intense theoretical investigations. The electronic structure of these compounds was calculated in the local (spin) density approximation (LSDA). The inclusion of a Hubbard repulsion parameter U in the calculation yields the two magnetically different regimes for $x < 0.5$ and $x > 0.5$ [14] that are observed experimentally. The calculation also explains [15] the absence of pockets of the Fermi surface, as was registered in angle-resolved photoemission (ARPES) experiments for $x = 0.3$ [16], $x = 0.6$ [17] and $x = 0.7$ [18]. If the value of U is chosen large enough, an insulating ground state

can be obtained for $\text{Na}_{0.5}\text{CoO}_2$ [19]. The authors of Ref. [20] describe a charge disproportionation accompanied by magnetic moment localization $2\text{Co}^{3.5+} \rightarrow \text{Co}^{3+} + \text{Co}^{4+}$, occurring at a critical value $U = 3.4$ eV.

In a different approach, a multiorbital Hubbard model with strong Coulomb repulsion was considered. The calculations predict both the Fermi surface pocket cancellation and a band narrowing [21], again in good agreement with the results of ARPES measurements [22] at $x \neq 0.5$. With a similar approach, the authors of Ref. [23] focus on charge and spin instabilities, deriving a variety of possible metallic states with a spontaneous breaking of the original hexagonal symmetry; in particular, the zig-zag arrangement of Na^+ ions observed in $\text{Na}_{0.5}\text{CoO}_2$ is found to be energetically favourable and it is argued that this superstructure leads to a quasi one-dimensional band structure, with the possible formation of a spin-density wave.

The aim of our work was to elucidate the nature of both the phase transition at T_X and the phase between T_{MI} and T_X in $\text{Na}_{0.5}\text{CoO}_2$. It is predominantly our ^{23}Na NMR data that give clear evidence for a transition from a paramagnetic to an antiferromagnetically ordered state at $T_X = 88$ K upon cooling. This transition occurs in a low-conductivity metallic phase and does not result in the opening of a gap in the spectrum of electronic excitations. This observation is, to some extent, surprising, because a magnetic transition is rather expected to occur in the low-temperature insulating phase, or simultaneously with the metal-insulator transition at T_{MI} . To our knowledge, no theoretical model that would account for the described phenomenon has yet been proposed.

The paper is organised as follows. The preparation of the $\text{Na}_{0.5}\text{CoO}_2$ powder sample is described in Section II. In Sections III and IV we report the results of the measurements of the electrical conductivity $\sigma(T)$ and of the magnetic susceptibility $\chi(T)$. Section V is devoted to the ^{23}Na NMR experiments. We present the temperature variations of the spectra as well as of the spin-lattice and spin-spin relaxation rates T_1^{-1} and T_2^{-1} . In Section VI we discuss the experimental results. The emphasis is put on the magnetic properties of the phases at temperatures below T_X , but also the unusual properties of the metallic regime above T_X are considered to some extent.

II. SAMPLE

The $\text{Na}_{0.5}\text{CoO}_2$ powder sample was prepared by a procedure that is described in Ref. [8]. First, a powder of nominal composition $\text{Na}_{0.75}\text{CoO}_2$ was prepared by heating a stoichiometric mixture of Co_3O_4 (Aldrich, 99.995%) and Na_2CO_3 (Aldrich, 99.995%) in air at 850°C for 15 hours. The remelting procedure was repeated twice to ensure the proper cation concentration. For the synthesis of $\text{Na}_{0.5}\text{CoO}_2$, 0.5 g of $\text{Na}_{0.75}\text{CoO}_2$ were stirred in 120 ml of a solution of I_2 in acetonitrile for 4 days. The quantity of dissolved I_2 was chosen to be 10 times the

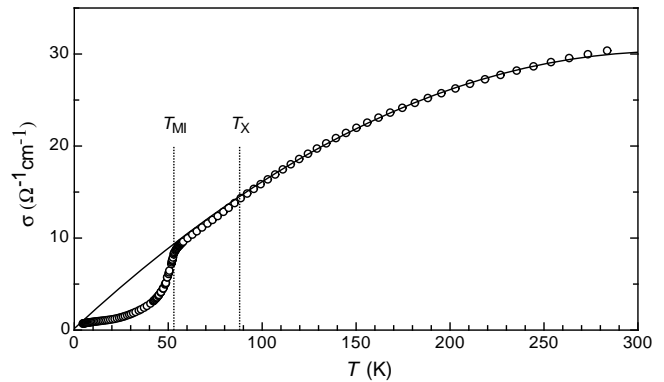


FIG. 1: Electrical conductivity σ as a function of temperature T . The solid line represents the results of best fits with the functions $\sigma(T) = c_2 \cdot T^2 + c_1 \cdot T + c_0$. Data in the temperature range 100-260 K was considered.

amount that would in principle be necessary to remove all the Na from $\text{Na}_{0.75}\text{CoO}_2$. The resulting material was cleaned with acetonitrile and dried in flowing argon. X-ray powder diffraction patterns showed that the resulting material is of single phase with lattice parameters of $a=2.8134(7)$ and $c=11.129(4)$ Å. These parameters yield an estimated Na content of $x=0.48$ [2].

III. ELECTRICAL CONDUCTIVITY

As a first characterization of our sample we measured the temperature dependence of the electrical resistivity. The resistance R of a piece of pressed powder, whose length and cross section were $d \approx 6$ mm and $A \approx 15$ mm² respectively, was measured using an a.c. four-terminal technique.

The conductivity $\sigma = (RA/d)^{-1}$ is shown, as a function of temperature T , in Figure 1. Upon cooling, the gradual decrease of σ at high temperatures (a factor of 5 between 290 K and 100 K) is intercepted by an abrupt downturn at $T_{\text{MI}} = 53$ K. This reflects the metal-insulator transition.

The high-temperature phase is not properly metallic. First of all, the continuous decrease of $\sigma(T)$ with decreasing temperature is certainly not typical for a metal. A similar behaviour is observed, e.g., for V_2O_3 , a compound in which the metal-insulator transition can be driven by changing the pressure [24] or by V-substitution [25]). In that case the decrease in $\sigma(T)$ upon cooling is argued to reflect a semiconducting transport regime $\sigma \sim \exp(-\Delta/k_B)$ at low temperature ($T \ll \Delta/k_B$). A similar scenario is nevertheless excluded in the case of $\text{Na}_{0.5}\text{CoO}_2$, because it cannot account for the negative second derivative $d^2\sigma/dT^2 < 0$ that is observed experimentally.

Further insight in the transport properties of the metallic phase can be gained by estimating the mean free

path l of the charge carriers. From the Drude law

$$\sigma = \frac{e^2 n_e \tau}{m^*} = \frac{e^2 n_e l}{\hbar k_F} \quad , \quad (1)$$

with n_e as the charge carrier density, τ the average scattering time, m^* the effective mass of the charge carriers and $k_F = m^* l / \hbar \tau$, the Fermi wave vector. We assume one conduction electron per Na atom, resulting in $n_e = 5.26 \times 10^{22} \text{ cm}^{-3}$. Furthermore, we employ the high-temperature saturation value $\bar{\sigma}$ of σ , which is calculated as follows. The temperature dependence of the conductivity $\sigma(T)$ for temperatures in the range between 100 and 260 K can be approximated by (see Figure 1)

$$\sigma(T) = c_2 \cdot T^2 + c_1 \cdot T + c_0 \quad (2)$$

with $c_2 = -2.98 \times 10^{-4} (\text{K}^{-2} \Omega \text{ cm})^{-1}$, $c_1 = 0.19 (\text{K}^{-1} \Omega \text{ cm})^{-1}$ and $c_0 \approx 0$. Accordingly, the maximum of σ is reached at $\bar{T} = 318 \text{ K}$ and we take

$$\bar{\sigma} = \sigma(\bar{T}) \approx 30 (\Omega \text{ cm})^{-1} \quad (3)$$

as an estimate of the saturation value at high temperatures. We first assume a 3-dimensional free electron gas (3D)

$$k_F = (3\pi^2 n_e)^{\frac{1}{3}} \quad (3D) \quad . \quad (4)$$

Inserting (3) in (1) gives the mean free path

$$l = 2.7 \times 10^{-10} \text{ cm}^{-1} \quad (3D) \quad , \quad (5)$$

which is far less than the interatomic distance.

We note that the values of σ are smaller by an order of 50 w.r.t. σ_{\parallel} measured along the CoO_2 -planes of a single crystal and reported in Ref.[8]. This suggests a large anisotropy of the conductivity in $\text{Na}_{0.5}\text{CoO}_2$, not unexpected in a layered compound (see, e.g., $\text{La}_{0.5}\text{Sr}_{1.5}\text{MnO}_4$, where the anisotropy in σ is of a factor of about 1000 [26]). Hence, for a more realistic estimate of the mean free path l we assume a gas of electrons that is constrained to two dimensional planes (2D), i.e.,

$$k_F = (2\pi n_e c)^{\frac{1}{2}} \quad (2D) \quad , \quad (6)$$

where c is the value of the lattice constant along the c -axis (see Section II). In Equation (1) we replace σ with the in plane saturation value $\bar{\sigma}_{\parallel} \approx 50\bar{\sigma}$. This yields an estimate of the mean free path in the ab -plane

$$l \approx 2.3 \times 10^{-8} \text{ cm}^{-1} \quad (2D) \quad , \quad (7)$$

of the order of the interatomic distances in $\text{Na}_{0.5}\text{CoO}_2$. This extremely small value seriously questions the description of the metallic phase in terms of simple transport scenarios. Further discussions on this point are postponed to Section VI.

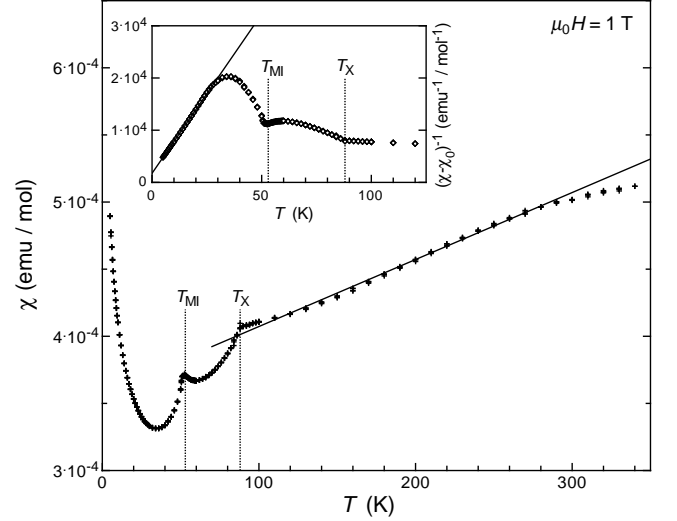


FIG. 2: Magnetic susceptibility χ as a function of temperature T , measured in a fixed magnetic field $\mu_0 H = 1 \text{ T}$. The solid line is the best linear fit for $100 \text{ K} < T < 260 \text{ K}$. Inset: inverse magnetic susceptibility $(\chi - \chi_0)^{-1}$ as a function of T . The solid line is the best linear fit for $5 \text{ K} < T < 20 \text{ K}$.

IV. MAGNETIC SUSCEPTIBILITY

As an additional characterization of our sample, we measured the temperature dependence of the magnetic susceptibility $\chi(T)$. The magnetization of 50 mg of $\text{Na}_{0.5}\text{CoO}_2$, again in the form of a powder sample (number of mols $n = 4.88 \times 10^{-4}$), was measured in different magnetic fields up to $\mu_0 H = 5 \text{ T}$ and in the temperature range between 5 and 340 K. At fixed temperatures the magnetic susceptibility $\chi = M/n\mu_0 H$ is found to be field independent. Figure 2 shows $\chi(T)$ for $\mu_0 H = 1 \text{ T}$. Our result is in good agreement with previously published single-crystal data [8, 13].

Two anomalies at $T_{\text{MI}} = 53 \text{ K}$ and $T_X = 88 \text{ K}$ are revealed by kinks, both followed by abrupt decreases of χ upon cooling.

Above T_X , $\chi(T)$ decreases continuously with decreasing temperature. In the range from 260 to 100 K, the susceptibility depends approximately linearly on the temperature (see Figure 2). Above 260 K, the experimentally measured susceptibility tends to saturate to an estimated value of

$$\bar{\chi} = 5.2 \times 10^{-4} \text{ emu/mol} \quad . \quad (8)$$

Assuming that the susceptibility above 300 K is due to pure Pauli paramagnetism, $\bar{\chi}$ yields the total density of states at the Fermi energy

$$D(E_F) = \frac{1}{\mu_B^2 V_{\text{mol}}} \bar{\chi} = 2.6 \times 10^{+35} \text{ erg}^{-1} \text{ cm}^{-3} \quad . \quad (9)$$

Here, $V_{\text{mol}} = 22.91 \text{ cm}^3$ is the molar volume of $\text{Na}_{0.5}\text{CoO}_2$. The expected values of $D(E_F)$ for a 3D and

a 2D conduction band, respectively, are

$$D(E_F) = \frac{3n_e^{\frac{1}{3}} m^*}{(3\pi^2)^{\frac{2}{3}} \hbar^2} \quad (3D) \quad (10)$$

and

$$D(E_F) = \frac{2m^*}{(2\pi)\hbar^2 c} \quad (2D), \quad (11)$$

where c is again the value of the lattice constant along the c -axis (see Section II), and m^* is the effective mass of the conduction electrons. The comparison of $D(E_F)$ given in Equation (9) with (10) and (11) yields an effective mass

$$m^* \approx 101 m_e \quad (3D), \quad (12)$$

or, for the more realistic 2D situation,

$$m^* \approx 11 m_e \quad (2D), \quad (13)$$

where m_e is the free electron mass. Further comments concerning these values are presented in Section VI.

We now consider the possibility that the anomaly in $\chi(T)$ at T_X is due to antiferromagnetic ordering of localized magnetic moments upon cooling the sample. In a very simple scenario we suppose that the valences are Na^{1+} and O^{2-} , and that there is 1 electron per Na atom in the conduction band. This leads to the $3d^5$ configuration Co^{4+} . If we also assume that only the lowest t_{2g} Co orbitals are occupied [27], we find that the total spin is $S = 1/2$ per Co ion. If the orbital component is quenched, the corresponding effective magnetic moment per formula unit is

$$\mu_{\text{eff}, S=1/2} = g\sqrt{S(S+1)} = 1.73 \quad , \quad (14)$$

where $g = 2$. The Curie-Weiss temperature dependence of the susceptibility is

$$\chi_{S=1/2}(T) = (\mu_{\text{eff}, S=1/2})^2 \frac{N\mu_B^2}{3k_B} \frac{1}{T} \quad . \quad (15)$$

At $T = 300$ K, $\chi_{S=1/2} = 1.25 \times 10^{-3}$ emu/mol, and at the transition temperature T_X $\chi_{S=1/2} = 4.26 \times 10^{-3}$ emu/mol, respectively. These values are much larger than the measured values of χ , thus indicating that no significant moments reside on the Co sites. The susceptibility $\chi(T)$ for $T \geq T_{\text{MI}}$ is thus attributed, as claimed above, to the Pauli paramagnetism of the itinerant charge carriers. In previous work [13], the reduction of χ upon cooling below room temperature was ascribed to a pseudogap feature in the electronic excitation spectrum.

Below 20 K, $\chi(T)$ increases with decreasing temperature. Forcing $\chi(T)$ for $5 \text{ K} \leq T \leq 10 \text{ K}$ to fit a Curie-Weiss function $\chi_0 + C(T - \Theta)^{-1}$ results in $\chi_0 = 2.82 \times 10^{-4}$ emu/mol, significantly less than above room temperature. The inset of Figure 2 shows $(\chi - \chi_0)^{-1}$ as a function of T , emphasizing that

$$(\chi - \chi_0)^{-1} \approx C^{-1}(T - \Theta) \quad (16)$$

up to 30 K, with $C = (1.7 \pm 0.1) \times 10^{-3}$ (emu mol) $^{-1}$ K and $\Theta = 2.5 \pm 0.4$ K. The effective magnetic moment per formula unit is thus (in units of μ_B)

$$\mu_{\text{eff}} = \sqrt{\frac{3k_B}{N\mu_B^2}} C = 0.11 \pm 0.005 \quad . \quad (17)$$

The comparison of the latter value with the value calculated in Equation (14) leads to the conclusion that at most 7% of the Co atoms carry magnetic moments which are still acting freely at low temperatures.

V. ^{23}Na NMR

The ^{23}Na NMR experiments were made with two samples of pressed powder with masses 45 mg and 325 mg, respectively. No significant differences between the results of the measurements were observed.

The values of the magnetic fields $\mu_0 H$ in which the experiments were performed were determined from the measured resonance frequency of deuterated water D_2O . The ^{23}Na nuclear reference frequency f_0 was calculated using the standard gyromagnetic ratio γ_{Na} , i.e., $f_0 = \gamma_{\text{Na}}\mu_0 H$.

A. Spectra

^{23}Na NMR spectra were obtained by monitoring the integrated spin-echo intensity as a function of the irradiation frequency in a fixed magnetic field H . The echo was generated with a two-pulse $\pi/2$ -delay- π spin-echo sequence, irradiating a frequency window of about 25 kHz.

In the inset of Figure 3 we show examples of the spectra taken in a magnetic field $\mu_0 H = 7.0$ T at temperatures above 87.2 K. Above $T_X = 88$ K, we observe a single, narrow NMR line, labelled P, peaking at a frequency f_P . The relative frequency shift $K_P = (f_P - f_0)/f_0$ is represented in Figure 3 as a function of temperature T . K_P is field independent and, above T_X , varies approximately linearly with T . It is related to the susceptibility χ by

$$K_P \approx \frac{1}{N\mu_B} A_P \chi + K_0 \quad . \quad (18)$$

The parameter $K_0 \approx 0$ and the hyperfine coupling constant is $A_P = 0.43 \pm 0.03$ T per μ_B magnetization of a formula unit of $\text{Na}_{0.5}\text{CoO}_2$. The full width at half maximum (FWHM) of the NMR line P, Δf_P , slowly increases upon cooling from the room temperature value, $\Delta f_P \approx 12$ kHz, to $\Delta f_P \approx 16$ kHz at T_X .

The spectra recorded at temperatures $T \geq T_X$ exhibit wings in the range labelled W_1 - W_2 with features labelled X_1 , Y_1 and X_2 , Y_2 . Corresponding spectra are shown in Figure 4. The shape and the width $\Delta f_W = f_{W_2} - f_{W_1}$ of the wings are the same for $\mu_0 H = 4.2$ T and $\mu_0 H = 7.0$ T, suggesting that they represent the quadrupolar wings

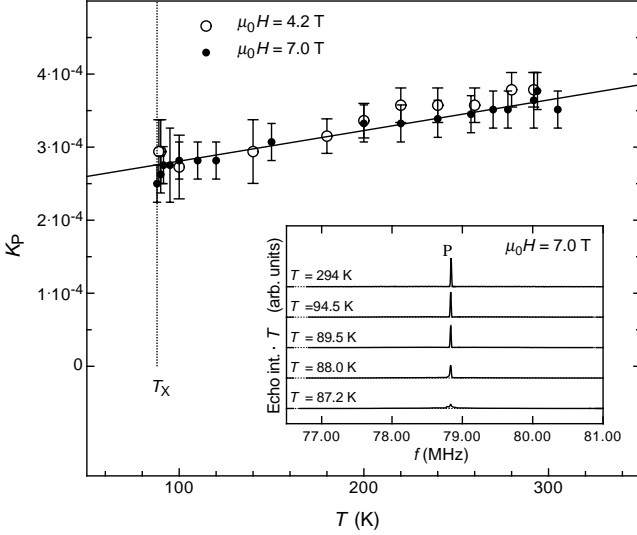


FIG. 3: Relative frequency shift K_P as a function of temperature T of the ^{23}Na NMR line P ($T \geq 88$ K), in magnetic fields $\mu_0 H = 4.2$ T and $\mu_0 H = 7.0$ T. Inset: ^{23}Na NMR spectra measured in a fixed magnetic field of $\mu_0 H = 7.0$ T, for $T \geq 87.2$ K. The integrated echo-intensity, multiplied with the temperature T , is plotted as a function of the irradiation frequency f .

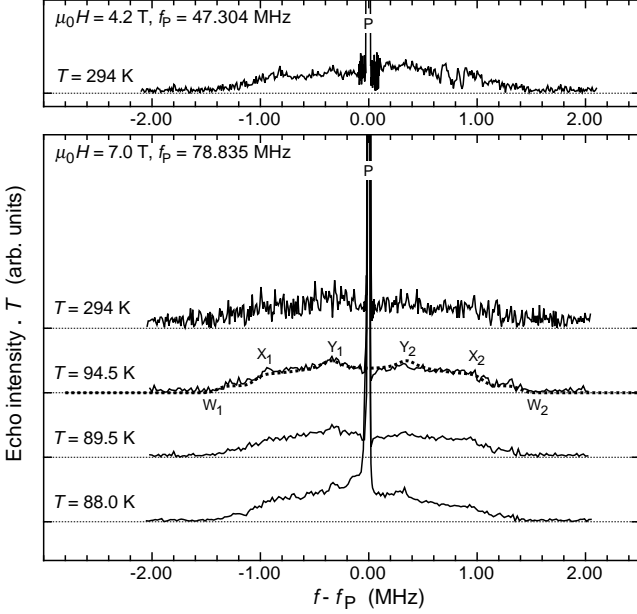


FIG. 4: ^{23}Na NMR spectra measured in fixed magnetic fields $\mu_0 H = 4.2$ T (upper plot) and $\mu_0 H = 7.0$ T (lower plot), for $T \geq 88.0$ K. The integrated echo-intensity, multiplied with the temperature T , is plotted as a function of $f - f_P$, with f the irradiation frequency and f_P the frequency of the central line P. The dotted line on the spectrum at $T = 94.5$ K represents the calculated shape of the wings due to first-order quadrupolar effects. The significance of the different letters is explained in the text.

of peak P. The ratio between the intensities of the central line P and the wings is 0.62 ± 0.7 , close to the theoretical value of $2/3$. Our interpretation is further supported by the results of comparisons of the measured signals with the signal calculated by assuming a random orientation of the crystalline grains and first order quadrupolar shifts of the transitions $\pm \frac{3}{2} \leftrightarrow \pm \frac{1}{2}$ for spin $I = 3/2$ nuclei according to [28]

$$\Delta f_Q^{(1)} = \pm \frac{f_Q}{2} [3 \cos^2 \theta - 1 - \eta \sin^2 \theta \cos 2\phi] \quad (19)$$

Here, θ and ϕ are the spherical angles describing the orientation of the principal axes of the electric field gradient tensor with respect to the direction of the applied magnetic field. The dotted line in Figure 4 for $T = 94.5$ K represents the calculated signal without the contribution of the central transition $+\frac{1}{2} \leftrightarrow -\frac{1}{2}$ (the peak labelled P). The best coincidence is achieved with a quadrupolar frequency $f_Q = 1/2 \cdot \Delta f_W = 1.4$ MHz and an asymmetry parameter $\eta = 0.5$. No substantial variations in the shape and the width of the wings were found in the temperature range between 295 and 88 K, suggesting only very small rearrangements of electrical charge above T_X .

A generalized broadening of the NMR spectra, revealed by a substantial loss of intensity of the central line P, occurs at T_X upon cooling, as is shown in Figure 5 and in the inset of Figure 3. At T_X , peak P transforms into three different NMR signals, whose temperature evolution can be followed down to 30 K. The three NMR signals are (a) a narrow signal labelled A, (b) a prominent rectangular signal in the range B_1 - B_2 , labelled B, and, (c) another rectangular signal, labelled C, in the range C_1 - C_2 . Either the position or the ranges of the signals are indicated with the corresponding letters in the spectra displayed in Figure 5.

The intensity of peak A is clearly smaller than that of the signals B and C. The relative frequency shift K_A is represented in the inset (a) of Figure 5 as a function of temperature T . Comparing $K_A(T)$ with the extrapolation of K_P to low temperatures reveals a discontinuous change of slope at exactly T_X . The FWHM Δf_A of signal A exhibits an abrupt increase, followed by a trend to saturation to the constant value $\Delta f_A \approx 45$ kHz, which is reached at temperatures between 70 and 60 K (see inset (b) of Figure 5).

The effective frequency width Δf_B of signal B is calculated as

$$\Delta f_B = f_{B_2} - f_{B_1} - \Delta f_P^* \quad (20)$$

where f_{B_1} and f_{B_2} are the frequencies of the lower and upper limits of the rectangular signal B, and $\Delta f_P^* = 40$ kHz represents the total width in the paramagnetic state at T_X . In order to emphasize the influence of the ordering on the NMR signal, Δf_P^* has to be subtracted from the total width of signal B (see Equation (20)). In Figure 6 we present the temperature dependence of Δf_B . In the inset we compare Δf_B with Δf_C , the latter being

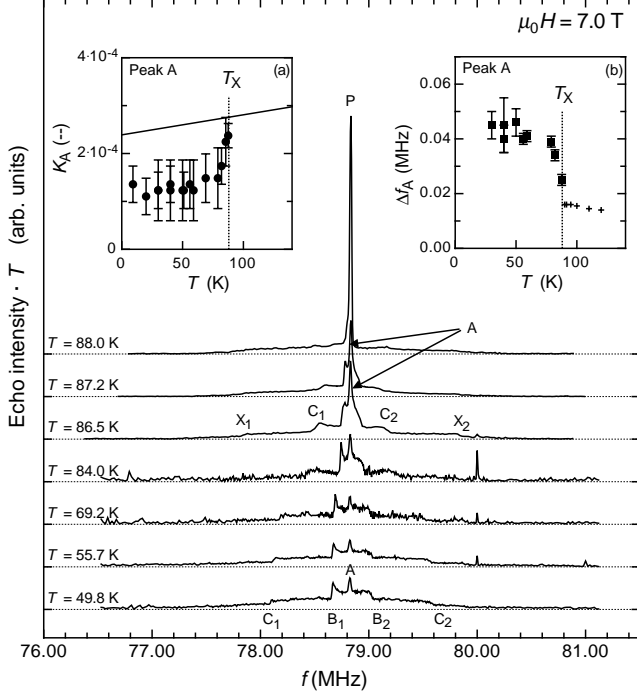


FIG. 5: ^{23}Na NMR spectra measured in a fixed magnetic field of $\mu_0 H = 7.0$ T, for $T \leq 88.0$ K. The integrated echo-intensity, multiplied with the temperature T , is plotted as a function of the irradiation frequency f . The significance of the different letters is explained in the text. Inset (a): Relative frequency shift K_A as a function of temperature T of the ^{23}Na NMR line A ($T \leq 88$ K). The solid line is the extrapolation for $T \leq 88$ K of the solid line approximating K_P in Figure 3. Inset (b): FWHM Δf_A as a function of temperature T of the ^{23}Na NMR line A ($T \leq 88$ K). The small crosses represent $\Delta f_P(T)$ ($T \geq 88$ K).

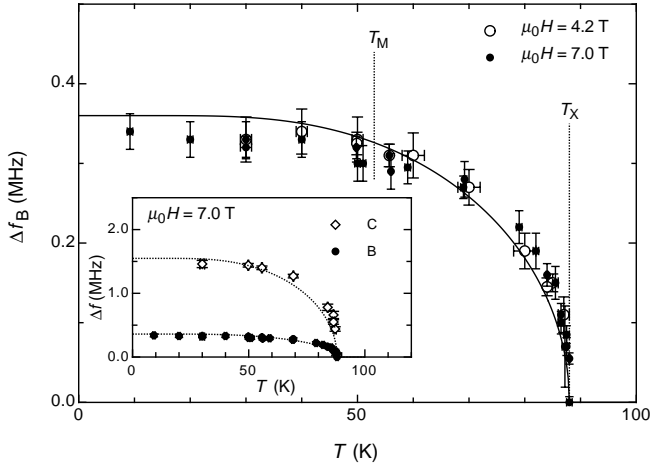


FIG. 6: Width Δf_B of the rectangle-shaped signal B as a function of temperature T . Δf_B is extracted from the ^{23}Na NMR spectra measured in magnetic fields $\mu_0 H = 4.2$ T and $\mu_0 H = 7.0$ T. The solid line represents the function (22). Inset: Δf of the signals B and C.

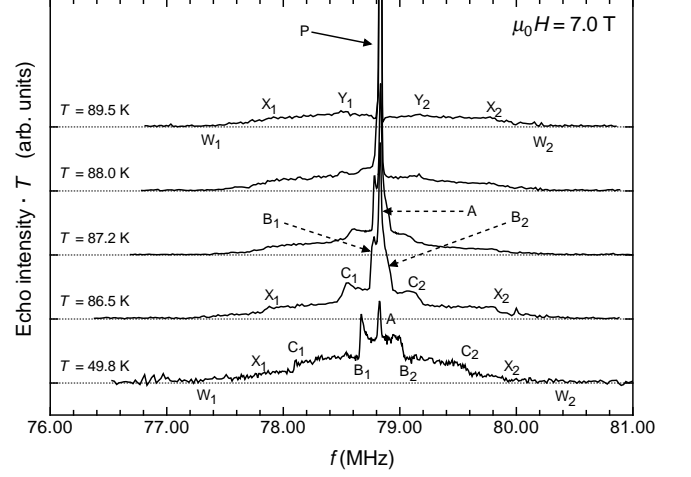


FIG. 7: ^{23}Na NMR spectra measured in a fixed magnetic field of $\mu_0 H = 7.0$ T, for T between 86.5 and 89.5 K, and at $T = 49.8$ K. The integrated echo-intensity, multiplied with the temperature T , is plotted as a function of the irradiation frequency f . The significance of the different letters is explained in the text.

calculated in the same way as Δf_B . Δf_B and Δf_C both increase with decreasing temperature, approaching a constant value for $T \rightarrow 0$. From the main-frame diagram it is obvious that Δf_B is magnetic-field independent. The ratio

$$\Delta f_C / \Delta f_B = 4.2 \pm 0.2 \quad (21)$$

is H - and T -independent, indicating that the broadening of the two signals B and C is of common origin. The behaviour of $\Delta f_B(T)$ suggests that it can be considered to reflect an order parameter, as is indicated by the good agreement between the experimental data and

$$\Delta f_B(T) = \Delta f_B(0) \cdot \phi(T/T_X) \quad , \quad (22)$$

with $\Delta f_B(0) = 0.36$ MHz, and $\phi(\alpha)$ representing the order-parameter type function, which is the solution of the functional equation $\phi(\alpha) = \tanh(\phi(\alpha)/\alpha)$.

The variation of the spectra below T_X is thus attributed to the formation of a staggered internal field. In particular, it is excluded that signals B and C are simply modifications of the quadrupolar wings W observed at temperatures above T_X . Signals B and C emerge from the the NMR line P, as is clearly recognized in Figure 7. The total intensity of the NMR signal ($P+W$ above T_X , $A+B+C+W$ below T_X) is unchanged within an error of 5% between 94.5 and 86.5 K, excluding a loss of signal intensity across the transition. The wing features W_1 , X_1 and W_2 , X_2 are not affected by the phase transition at T_X , yielding further support for the interpretation that signals B and C are due to transitions $+\frac{1}{2} \leftrightarrow -\frac{1}{2}$, and, in addition, excluding the possibility of substantial charge rearrangements at T_X . The

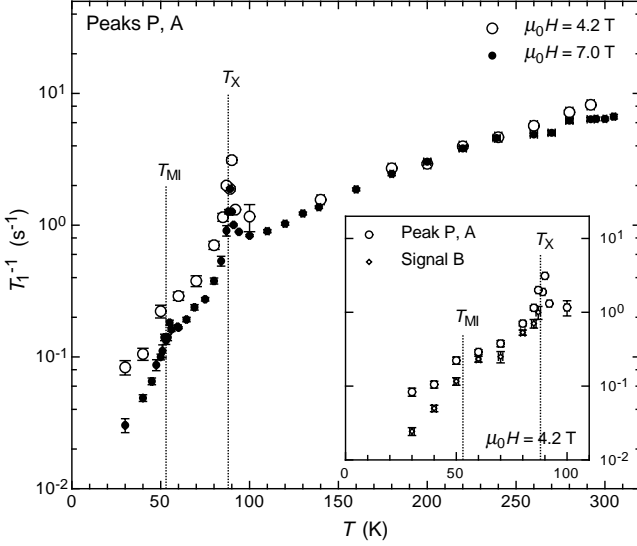


FIG. 8: ^{23}Na NMR spin-lattice relaxation rate T_1^{-1} of the signals P ($T \geq 88$ K) and A ($T \leq 88$ K), as a function of temperature T , and in fixed magnetic fields $\mu_0 H = 4.2$ T and $\mu_0 H = 7.0$ T, respectively. Inset: comparison of $T_1^{-1}(T)$ of the signals A and B, for temperatures below 100 K and in fixed magnetic field $\mu_0 H = 4.2$ T.

values of the staggered field at the B- and C-sites, respectively, are $\mu_0 H_{\text{int,B}} = \Delta f_{\text{B}}(0)/2\gamma_{\text{Na}} \approx 0.016$ T and $\mu_0 H_{\text{int,C}} = 4.1 \cdot \mu_0 H_{\text{int,B}} \approx 0.068$ T, respectively.

As may be seen in Figures 5 and 7, the quadrupolar features W_1 , X_1 and W_2 , X_2 persist with decreasing temperature down to 50 K. The changes in their frequencies f_{W_1} , f_{W_2} , f_{X_1} and f_{X_2} , as well as the rounding-off of their contours, are accommodated by the broadening of the signals B and C.

A peak-shaped anomaly in the spectra is observed at the low-frequency end of the rectangular signal B, i.e., at the feature labelled B_1 in Figure 5. We suspect that it is a deformation of the B-labelled rectangular signal, due to the partial alignment of grains of the sample in the magnetic field. Else it may be an indication for a ferromagnetic component along the external field in the ordered state.

B. Spin-lattice relaxation rate T_1^{-1}

We measured the ^{23}Na NMR spin-lattice relaxation rate T_1^{-1} in the temperature range between 30 K and 305 K and in fixed magnetic fields $\mu_0 H = 4.2$ T and $\mu_0 H = 7.0$ T. T_1^{-1} was obtained from monitoring the recovery of the ^{23}Na nuclear magnetization m after the application of a long comb of radiofrequency pulses. The experiments were performed by irradiating a frequency window of about 25 kHz. Above T_X , the frequency was chosen to irradiate the NMR line P, while below T_X we

centered the window such as to cover either line A or part of signal B. In all the cases, a double exponential recovery function [29]

$$m(t) = m_{\infty} \left[1 - \left(0.4e^{-\frac{t}{T_1}} + 0.6e^{-\frac{t}{6T_1}} \right) \right] \quad , \quad (23)$$

characteristic of $I = 3/2$ nuclei with only the central transition $+\frac{1}{2} \leftrightarrow -\frac{1}{2}$ irradiated, was observed.

In Figure 8 we display the temperature dependence of T_1^{-1} and we note a prominent peak in $T_1^{-1}(T)$ at $T_X = 88$ K. Above T_X , $T_1^{-1}(T)$ of the NMR line labelled P is field independent, as is expected in a state dominated by paramagnetic moments, but slowly decreases by a factor of 5 per 100 K upon cooling. The fact that the magnetization recovery follows Equation (23) supports the identification of signal P to be due to the central transition $+\frac{1}{2} \leftrightarrow -\frac{1}{2}$.

Below T_X , $T_1^{-1}(T)$ exhibits an overall decrease by a factor of 20-50 per 100 K. The comparison of the values obtained for $\mu_0 H = 4.2$ T and $\mu_0 H = 7.0$ T, respectively, indicates a decrease of T_1^{-1} with increasing field at constant temperature, a dependence compatible with the scenario of magnetic ordering. As shown in the inset of Figure 8, the ratio between the values of T_1^{-1} of the signals A and B increases from 1 at 88 K to about 4 at 30 K. This indicates that the two signals arise from different Na sites. The general reduction of $T_1^{-1}(T)$ upon cooling is interrupted by a small cusp around the metal-insulator transition temperature $T_{\text{MI}} = 53$ K.

C. Spin-spin relaxation rate T_2^{-1}

Our measurements of the ^{23}Na NMR spin-spin relaxation rate were made in the temperature range between 30 K and 305 K and in fixed magnetic fields $\mu_0 H = 4.2$ T and $\mu_0 H = 7.0$ T. The spin-echo lifetime T_2^* was obtained by monitoring the spin-echo intensity as a function of the pulse delay time τ in the $\pi/2$ -delay- π echo sequence. The irradiation conditions were chosen to be the same as in the T_1 -experiments. At all temperatures, the intensity $m(t)$ decayed according to the stretched exponential behaviour

$$m(t) = m(0) \exp \left(-(t/T_2^*)^b \right) \quad . \quad (24)$$

Here, $t = 2(2/\pi \cdot t_{\pi/2} + \tau) + t_{\pi} \approx 2\tau$ [30], where $t_{\pi/2}$ and t_{π} are the durations of the $\pi/2$ and π spin-echo pulses. The spin-spin lattice relaxation rate T_2^{-1} is approximated with

$$T_2^{-1} \approx T_2^{*-1} \quad , \quad (25)$$

which is justified because $T_2^{*-1} \ll T_1^{-1}$.

In Figure 9 we display the temperature dependences of T_2^{-1} and, in the inset, of the parameter b appearing in the stretched exponential function (24). A value $b \neq 1$ is attributed to indirect coupling between the nuclear spin at the different Na nuclei (for example, electron-mediated spin-spin interaction [31, 32]), as opposed to direct scalar

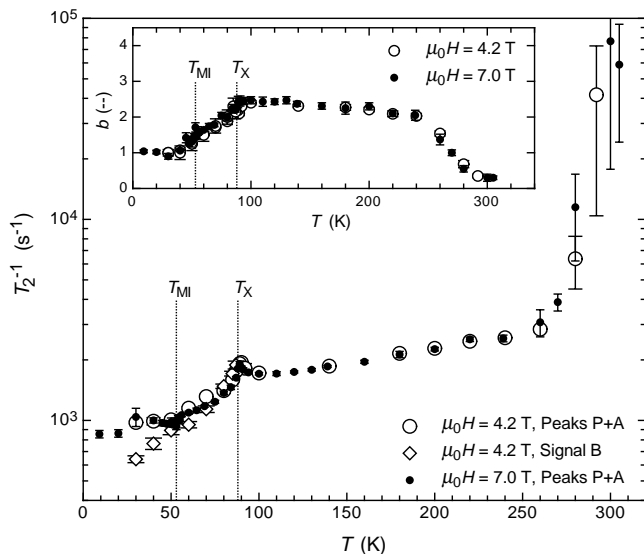


FIG. 9: ^{23}Na NMR spin-spin relaxation rate T_2^{-1} as a function of temperature T in fixed magnetic fields $\mu_0 H = 4.2$ T (signals P, A and B) and $\mu_0 H = 7.0$ T (signals P and A only). Inset: parameter b appearing in the intensity decay (24), as a function of T .

or dipolar interactions which yield $b = 1$. For example, a value $b = 2$ was predicted and observed for the $^{63,65}\text{Cu}$ NMR spin-echo decay in high-temperature superconductors [33, 34]. The exact value of b depends on the details of the indirect coupling mechanism. Nevertheless, a qualitative knowledge of the temperature dependence $b(T)$ is useful, because it can reflect modifications in the interaction-mediating electron gas.

Four different temperature intervals can be identified, each characterized by its own $b(T)$ regime, and thus by its own electronic regime. In the temperature range from 88 to 260 K, T_2^{-1} is field independent and upon cooling slowly decreases by a factor of about 1.4 per 100 K. The parameter $b \approx 2.4$ is approximately constant.

Upon cooling, the peak in $T_2^{-1}(T)$ at $T_X = 88$ K is followed by an abrupt decrease. Between 88 and 53 K, T_2^{-1} is reduced by a factor of 6 per 100 K upon cooling, and the parameter b decreases from $b \approx 2.4$ to $b \approx 1.3$. The reduction of T_2^{-1} when increasing the magnetic field from $\mu_0 H = 4.2$ T to $\mu_0 H = 7.0$ T is small (less than a factor of 1.1). Differences between the values of T_2^{-1} for the signals A and B are marginal (less than a factor 1.2).

Possible anomalies in $T_2^{-1}(T)$ at $T_{\text{MI}} = 53$ K are hidden by the noise in the data. Below T_{MI} , $T_2^{-1}(T)$ of signal A tends to a constant value with decreasing temperature, while for signal B, $T_2^{-1}(T)$ continues to decrease. The parameter b is approximatively unity below 40 K.

Above 260 K, an abrupt upturn in $T_2^{-1}(T)$ with increasing temperature is observed. The enhancement is about a factor of 800 per 100 K. The parameter b changes from $b \approx 2.4$ at 260 K to $b \approx 0.5$ at 300 K.

VI. DISCUSSION OF THE RESULTS

Metallic phase above T_{MI} .— We first turn our attention to the very unusual properties of $\text{Na}_{0.5}\text{CoO}_2$ in the metallic phase above T_{MI} and first discuss the magnetic susceptibility χ . At temperatures $T \geq T_X$, $\chi(T)$ is more or less identical for $\text{Na}_{0.5}\text{CoO}_2$ and $\text{Na}_{0.31}\text{CoO}_2$ [2], and is attributed to Pauli paramagnetism. The decrease of $\chi(T)$ of about 20% between 300 and 100 K is thus not a singular feature of $\text{Na}_{0.5}\text{CoO}_2$. The equivalence of the values of $\chi(T)$ above T_X for $x \leq 0.5$ suggests that if the effective mass m^* of the charge carriers is the same in all compounds, then their density is approximately the same across the range defined by $x \leq 0.5$ of the Na_xCoO_2 -series. At this point, we note that the substantial enhancement of the effective electron mass for $\text{Na}_{0.5}\text{CoO}_2$, evaluated from the high-temperature saturation value of χ and cited above in Equation (13), is consistent with the result of an LSDA+U calculation [21].

A remaining puzzle of $\text{Na}_{0.5}\text{CoO}_2$ is the apparent inconsistency between magnetic and transport properties. At room temperature, the conductivity σ is of the same order of magnitude for $\text{Na}_{0.5}\text{CoO}_2$ and $\text{Na}_{0.31}\text{CoO}_2$ [2], and, more generally, for all materials with $0.31 \leq x \leq 0.75$. This value implies a very short mean free path l , in particular for $\text{Na}_{0.5}\text{CoO}_2$, as cited above in Equation (7), and indicates an unusual transport regime. It remains an open question whether a description of the transport properties in terms of a mean free path concept makes sense at all for Na_xCoO_2 . While for $x = 0.31$, and, in general, for x different from 0.5, the conductivity σ at least increases with decreasing temperature as expected for metals, for $\text{Na}_{0.5}\text{CoO}_2$, $\sigma(T)$ exhibits the opposite trend, indicating that magnetic and transport properties are not correlated in this case.

Evidence for magnetic ordering at T_X .— The most instructive result of our experiments, the temperature evolution of the ^{23}Na NMR spectra, provides a strong indication for $\text{Na}_{0.5}\text{CoO}_2$ to order antiferromagnetically at $T_X = 88$ K, as previously concluded on the basis of μSR -data [12] and of results of Co NMR measurements [13].

Above T_X , the paramagnetic behaviour is reflected by the temperature- and field-independent proportionality $K_P \sim \chi$. Assuming an equal occupation of the sites Na1 and Na2, the appearance of a single NMR signal P suggests a uniform distribution of magnetic moment density in the conducting CoO_2 -layers, implying a value of the hyperfine coupling constant A_P that is equal for all Na sites.

The broadening of signals B and C upon cooling below T_X (see Figure 6) can only be accounted for by assuming the formation of a staggered internal field H_{int} . The magnetic nature of the transition is confirmed by the kink in $\chi(T)$ (see Figure 2) and by the anomalies in $T_1^{-1}(T)$ (see Figure 8), $T_2^{-1}(T)$ and $b(T)$ (see Figure 9) at T_X . The abrupt decrease of $T_1^{-1}(T)$ below T_X is typical for the suppression of magnetic fluctuations, which, in our case, is caused by the onset of an ordered state. The

magnetic ordering yields two inequivalent sites, B and C, with $H_{\text{int,C}}/H_{\text{int,B}} \approx 4.2$. From the ratio of the signal intensities B and C, which is close to 1, we argue that the two signals arise from two magnetically inequivalent but equally occupied Na sites. Although other possibilities cannot be excluded a priori, it is plausible to identify the two sites with Na1 and Na2, an assignment that results from previous work [1, 7].

Itinerant type of ordering at T_X .- In comparison with the electronic-transport and magnetic-ordering features of a large number of oxide compounds [35], $\text{Na}_{0.5}\text{CoO}_2$ seems to be a special case. The magnetic order sets in at a temperature that significantly exceeds the metal-insulator transition temperature T_{MI} , and not at T_{MI} [36] or below [37, 38].

From the analysis of the $\chi(T)$ data of $\text{Na}_{0.5}\text{CoO}_2$, presented in Section IV, we conclude that at most a few percent of the Co ions carry a local magnetic moment which would be present also in the metallic phase. This amount is certainly too small to identify the transition at T_X as an ordering of such moments upon cooling. This implies that the observed antiferromagnetic order below T_X most likely involves the magnetic moments of the conduction electrons, and thus is of itinerant type.

Origin of signal A.- Despite its weak intensity, signal A is not attributed to the persistence of a small portion of paramagnetic phase in the sample. This scenario would imply that signal A is a remnant of signal P. The NMR data $K_A(T)$, $\Delta f_A(T)$, $T_{1,A}^{-1}(T)$ and $T_{2,A}^{-1}(T)$ below T_X (see Section V) exclude this interpretation because their T -variations are correlated to those of signals B and C. The latter are clearly features related to the ordered phase below T_X . Signal A may, e.g., be due to Na nuclei which couple more weakly to the ordered moments, because they are located at boundaries of domains with different magnetic and/or Na-ordering patterns.

Absence of charge disproportionation or structural modifications.- The temperature evolution of the ^{23}Na NMR spectra around T_X ($T_X \pm 5$ K) provides no evidence for significant variations of the quadrupolar parameters f_Q and η (see Figure 7). This observation allows to straighten out a controversy, in the sense that we can exclude a charge disproportionation or a structural transition to occur at T_X .

The features of the quadrupolar wings in the spectra can be tracked down to 50 K, i.e., to below the metal-insulator transition temperature T_{MI} (see Figure 5). We did not observe abrupt changes in these features at T_{MI} . This excludes an abrupt charge disproportionation with decreasing temperature at T_{MI} . The formal valence of the Co ions is either unaffected or, at most, only gently altered by the metal insulator transition.

Magnetic component of the metal-insulator transition at T_{MI} .- Our data reveal that the metal insulator transition also involves a magnetic component. The abrupt decrease in $\chi(T)$ below $T_{\text{MI}} = 53$ K upon cooling, and the observed anomalies in $T_1^{-1}(T)$ and $T_2^{-1}(T)$ support this claim. The metal-insulator transition is not reflected

in the temperature evolution of the ^{23}Na NMR spectra, indicating that the staggered magnetic field at the Na sites is not significantly modified at T_{MI} . A magnetic component of the metal-insulator transition was already claimed by the authors of Ref.[12]. Their conclusions were based on anomalous temperature dependences of two of the three detected μSR -frequencies at T_{MI} , which were attributed to moderate reorientations of magnetic moments. Such a scenario seems to be contradicted by our T_1^{-1} data. The saturation trend upon cooling exhibited by $T_1^{-1}(T)$ above T_{MI} is interrupted by an abrupt decrease in $T_1^{-1}(T)$ below T_{MI} . This behaviour cannot be accommodated by small rearrangements of the magnetic moments, but more likely hints for the onset of a different regime of magnetic fluctuations below T_{MI} .

Curie-Weiss behaviour of $\chi(T)$ at low temperatures.- In previous work [8] an anomaly in the electrical conductivity $\sigma(T)$ at 25 K was observed and attributed to the occurrence of a phase transition. Based on anomalies in the temperature evolution of μSR -frequencies at 29 K, the authors of Ref.[12] suggested some rearrangements of magnetic moments in the ordered phase. In view of these speculations, the observed upturn of $\chi(T)$ with decreasing temperature below 25 K (see Section IV) requires some additional comments. The presence of such an upturn was already reported in Ref.[2], but other reports suggest that $\chi(T)$ tends to a constant value with $T \rightarrow 0$ [8, 13]. The discrepancies suggest that the free magnetic moments, which determine the low-temperature Curie-Weiss behaviour of $\chi(T)$, may be related to presence of defects or domains in the sample, whose concentration is sample dependent. In any case, only a few percent of Co ions are involved. Hence we argue that the upturn in $\chi(T)$ in $\text{Na}_{0.5}\text{CoO}_2$ is not related to any phase transition at all.

High-temperature regime.- Anomalies in $T_2^{-1}(T)$ and $b(T)$ are observed at 260 K (see Figure 9). They are accompanied by the onset of a trend to saturation of $\chi(T)$ (see Figure 2). However, we did not observe concomitant significant changes in the ^{23}Na NMR spectra, implying that the cause of the above anomalies is very unlikely of magnetic type, but rather due to the onset of a different regime of interaction between the magnetic moments of the Na nuclei. Since the onset of Na motion would be reflected by visible changes in the spectra, as was observed in $\text{Na}_{0.7}\text{CoO}_2$ [4, 39], we attribute the anomalies in $T_2^{-1}(T)$ and $b(T)$ to small rearrangements in the Na positions.

VII. CONCLUSIONS

In $\text{Na}_{0.5}\text{CoO}_2$, the onset of the insulating phase at $T_{\text{MI}} = 53$ K is preceded by an unusual type of antiferromagnetic ordering below $T_X = 88$ K, i.e., in the metallic phase. Our data exclude a concomitant structural-type of ordering at T_X . The physical properties of the metallic phase above T_{MI} are characterized by a large effective

mass and an extremely short mean free path of the itinerant charge carriers. A convincing description of the itinerant-electron system of $\text{Na}_{0.5}\text{CoO}_2$ above T_{MI} is yet to be found.

Note added.- During the preparation of this manuscript, we got aware of a Co and Na NMR study on $\text{Na}_{0.5}\text{CoO}_2$ [40]. The authors report clear evidence of antiferromagnetic ordering below 86 K, not accompanied by any charge disproportionation with decreasing temperature. These conclusions are identical

to those which follow from our measurements.

Acknowledgments

We acknowledge useful discussions with M. Indergand and M. Sigrist. We also acknowledge the support of K. Magishi in interpreting part of the NMR data.

-
- [1] Q. Huang, M. L. Foo, R. A. Pasacal, Jr., J. W. Lynn, B. H. Toby, T. He, H. W. Zandbergen, and R. J. Cava, Phys. Rev. B **70**, 184110 (2004).
 - [2] M. L. Foo, Y. Wang, S. Watauchi, H. W. Zandbergen, T. He, R. J. Cava, and N. P. Ong, Phys. Rev. Lett. **92**, 247001 (2004).
 - [3] I. Terasaki, Y. Sasago, and K. Uchinokura, Phys. Rev. B **56**, 12685(R) (1997).
 - [4] J. L. Gavilano, D. Rau, B. Pedrini, J. Hinderer, H. R. Ott, S. M. Kazakov, and J. Karpinski, Phys. Rev. B **69**, 010040(R) (2004).
 - [5] J. Sugiyama, H. Itahara, J. H. Brewer, E. J. Ansaldo, T. Motohashi, M. Karppinen, and H. Yamauchi, Phys. Rev. B **67**, 214420 (2003).
 - [6] K. Takada, H. Sakurai, E. Takayama-Muromachi, F. Izumi, R. A. Dilanian, and T. Sasaki, Nature (London) **422**, 53 (2003).
 - [7] H. W. Zandbergen, M. Foo, Q. Xu, V. Kumar, , and R. J. Cava, Phys. Rev. B **70**, 024101 (2004).
 - [8] Q. Huang, M. L. Foo, J. W. Lynn, H. W. Zandbergen, G. Lawes, Y. Wang, B. H. Toby, A. P. R. N. P. Ong, and R. J. Cava, J. Phys.: Cond. Mat. **16**, 5803 (2004).
 - [9] N. L. Wang, D. Wu, G. Li, X. H. Chen, C. H. Wang, and X. G. Luo, Phys. Rev. Lett. **93**, 147403 (2004).
 - [10] P. Zhang, R. B. Carpaz, M. L. Cohen, , and S. G. Louie, Phys. Rev. B **71**, 153102 (2005).
 - [11] Y. J. Uemura, P. L. Russo, A. T. Savici, C. R. Wiebe, G. J. MacDougall, G. M. Luke, M. Mochizuki, Y. Yanase, M. Ogata, M. L. Foo, et al., cond-mat/0403031.
 - [12] P. Mendels, D. Bono, J. Bobroff, G. Collin, D. Colson, N. Blanchard, H. Alloul, I. Mukhamedshin, F. Bert, A. Amato, et al., Phys. Rev. Lett. **94**, 136403 (2005).
 - [13] M. Yokoi, T. Moyoshi, Y. Kobayashi, M. Soda, Y. Yasui, M. Sato, and K. Kakurai, cond-mat/0506220.
 - [14] K.-W. Lee, J. Kuneš, and W. E. Pickett, Phys. Rev. B **70**, 045104 (2004).
 - [15] P. Zhang, W. Luo, M. L. Cohen, and S. G. Louie, Phys. Rev. Lett. **93**, 236402 (2004).
 - [16] M. Z. Hasan, D. Quian, Y. Li, A. V. Fedorov, Y.-D. Chuang, A. P. Kuprin, M. L. Foo, and R. J. Cava, cond-mat/0501530.
 - [17] H.-B. Yang, S.-C. Wang, A. K. P. Sekharan, H. Matsui, S. Souma, T. Sato, T. Takahashi, T. Takeuchi, J. C. Campuzano, R. Jin, et al., Phys. Rev. Lett. **92**, 246403 (2004).
 - [18] M. Z. Hasan, Y.-D. Chuang, D. Quian, Y. W. Li, Y. Kong, A. Kuprin, A. V. Fedorov, R. Kimmerling, E. Rothenberg, K. Rossnagel, et al., Phys. Rev. Lett. **92**, 246402 (2004).
 - [19] Z. Li, J. Yang, J. G. Hou, and Q. Zhu, Phys. Rev. B **71**, 024502 (2005).
 - [20] K.-W. Lee, J. Kuneš, P. Novak, and W. E. Pickett, Phys. Rev. Lett. **94**, 026403 (2005).
 - [21] S. Zhou, M. Gao, H. Ding, P. A. Lee, and Z. Wang, Phys. Rev. Lett. **94**, 206401 (2005).
 - [22] H.-B. Yang, Z.-H. Pan, A. K. P. Sekharan, T. Sato, S. Souma, T. Takahashi, R. Jin, B. C. Sales, D. Mandrus, A. V. Fedorov, et al., cond-mat/0501403.
 - [23] M. Indergand, Y. Yamashita, H. Kusunose, and M. Sigrist, Phys. Rev. B **71**, 214414 (2005).
 - [24] S. A. Carter, T. F. Rosenbaum, M. Lu, H. M. Jaeger, P. Metcalf, J. M. Honig, and J. Spalek, Phys. Rev. B **49**, 7898 (1994).
 - [25] D. B. McWhan, A. Menth, J. P. Remeika, W. F. Brinkman, and T. M. Rice, Phys. Rev. B **7**, 1920 (1973).
 - [26] Y. Moritomo, Y. Tomioka, A. Asamitsu, Y. Tokura, and Y. Matsui, Phys. Rev. B **51**, 3297 (1995).
 - [27] S. Zhou, M. Gao, H. Ding, P. A. Lee, and Z. Wang, cond-mat/0503346.
 - [28] A. Abragam, *Principles of Nuclear Magnetism* (Oxford University Press, Oxford, 1986).
 - [29] A. Suter, M. Mali, J. Roos, and D. Brinkman, J. Phys.: Cond. Mat. **10**, 5977 (1998).
 - [30] C. P. Slichter, *Principles of Magnetic Resonance* (Springer Verlag, Berlin, 1990), 3rd ed.
 - [31] J. P. Ansermet, C. P. Slichter, and J. H. Sinfelt, J. Chem. Phys. **88**, 5963 (1988).
 - [32] R. E. Walstedt and S.-W. Cheong, Phys. Rev. B **51**, 3163 (1995).
 - [33] C. H. Pennington, D. J. Durand, C. P. Slichter, J. P. Rice, E. D. Bukowski, and D. M. Ginsberg, Phys. Rev. B **39**, 274 (1989).
 - [34] R. E. Walstedt and S.-W. Cheong, Phys. Rev. B **53**, 6030(R) (1996).
 - [35] M. Imada, A. Fujimori, and Y. Tokura, Rev. Mod. Phys. **70**, 1039 (1998).
 - [36] M. Takano and Y. Takeda, Bull. Ins. Chem. Res., Kyoto Univ. **61**, 406 (1983).
 - [37] S. H. Lee and S. W. Chong, Phys. Rev. Lett. **79**, 2514 (1997).
 - [38] B. J. Sternlieb, J. P. Hill, U. C. Wildgruber, G. M. Luke, B. Nachumi, Y. Moritomo, and Y. Tokura, Phys. Rev. Lett. **76**, 2169 (1996).
 - [39] J. L. Gavilano, B. Pedrini, and H. R. Ott, unpublished.
 - [40] J. Bobroff, G. Lang, H. Alloul, N. Blanchard, and G. Collin, cond-mat/050607514.