

Striking properties of Superconductor/Ferromagnet structures with spin-dependent scattering

M. Fauré¹, A. I. Buzdin^{1,2}, A. A. Golubov³, M. Yu. Kupriyanov⁴

¹*Centre de Physique Moléculaire Optique et Hertzienne,
Université Bordeaux 1-UMR 5798, CNRS, F-33405 Talence Cedex, France*

²*Institut Universitaire de France, Paris, France*

³*Faculty of Science and Technology, University of Twente,
7500 AE Enschede, The Netherlands and*

⁴*Nuclear Physics Institute, Moscow State University, Moscow, 119992 Russia*

Abstract

We investigate Superconductor/Ferromagnet (S/F) hybrid structures in the dirty limit, described by the Usadel equations. More precisely, the oscillations of the critical temperature and critical current with the thickness of the ferromagnetic layers are studied. We show that spin-flip and spin-orbit scattering lead to the decrease of the decay length and the increase of the oscillations period. The critical current decay is more sensitive to these pair-breaking mechanisms than that of the critical temperature. These two scattering mechanisms should be taken into account to get a better agreement between experimental results and theoretical description. We also study the influence of the interface transparency on the properties of S/F structures.

PACS numbers: 74.50.+r, 74.80.Dm, 75.30.Et

I. INTRODUCTION

It has been known for quite a long time that superconductivity (S) and ferromagnetism (F) are two antagonistic orderings and that they can hardly coexist in a same compound. Although they tend to avoid each other, their mutual interaction may be studied when they are spatially separated, which is realized in Superconductor/Ferromagnet (S/F) hybrid structures (as a review, see [1, 2, 3]). Indeed, in such systems, superconductivity and ferromagnetism can influence each other through the so called 'proximity effect'. The main peculiarity of the proximity effect in S/F structures is the damping oscillatory behavior of the superconducting correlations in the F layers (while they monotonically decay in normal layers of Superconductor/Normal metal structures). In the dirty limit and for large exchange field, the characteristic lengths of the decay and oscillations are the same. They are given by $\xi_f = \sqrt{D_f/h}$, where D_f is the diffusion coefficient in the ferromagnet and h is the exchange field acting on the electrons spins. This unusual proximity effect leads to several striking phenomena, such as the non-monotonic dependence of the critical temperature and current of S/F multilayers on the F layers thickness and the realization of the so-called π junction in S/F/S trilayers [1, 2, 3].

Although the existing theory provides rather good qualitative description of the observed effects, there is still no complete quantitative agreement with experiments. This indicates that besides the exchange field, some additional pair-breaking mechanisms are present in the F layers. Indeed, spin-flip process is inherent to the ferromagnetic layers (because of magnetic impurities, spin-wave or non stoichiometric lattices) and may have dramatic consequences on superconductivity (contrary to non magnetic impurities that have very little impact). Such a pair-breaking mechanism also arises in usually used weak ferromagnetic alloys, because they are close to ferromagnetism disappearance and then quite favorable to large magnetic disorder. This can be inferred for instance from the very strong decrease of the critical current of S/F/S junctions as a function of the thickness of the ferromagnetic layer in experimental studies [4, 5, 6]. In such experiments, the ferromagnetic alloys used were $\text{Cu}_x\text{Ni}_{1-x}$ with $x \sim 0.5$, limit range of concentration for ferromagnetic properties. In addition, the pair destruction due to spin-orbit interaction must be taken into account as well.

Though the spin-flip and spin-orbit interactions in the ferromagnetic material were in-

roduced in several recent theoretical studies on proximity effect in S/F hybrids, only few simple limiting cases were considered (we'll give appropriate references below). Thus the problem of quantitative description of these effects in S/F multilayered systems is still unsolved. In this paper we present the results of detailed theoretical study of the influence of spin-flip and spin-orbit scattering mechanisms on the critical temperature (T_c^*) and critical current (I_c) of S/F multilayered systems. We obtain analytical and numerical solutions of the problem which provide the basis not only for qualitative understanding of experimental results but also to fit the data quantitatively. In particular, we show that spin-orbit and spin-flip scattering mechanisms influence differently the properties of S/F structures: spin-orbit mechanism can destroy the T_c^* and I_c oscillations while spin-flip scattering can only modify them. We also report on a striking non-intuitive behavior that the critical temperature and current can acquire with the variation of the S/F interface transparency.

II. LINEARIZED USADEL EQUATIONS

A very convenient set of equations for an inhomogeneous superconductor was elaborated by Eilenberger [7]. However, the Eilenberger equations can be replaced by the much simpler Usadel equations [8] when the electron scattering free path in S/F systems is shorter than the superconducting length, which is often the case. These equations are nonlinear but can be simplified when the temperature is close to the critical temperature T_c or at any temperature in the F layer when the transparency is low. We consider a S/F multilayered system where all physical quantities depend only on the coordinate x perpendicular to the layers. The natural choice of the spin-quantization axis is along the direction of the exchange field. In the general case, magnetic and spin-orbit scatterings mix up the up and down spin states. Therefore, two anomalous Green functions, namely $F_+ \sim \langle \psi_\uparrow \psi_\downarrow \rangle$ and $F_- \sim \langle \psi_\downarrow \psi_\uparrow \rangle$ are needed to describe this situation. The linearized Usadel equations may be written for $\omega > 0$ as [1, 9]

$$\left(\omega - \frac{D_s}{2} \frac{\partial^2}{\partial x^2} \right) F_{\pm s}(\omega, x) = \Delta(x), \quad (1)$$

in the S layers and

$$\left(\omega - \frac{D_f}{2} \frac{\partial^2}{\partial x^2} \pm i\hbar + \frac{1}{\tau_z} + \frac{2}{\tau_x} \right) F_{\pm f}(\omega, x) + \left(\frac{1}{\tau_{so}} - \frac{1}{\tau_x} \right) (F_{\pm f}(\omega, x) - F_{\mp f}(\omega, x)) = 0, \quad (2)$$

in the F layers, where $\Delta(x)$ is the superconducting order parameter, h is the exchange field, D_s (D_f) is the diffusion coefficient in the S(F) layer and ω are the Matsubara frequencies, $\omega = 2\pi T(n + \frac{1}{2})$. The parameter τ_{so} is the spin-orbit scattering time. The magnetic scattering times are $\tau_z = \tau_2 S^2 / \langle S_z^2 \rangle$ and $\tau_x = \tau_2 S^2 / \langle S_x^2 \rangle$. The rate τ_2^{-1} is proportional to the square of the exchange interaction potential (the notations are the same as in [10]). Note that the microscopical Green functions theory of superconductors with magnetic impurities and spin-orbit scattering was proposed by Abrikosov and Gor'kov [11].

Besides, the usually used ferromagnets present a strong uniaxial anisotropy. In that case, the perpendicular fluctuations of the exchange field are suppressed, that is $\tau_x^{-1} \sim 0$. Therefore, henceforth, τ_z will be noted as the magnetic scattering time τ_m . The spin-flip scattering is now simply incorporated replacing ω by $\omega + \frac{1}{\tau_m}$ in the standard Usadel equation, and τ_m is the magnetic scattering time (see for example [12]). Note that the Usadel equations in the F layers are not coupled anymore when $\tau_{so}^{-1} = 0$, and only one equation is needed.

III. THEORETICAL DESCRIPTION OF THE NON-MONOTONIC DEPENDENCE OF T_c^* .

The common feature of all the S/F bilayered and multilayered heterostructures is the non monotonic evolution of the critical temperature T_c^* with the thickness of the ferromagnetic layer. This behavior was first predicted by Buzdin and Kuprianov [13] and Radovic *et al.* [14], and was since then intensively studied both theoretically and experimentally (as a review, see [1]). The presence of magnetic scattering can result in an additional decrease of the transition temperature (on the contrary, nonmagnetic impurities do not affect the transition temperature). Note that the theoretical description of T_c^* for ferromagnetic layers with spin-orbit scattering was performed by Demler *et al.* [15] and Oh *et al.* [16]. In the present section, we therefore mainly focus on the influence of spin-flip process and neglect spin-orbit scattering. We report here on the influence of the spin-flip scattering on the non monotonic dependence of T_c^* when the thickness of the superconducting layer is supposed to be small, *i. e.* $d_s \ll \xi_s$. In that case, an analytical solution may be obtained. It should also be underlined that the question of the spin-flip role was first addressed by Tagirov [17] in the discussion of T_c^* of SF multilayers and by Fal'ko *et al.* [18] in the study of the resistance of a diffusive F/N junction.

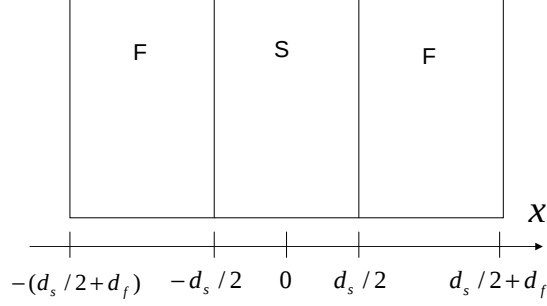


FIG. 1: Geometry of the considered system.

A. Influence of spin-flip scattering on T_c^*

We consider a S/F multilayered system with F layers of thickness d_f and parallel magnetization directions and S layers of thickness d_s , see Fig. 1 (this system is also equivalent to a S/F bilayer of thicknesses $d_f/2$ and $d_s/2$ respectively). Further, we assume that the SF interfaces are not 'magnetically-active', i.e. there is no rotation of the quasiparticle spin at the interfaces as considered in Refs. [19, 20, 21, 22]. Under these conditions, long-range spin-triplet superconductivity does not appear [3]. Discussion of the role of spin-flip scattering in a ferromagnet in combination with magnetically-active SF interfaces and/or noncollinear magnetizations requires separate study.

The anomalous Green's function F_s varies a little in the S layer and may be approximated by a simple expansion up to the second order x^2 (see for example [23] and [24])

$$F_s(x, \omega) = F_0 \left(1 - \frac{\beta_\omega}{2} x^2 \right), \quad (3)$$

where F_0 is the value of the anomalous Green's function at the center of the S layer. Moreover, in that case, the spatial variation of the pair potential $\Delta(x)$ can be neglected $\Delta(x) \sim \Delta$. It follows from Eq. (1) that $F_0 = \frac{\Delta}{\omega + \tau_s^{-1}}$ where $\tau_s^{-1} = \frac{D_s}{2} \beta_\omega$ is the complex pair-breaking parameter.

The Usadel equation in the S layer is completed by the self-consistency equation

$$\Delta(x) \ln \frac{T_c}{T_c^*} + \pi T_c^* \sum_{\omega} \left(\frac{\Delta(x)}{|\omega|} - F_{\pm s}(x, \omega) \right) = 0, \quad (4)$$

where T_c is the bare transition temperature of the superconducting layer in the absence of the proximity effect. Hence, this self-consistent equation gives for T_c^*

$$\ln \frac{T_c^*}{T_c} = \Psi \left(\frac{1}{2} \right) - \text{Re} \Psi \left\{ \frac{1}{2} + \frac{1}{2\pi T_c^* \tau_s} \right\}. \quad (5)$$

If the temperature variation is small ($\tau_s^{-1} \ll T_c$), (5) becomes

$$\frac{T_c - T_c^*}{T_c} = \frac{\pi}{4T_c} \text{Re}(\tau_s^{-1}). \quad (6)$$

The boundary conditions for the linearized Usadel equation are [25]

$$\left(\frac{\partial F_s}{\partial x} \right)_{\pm d_s/2} = \frac{\sigma_n}{\sigma_s} \left(\frac{\partial F_f}{\partial x} \right)_{\pm d_s/2},$$

$$F_s(d_s/2) = F_f(d_s/2) - \xi_n \gamma_B \left(\frac{\partial F_f}{\partial x} \right)_{d_s/2}, \quad (7)$$

$$F_s(-d_s/2) = F_f(-d_s/2) + \xi_n \gamma_B \left(\frac{\partial F_f}{\partial x} \right)_{-d_s/2} \quad (8)$$

with σ_n (σ_s) the conductivity of the F(S) layer, $\xi_n = \sqrt{\frac{D_f}{2\pi T_c}}$ and $\gamma_B = \frac{R_b \sigma_n}{\xi_n}$ is the interface transparency, related to the S/F resistance per unit area R_b . They lead to the determination of the pair-breaking parameter τ_s^{-1}

$$\tau_s^{-1} = -\frac{D_s \sigma_n}{d_s \sigma_s} \frac{F'_f(d_s/2)/F_f(d_s/2)}{1 - \xi_n \gamma_B F'_f(d_s/2)/F_f(d_s/2)}. \quad (9)$$

Next, the resolution of the Usadel equation in the F layers (2) with symmetry consideration gives rise to the expression of the anomalous Green's function in the F layer

$$F_f(x, \omega > 0) = A \cosh[k(x - d_s/2 - d_f/2)], \quad (10)$$

in the 0 phase and

$$F_f(x, \omega > 0) = B \sinh[k(x - d_s/2 - d_f/2)], \quad (11)$$

in the π phase. If $T_c < \tau_m^{-1}$, h , we may neglect the Matsubara frequencies in the expression for k that becomes

$$k = \frac{\sqrt{2}}{\xi_f} \sqrt{i + \alpha} = \frac{1}{\xi_{f1}} + i \frac{1}{\xi_{f2}}, \quad (12)$$

with $\xi_f = \sqrt{\frac{D_f}{h}}$ and $\alpha = \frac{1}{\tau_m h}$. The two parameters ξ_{f1} and ξ_{f2} are respectively the decay characteristic length and the oscillations period, and may be written as

$$\xi_{f1} = \frac{\xi_f}{\sqrt{\sqrt{1 + \alpha^2} + \alpha}}, \quad (13)$$

$$\xi_{f2} = \frac{\xi_f}{\sqrt{\sqrt{1 + \alpha^2} - \alpha}}. \quad (14)$$

For $\tau_m^{-1} = 0$, Eqs. (13) and (14) reduce to $\xi_{f1} = \xi_{f2} = \xi_f$. As expected, it is found that the decay length and oscillations period are the same in absence of spin-flip scattering.

The pair breaking parameter may be determined and it reads

$$\tau_{s,0}^{-1}(\omega > 0) = \tau_0^{-1} \frac{q \tanh(q\tilde{d}_f/2)}{1 + \tilde{\gamma}q \tanh(q\tilde{d}_f/2)}, \quad (15)$$

in the 0 phase and

$$\tau_{s,\pi}^{-1}(\omega > 0) = \tau_0^{-1} \frac{q \coth(q\tilde{d}_f/2)}{1 + \tilde{\gamma}q \coth(q\tilde{d}_f/2)}, \quad (16)$$

in the π phase, where $\tau_0^{-1} = \frac{D_s}{d_s} \frac{\sigma_n}{\sigma_s} \frac{1}{\xi_f}$, $\tilde{\gamma} = \frac{\xi_n}{\xi_f} \gamma_B$, $q = k\xi_f$ and $\tilde{d}_f = \frac{d_f}{\xi_f}$.

First, if the interface is supposed to be transparent, analytical expressions of the variation of the temperature may be found if $\frac{T_c - T_c^*}{T_c} \ll 1$:

$$\frac{4\tau_0}{\pi} (T_c - T_c^{*0}) = \frac{1}{2} \frac{a \sinh(a\tilde{d}_f) - b \sin(b\tilde{d}_f)}{\cosh^2(a\tilde{d}_f) \cos^2(b\tilde{d}_f) + \sin^2(b\tilde{d}_f) \sinh^2(a\tilde{d}_f)}, \quad (17)$$

$$(18)$$

$$\frac{4\tau_0}{\pi} (T_c - T_c^{*\pi}) = \frac{1}{2} \frac{a \sinh(a\tilde{d}_f) + b \sin(b\tilde{d}_f)}{\cosh^2(a\tilde{d}_f) \sin^2(b\tilde{d}_f) + \cos^2(b\tilde{d}_f) \sinh^2(a\tilde{d}_f)}, \quad (19)$$

where two dimensionless parameters have been introduced, namely $a = \frac{\xi_f}{\xi_{f1}} = \sqrt{\sqrt{1 + \alpha^2} + \alpha}$ and $b = \frac{\xi_f}{\xi_{f2}} = \sqrt{\sqrt{1 + \alpha^2} - \alpha}$, so that $q = a + ib$.

In the general case however a numerical analysis has to be performed.

The ratio of the characteristic lengths

$$\frac{\xi_{f1}}{\xi_{f2}} = \frac{\sqrt{\sqrt{1 + \alpha^2} - \alpha}}{\sqrt{\sqrt{1 + \alpha^2} + \alpha}}, \quad (20)$$

clearly shows that the magnetic scattering decreases the decay length and increases the oscillation period. If $\tau_m^{-1} \gg h$, ξ_{f1} can become much smaller than ξ_{f2} . Besides, the decrease of ξ_{f1} makes the observation of the oscillations more difficult.

The evolution of the critical temperature without and with spin-flip scattering is given in Fig. 2. The phase that really occurs is the one with higher critical temperature. It is seen that ξ_{f1} decreases in presence of spin-flip while ξ_{f2} increases.

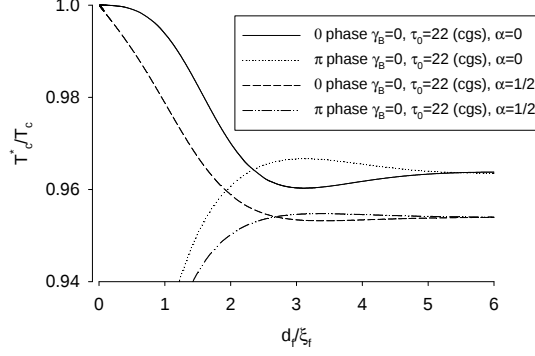


FIG. 2: Influence of the spin-flip scattering on the evolution of critical temperature as a function of the ferromagnetic layer thickness.

B. Influence of the interface transparency parameter γ_B on T_c^*

The influence of the interface transparency parameter γ_B on T_c^* of SF bilayers was studied before by Aarts *et al.* [26], Fominov *et al.* [27] and Tagirov [17]. Here we extend this discussion taking into account spin-flip scattering in the F-layer and considering broader range of interface transparencies and demonstrate that new effects take place in this situation.

The intriguing evolution of T_c^{*0} with the interface transparency parameter $\tilde{\gamma}$ must be underlined (see Fig. 3). If $\alpha = 0$, there is no magnetic scattering and it could intuitively be believed that, the higher the barrier, the less is the influence of the proximity effect on the S layer and therefore, $T_c^*(\tilde{\gamma} \gg 1) > T_c^*(\tilde{\gamma} \sim 1)$. However, it can be seen from Fig. 3 that the critical temperature is a decreasing function of the interface transparency parameter $\tilde{\gamma}$ for a small thickness of the F layer. This counter-intuitive behavior can be qualitatively understood for a S/F bilayer. The probability for a Cooper pair to leave the S layer is smaller for a low transparent interface ($\tilde{\gamma} \gg 1$). Nevertheless, the probability for this pair to come back again in the S layer is much higher for a transparent interface. Indeed, when the F layer is thin enough, the reflection of the Cooper pair at the other interface of the F layer allows the pair to cross again the first interface, which is easier when $\tilde{\gamma}$ is small. Consequently, the staying time in the F layer increases with the increase of the barrier, and when this time becomes higher than the coherence time of the Cooper pair, the pair is destroyed, leading to a weakened superconductivity. Therefore, the critical temperature decreases with the barrier in that case. On the other hand, if $\tilde{d}_f$ increases, the Cooper pair is hardly reflected by the external interface of the F layer whatever the value of $\tilde{\gamma}$ is and the

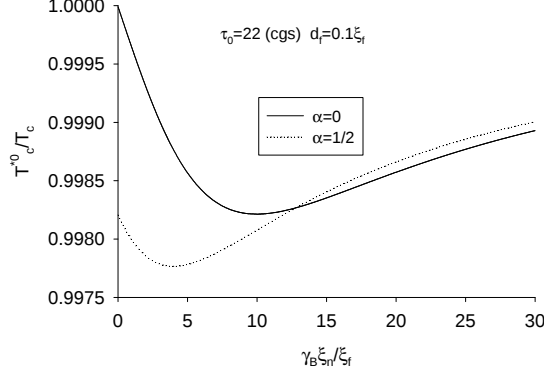


FIG. 3: Evolution of the critical temperature versus the interface transparency parameter for a S/F bilayer.

critical temperature is expected to increase with the barrier.

Besides, an analytical approach using formula (6) leads to the determination of the critical temperature when $\tilde{d}_f < 1$. In that case, the pair breaking parameter in the 0 phase becomes

$$\text{Re}(\tau_m^{-1}) = \tau_0^{-1} \frac{\tilde{\gamma} + \frac{\tilde{d}_f}{6}}{\left(\tilde{\gamma} + \frac{\tilde{d}_f}{6}\right)^2 + \left(\frac{1}{\tilde{d}_f}\right)^2}. \quad (21)$$

Two behaviors emerge whether $\tilde{\gamma}\tilde{d}_f \gg 1$ or not. Indeed, if $\tilde{\gamma} > \tilde{d}_f^{-1}$, the critical temperature evolution is described by

$$\left(\frac{T_c^*}{T_c}\right)_{\tilde{\gamma}\tilde{d}_f > 1} = 1 - \frac{\pi}{4T_c} \frac{\tau_0^{-1}}{\tilde{\gamma}}, \quad (22)$$

which is an increasing function of $\tilde{\gamma}$. On the contrary, if $\tilde{\gamma} < \tilde{d}_f^{-1}$, the critical temperature decreases when $\tilde{\gamma}$ increases, following

$$\left(\frac{T_c^*}{T_c}\right)_{\tilde{\gamma}\tilde{d}_f < 1} = 1 - \frac{\pi}{4T_c} \tilde{d}_f^2 \tau_0^{-1} \tilde{\gamma}. \quad (23)$$

The critical temperature evolution with $\tilde{\gamma}$ presented in Fig. 3 is therefore understood.

In presence of small magnetic scattering, the critical temperature evolution remains qualitatively the same. As shown in Fig. 3, it appears that superconductivity may be less destroyed when there is spin-flip scattering. In that case, the pair breaking parameter becomes

$$\text{Re}(\tau_m^{-1}) = \tau_0^{-1} \frac{\tilde{\gamma} + \frac{\alpha}{\tilde{d}_f} + \frac{\tilde{d}_f}{6}}{\left(\tilde{\gamma} + \frac{\alpha}{\tilde{d}_f} + \frac{\tilde{d}_f}{6}\right)^2 + \left(\frac{1}{\tilde{d}_f}\right)^2}. \quad (24)$$

The critical temperature is described by

$$\left(\frac{T_c^*}{T_c}\right)_{\tilde{\gamma}\tilde{d}_f > 1} = \left(\frac{T_c^*(\alpha = 0)}{T_c}\right)_{\tilde{\gamma}\tilde{d}_f > 1} + \frac{\pi}{4T_c} \frac{\tau_0^{-1}}{\tilde{\gamma}} \frac{\alpha}{\tilde{d}_f \tilde{\gamma}}, \quad (25)$$

when $\tilde{d}_f \tilde{\gamma} > 1$, and magnetic scattering leads to a slight enhancement of the transition temperature. On the contrary, if $\tilde{\gamma} \tilde{d}_f < 1$,

$$\left(\frac{T_c^*}{T_c}\right)_{\tilde{\gamma}\tilde{d}_f < 1} = \left(\frac{T_c^*(\alpha = 0)}{T_c}\right)_{\tilde{\gamma}\tilde{d}_f < 1} - \frac{\pi}{T_c} \tilde{d}_f \tau_0^{-1} \alpha, \quad (26)$$

and spin-flip implies the decrease of the transition temperature.

C. Influence of spin-orbit scattering and 'perpendicular' spin-flip

Let us now consider briefly the general case, with spin-orbit and/or perpendicular spin-flip scattering. An additional parameter has to be introduced, namely

$$\alpha_{\perp} = \frac{1}{h} \left(\frac{1}{\tau_x} - \frac{1}{\tau_{so}} \right), \quad (27)$$

and the parameter α now becomes

$$\alpha = \frac{1}{h} \left(\frac{1}{\tau_z} + \frac{2}{\tau_x} \right). \quad (28)$$

In that case, expressions (15) and (16) are modified. In the 0 phase, $q \tanh(q\tilde{d}_f)$ is replaced by

$$q \tanh(q\tilde{d}_f/2) + \beta \frac{q^* \tanh(q^* \tilde{d}_f/2) - q \tanh(q\tilde{d}_f/2)}{\beta + \frac{1 + \tilde{\gamma} q^* \tanh(q^* \tilde{d}_f/2)}{1 + \tilde{\gamma} q \tanh(q\tilde{d}_f/2)}}, \quad (29)$$

where q becomes

$$q^2 = 2 \left(\frac{\omega}{h} + \alpha - \alpha_{\perp} + i \sqrt{1 - \alpha_{\perp}^2} \right), \quad (30)$$

and β is

$$\beta = -\alpha_{\perp} \frac{\alpha_{\perp} - i \sqrt{1 - \alpha_{\perp}^2}}{1 + \sqrt{1 - \alpha_{\perp}^2}}. \quad (31)$$

In the π phase, $q \coth(q\tilde{d}_f)$ is replaced by

$$q \coth(q\tilde{d}_f/2) + \beta \frac{q^* \coth(q^* \tilde{d}_f/2) - q \coth(q\tilde{d}_f/2)}{\beta + \frac{1 + \tilde{\gamma} q^* \coth(q^* \tilde{d}_f/2)}{1 + \tilde{\gamma} q \coth(q\tilde{d}_f/2)}}. \quad (32)$$

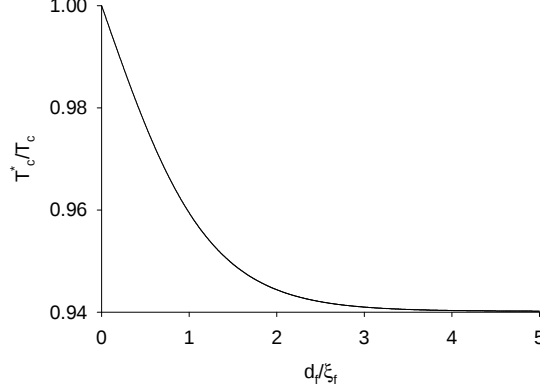


FIG. 4: Monotonic evolution of the critical temperature for an transparent interface, and for $\tau_0 = 22$ (cgs), $\alpha = 1$ and $\alpha_\perp = -3/2$.

Therefore, the influence of 'perpendicular' spin-flip scattering and spin-orbit scattering is quite similar to the influence of 'parallel' spin-flip processes, in the sense that it also implies the decrease of the decaying length and the increase of the oscillations period. However, a special situation arises when $\alpha_\perp > 1$. Then, the oscillations of the Cooper pair wave function are completely destroyed. Similar conclusion for spin-orbit mechanism was obtained in [15]. In fact, the influence of the 'perpendicular' magnetic scattering is analogous to the spin-orbit scattering (see Fig. 4). Probably the role of 'perpendicular' spin-flip or spin-orbit scattering is important for the understanding of experimental results where no oscillation of the critical temperature was detected. Besides, note that the critical temperature oscillations can not disappear when there is only 'parallel' spin-flip.

IV. BEHAVIOR OF THE CRITICAL CURRENT I_c

A Josephson junction may be realized with S/F/S sandwiches in which the weak link between the two superconductors is ensured by the ferromagnetic layer. The supercurrent $J_s(\varphi)$ flowing across the structure can be expressed as $J_s(\varphi) = I_c \sin(\varphi)$, where I_c is the critical current and φ stands for the phase difference between the two superconducting layers. A standard junction has at equilibrium $I_c > 0$ and $\varphi = 0$, and therefore, no current exists. It may appear however that I_c becomes negative, which implies that the equilibrium phase difference is $\varphi = \pi$ and the ground state undergoes a π phase shift. This so called ' π junction' was first predicted for S/F/S structures in the clean limit [28], and later in the more realistic

case of the diffusive limit [29]. The critical current I_c in S/F/S junctions is controlled by the exchange field in the ferromagnet, the interface transparency parameter γ_B , the spin-flip and spin-orbit scattering rates. In this section we will discuss the influence of these parameters on I_c , paying the main attention to the role of spin-orbit and magnetic scatterings. Besides, note that the spin-orbit effect on the critical current has already been studied for S/F bilayers separated by an insulator with thin F layers [30] and for the FSFSF structure with noncollinear magnetizations of F-layers [31]. We will consider a symmetric S/F/S structure with the F layer having thickness d_f and assume that the dirty limit conditions are fulfilled for S and F materials. We will assume that the rigid boundary condition $\gamma_B \gg \min\{\sigma_n \xi_S / \sigma_s \xi_n, 1\}$ is fulfilled, when the suppression of superconductivity in S can be neglected and the linearized Usadel equations (2) can be used. The case of transparent interfaces, $\gamma_B = 0$, will be considered at the end.

A. General expression for I_c

To derive the general expression for I_c we should supplement (2) by the boundary conditions [25] at S/F interfaces ($x = \pm d_f$)

$$\gamma_B \xi_n \frac{\partial}{\partial x} F_{\pm f}(\pm d_f) = \pm G_S \left[\frac{\Delta(\pm d_f)}{\omega} - F_{\pm f}(\pm d_f) \right] \text{sign}(\omega), \quad (33)$$

$$G_S = \frac{\omega}{\sqrt{\omega^2 + |\Delta|^2}}, \quad \Delta(\pm d_f) = |\Delta| \exp \{ \pm i\varphi/2 \}.$$

The solution of the boundary problem (2), (33) has the form

$$F_{+f} = \frac{1}{2}((1+\eta_\omega) \{A_{\omega+} \cosh[k_+x] + B_{\omega+} \sinh[k_+x]\} + (1-\eta_\omega) \{A_{\omega-} \cosh[k_-x] + B_{\omega-} \sinh[k_-x]\}), \quad (34)$$

$$F_{-f} = \frac{1}{2}((1-\eta_\omega) \{A_{\omega+} \cosh[k_+x] + B_{\omega+} \sinh[k_+x]\} - (1+\eta_\omega) \{A_{\omega-} \cosh[k_-x] + B_{\omega-} \sinh[k_-x]\}), \quad (35)$$

where the coefficients $A_{\omega\pm}$ and are given $B_{\omega\pm}$ in the Appendix, while

$$\eta_\omega = \frac{\alpha_{so} + \sqrt{\alpha_{so}^2 - 1}}{i\hbar \text{sign}(\omega)}, \quad k_\pm = \frac{\sqrt{2}}{\xi_f} \sqrt{|\tilde{\omega}| + \alpha_{so} + \alpha \pm \sqrt{\alpha_{so}^2 - 1}}. \quad (36)$$

The parameter α_{so} is defined by $\alpha_{so} = 1/(h\tau_{so})$, $\alpha = 1/(h\tau_m)$ and $\tilde{\omega} = \omega/h$. Note that in the general case 'perpendicular' spin-flip has to be added in α_{so} and α . The general expression for the supercurrent is

$$J_S = \frac{i\pi T \sigma_n}{4e} \sum_{\omega=-\infty, \sigma=\pm}^{\infty} \left[\tilde{F}_{\sigma f} \frac{\partial}{\partial x} F_{\sigma f} - F_{\sigma f} \frac{\partial}{\partial x} \tilde{F}_{\sigma f} \right], \quad (37)$$

where $\tilde{F}_{\pm f}(x, \omega) = F_{\pm f}^*(x, -\omega)$. Substituting (34) and (35) into the above expression and taking into account the symmetry relations (given in the Appendix), we get $J_S = I_c \sin \varphi$.

For large spin-orbit scattering, i. e. $\tau_{so}^{-1} \geq h$, the critical current I_c equals to

$$\frac{e\xi_n I_c}{2\pi T_c \sigma_n} = \frac{T}{T_c} \sum_{\omega=0}^{\infty} \frac{\Delta^2 G_S^2}{\omega^2 (1 + \eta_{\omega}^2)} (\kappa_+ + \eta_{\omega}^2 \kappa_-), \quad (38)$$

where

$$\kappa_{\pm} = \frac{\xi_n k_{\pm}}{(\gamma_B^2 \xi_n^2 k_{\pm}^2 + G_S^2) \sinh[k_{\pm} d_f] + 2G_S \gamma_B \xi_n k_{\pm} \cosh[k_{\pm} d_f]}. \quad (39)$$

At larger exchange field $h \geq \tau_{so}^{-1}$, the critical current becomes

$$\frac{eI_c}{2\pi T_c \sigma_n} = \frac{T}{\xi_f T_c} \sum_{\omega=0}^{\infty} \frac{\Delta^2 G_S^2}{\omega^2} \operatorname{Re} \left\{ \frac{(a + ib) \left[1 + i \frac{2}{\sqrt{\alpha_{so}^{-2} - 1}} \right]}{((\gamma_B \xi_n k)^2 + G_S^2) \sinh[k d_f] + 2G_S \gamma_B \xi_n k \cosh[k d_f]} \right\}, \quad (40)$$

where $k = q/\xi_f$ and $q = a + ib$, with

$$a = \sqrt{|\tilde{\omega}| + \alpha_{so} + \alpha + \sqrt{(|\tilde{\omega}| + \alpha)^2 + 2(|\tilde{\omega}| + \alpha)\alpha_{so} + 1}}, \quad (41)$$

$$b = \sqrt{\frac{1 - \alpha_{so}^2}{|\tilde{\omega}| + \alpha_{so} + \alpha + \sqrt{(|\tilde{\omega}| + \alpha)^2 + 2(|\tilde{\omega}| + \alpha)\alpha_{so} + 1}}}. \quad (42)$$

In appropriate limits, expressions (38),(40) transform into the previously obtained results [1], [15], [25],[24],[32]. This approach is valid if $F_{\omega\pm} \ll 1$ or

$$\gamma_B \gg \gamma, \quad \frac{a}{a^2 + b^2} \frac{\Delta}{\pi T_c} \frac{1}{\min\{1, d_f/\xi_n\}}. \quad (43)$$

As follows from (40) - (42), in the case of strong spin-orbit scattering $\tau_{so}^{-1} \geq h$, the critical current decays monotonically with the increase of d_f with two decay lengths $k_{\pm}^{-1}$ defined by Eq.(36). It is seen from (36) that in the limit $h \rightarrow 0$, the parameter $\eta_{\omega} \rightarrow \infty$. As a result, the

contribution to the critical current in (38) comes only from κ_- component with the length scale k_-^{-1} which describes the case of an S/N/S junction in which spin-orbit scattering does not influence I_c . With the increase of h , the contribution to I_c from the faster decaying κ_+ component ($k_+ > k_-$) also increases and the difference between k_+ and k_- decreases. Finally, when $h = \tau_{so}^{-1}$, both scales coincide, $k_+ = k_-$, and the components κ_+, κ_- provide equal contributions to I_c .

For relatively weak spin-orbit scattering, $\tau_{so}^{-1} \leq h$, the dependence $I_c(d_f)$ follows the damped oscillation law, when two length scales ξ_{f1}, ξ_{f2} can be introduced describing respectively the decay and the oscillation period of $I_c(d_f)$. In this section, we will concentrate on the case $\tau_{so}^{-1} \leq h$. The scales ξ_{f1}, ξ_{f2} are related to a, b and will be discussed in detail below in different limits.

1. Limit of small F layer thickness and large γ_B .

In the limit of small thickness $d_f \ll \xi_{f1}$, and large interface transparency parameter $\gamma_B \gg d_f/\xi_n, (\pi T_c G_S \xi_n)/(d_f(\omega + \tau_m^{-1} + \tau_{so}^{-1}))$ we can neglect the terms G_S^2 and $G_S \gamma_B \xi_n k(k d_f)^2$ in the denominator of Eq.(40) and with the accuracy of better than $(d_f/\xi_{f1})^3$ get

$$\frac{e R_N I_c}{4 \pi T_c} = \frac{T}{\tilde{\gamma} d_f T_c} \xi_f \sum_{\omega=0}^{\infty} \frac{\Delta^2 G_S^2}{\omega^2} \left\{ \frac{\Omega_1 + 2\alpha_{so} + (\Omega^2 - v^2 + 4\alpha_{so}\Omega) \frac{d_f^2}{6\xi_f^2}}{\Omega_1^2 + v^2 + \frac{d_f^2}{3\xi_f^2} \Omega(\Omega^2 + v^2)} \right\}, \quad (44)$$

where $R_N = 2R_B$ is the normal junction resistance, $\tilde{\gamma} = \gamma_B \xi_n / \xi_f$, $\tilde{\omega} = \omega/h$ and

$$\Omega = \tilde{\omega} + \alpha_{so} + \alpha, \quad v^2 = 1 - \alpha_{so}^2, \quad \Omega_1 = \Omega + 2G_S \frac{\pi T_c \xi_n}{\gamma_B h d_f}.$$

If additionally

$$\gamma_B \gg \frac{6\xi_n^3 \pi T_c}{d_f^3 [(\pi T_c/h + \alpha_{so} + \alpha)^2 + 1 - \alpha_{so}^2]} h$$

then

$$\frac{e R_N I_c}{4 \pi T_c} = \frac{\xi_f}{\tilde{\gamma} d_f} \left\{ \frac{T}{T_c} \sum_{\omega=0}^{\infty} \frac{\Delta^2}{\omega^2 + \Delta^2} \frac{\Omega + 2\alpha_{so}}{(\Omega^2 + v^2)} - \frac{d_f^2}{6\xi_f^2} \frac{\Delta}{2T_c} \tanh \frac{\Delta}{2T} \right\}. \quad (45)$$

For $h \gg \pi T_c, \tau_m^{-1}, \tau_{so}^{-1}$ and $T \ll T_c$, the sum in (45) can be calculated by transforming from summation into integration over ω resulting in

$$\frac{e R_N I_c}{4 \pi T_c} = \frac{\Delta}{2T_c} \frac{\xi_f}{\tilde{\gamma} d_f} \left[\frac{2\Delta}{h\pi} \ln \frac{h}{\Delta} + \frac{3}{h\tau_{so}} + \frac{1}{h\tau_m} - \frac{d_f^2}{6\xi_f^2} \right], \quad (46)$$

From (46) it follows that the transformation from 0 to π junction may occur when the thickness d_f exceeds some critical value d_π

$$d_f \gtrsim d_\pi, \quad d_\pi = \sqrt{6}\xi_f \sqrt{\frac{2\Delta}{\pi h} \ln \frac{h}{\Delta} + \frac{3}{h\tau_{so}} + \frac{1}{h\tau_m}}. \quad (47)$$

For $\tau_{so}^{-1}, \tau_m^{-1} \ll h$ this result agrees with [32]. It is interesting to note that in this range of parameters, the condition (47) of the transition to π state does not depend on the properties of the interfaces. As is also seen from Eq. (47), both spin-orbit and spin-flip scattering increase the thickness d_π corresponding to the first 0 to π transition.

If $\tilde{\gamma}d_f/\xi_f \lesssim 1$, then the term $G_S\xi_f/(\tilde{\gamma}d_f)$ in (44) is not small. As a result, the transition to a π state should depend on the properties of interfaces and occurs at h larger than the critical value $h_\pi \propto \pi T_c(\xi_n/d_f)$ following from Eq.(46).

Therefore, in the limit of small $d_f \ll \xi_{f1}$ and large $\gamma_B \gg 1$ the transition from 0 to π junction exists only if the exchange energy $h \gtrsim h_\pi \propto \pi T_c(\xi_n/d_f)$ sufficiently exceeds πT_c . The smaller the interface transparency parameter γ_B , the larger should be the exchange energy h . The possibility of the 0- π transition in junctions with small thickness d_f in the case of large γ_B is related to the multiple scattering at the boundaries. As a result, the electrons spend more time in the F layer and its influence on superconductivity is enhanced. This is the manifestation of the same mechanism that leads in S/F bilayers to the critical temperature decrease with the increase of the interface transparency parameter (see section II B).

2. Limit of large F layer thickness.

In the limit of large $d_f \gg \xi_{f1}$ for the critical current from (40) - (42), we have

$$\frac{eI_c}{2\pi T_c \sigma_n} = \frac{2T}{\xi_f T_c} \sum_{\omega=0}^{\infty} \frac{\Delta^2 G_S^2}{\omega^2} \frac{u \sin(bd_f/\xi_f) + v \cos(bd_f/\xi_f)}{((G_S + a\tilde{\gamma})^2 + \tilde{\gamma}^2 b^2)^2} \exp\left\{-a\frac{d_f}{\xi_f}\right\}, \quad (48)$$

where the coefficients u and v are defined by

$$\begin{aligned} u &= b(G_S^2 - (a^2 + b^2)\tilde{\gamma}^2) + \frac{2}{\sqrt{\alpha_{so}^{-2} - 1}} G_S^2 (a + \tilde{\gamma}(a^2 + b^2)(2G_S + a\tilde{\gamma})), \\ v &= G_S^2 a + \tilde{\gamma}(a^2 + b^2)(2G_S + a\tilde{\gamma}) - \frac{2}{\sqrt{\alpha_{so}^{-2} - 1}} b(G_S^2 - (a^2 + b^2)\tilde{\gamma}^2). \end{aligned} \quad (49)$$

If additionally $\min\{h, \tau_{so}^{-1}, \tau_m^{-1}\} \gg \pi T_c$, then both a and b may be considered as independent on Matsubara frequencies, since the sum in (40) converges at $\omega \approx \pi T_c$. In this case

$$\frac{e\xi_f I_c}{2\pi T_c \sigma_n} = \left[\Sigma_1 \sin \frac{d_f}{\xi_{f2}} + \Sigma_2 \cos \frac{d_f}{\xi_{f2}} \right] \exp \left\{ -\frac{d_f}{\xi_{f1}} \right\}, \quad (50)$$

where

$$\Sigma_1 = \frac{2T}{T_c} \sum_{\omega=0}^{\infty} \frac{\Delta^2 G_S^2}{\omega^2} \frac{u}{((G_S + a\tilde{\gamma})^2 + b^2\tilde{\gamma}^2)^2}, \quad (51)$$

$$\Sigma_2 = \frac{2T}{T_c} \sum_{\omega=0}^{\infty} \frac{\Delta^2 G_S^2}{\omega^2} \frac{v}{((G_S + a\tilde{\gamma})^2 + b^2\tilde{\gamma}^2)^2}. \quad (52)$$

The two characteristic length scales are given by the following expressions

$$\xi_{f1} = \xi_f \sqrt{\frac{1}{\alpha + \alpha_{so} + \sqrt{\alpha^2 + 2\alpha\alpha_{so} + 1}}}, \quad (53)$$

$$\xi_{f2} = \xi_f \sqrt{\frac{\alpha + \alpha_{so} + \sqrt{\alpha^2 + 2\alpha\alpha_{so} + 1}}{1 - \alpha_{so}^2}}, \quad (54)$$

which generalize Eqs. (13) and (14) for the case of the presence of the spin-orbit scattering in a ferromagnet. One can see that with the increase of both scattering rates τ_m^{-1} and τ_{so}^{-1} the decay length ξ_{f1} decreases, while the oscillation period ξ_{f2} increases.

For a weak exchange field $h \ll \pi T_c$ and sufficiently high temperatures $\pi T \gg \{\tau_{so}^{-1}, \tau_m^{-1}, h\}$, with $h > \tau_{so}^{-1}$, only the first term with $n = 0$ in (40) is important and we have

$$\frac{e\xi_f I_c}{2\pi T_c \sigma_n} = \frac{2\Delta^2 G_0}{\pi^2 T T_c} \frac{\Sigma_1 \sin(d_f/\xi_{f2}) + \Sigma_2 \cos(d_f/\xi_{f2})}{((G_0 + a_0\tilde{\gamma})^2 + b_0^2\tilde{\gamma}^2)^2} \exp \left\{ -\frac{d_f}{\xi_{f1}} \right\}. \quad (55)$$

where $G_0 = \pi T / \sqrt{(\pi T)^2 + \Delta^2}$ and Σ_1 and Σ_2 become

$$\Sigma_1 = \frac{2T}{T_c} \frac{\Delta^2 G_0^2}{(\pi T)^2} \frac{u_0}{((G_0 + a_0\tilde{\gamma})^2 + b_0^2\tilde{\gamma}^2)^2}, \quad (56)$$

$$\Sigma_2 = \frac{2T}{T_c} \frac{\Delta^2 G_0^2}{(\pi T)^2} \frac{v_0}{((G_0 + a_0\tilde{\gamma})^2 + b_0^2\tilde{\gamma}^2)^2}. \quad (57)$$

The parameters a_0, b_0, u_0, v_0 are obtained replacing ω by πT in expressions (41), (42), (49).

The two characteristic lengths may be written in that case as

$$\xi_{f1} = \xi_f \sqrt{\frac{1}{\pi T/h + \alpha + \alpha_{so} + \sqrt{(\pi T/h + \alpha)^2 + 2(\pi T + \alpha)\alpha_{so} + 1}}}, \quad (58)$$

$$\xi_{f2} = \xi_f \sqrt{\frac{\pi T/h + \alpha + \alpha_{so} + \sqrt{(\pi T/h + \alpha)^2 + 2(\pi T + \alpha)\alpha_{so} + 1}}{1 - \alpha_{so}^2}}. \quad (59)$$

For $\tau_{so}^{-1}, \tau_m^{-1} = 0$, Eqs.(58), (59) reduce to a simple expression $\xi_{f1,2}^{-1} = \xi_n^{-1}[(h^2/(\pi T_c)^2 + (T/T_c)^2)^{1/2} \pm (T/T_c)]^{1/2}$ [4] which describes the temperature variations of both length scales. More precisely, in the considered limits, $\xi_{f1}^{-1} \sim \xi_n^{-1} \sqrt{2T/T_c}$, while $\xi_{f2}^{-1} \sim \xi_{f1}^{-1} h/(2\pi \sqrt{TT_c}) \ll \xi_{f1}^{-1}$. One can see that the scattering rates $\tau_{so}^{-1}, \tau_m^{-1}$ make the T variation of $\xi_{f1,2}$ weaker.

From (50), (55), one can derive the condition for $I_c = 0$ and obtain

$$d_{fn} = d_f, \quad \frac{d_{fn}}{\xi_{f2}} = \pi n - \arctan\left(\frac{\Sigma_2}{\Sigma_1}\right), \quad n = 0, 1, 2, \dots \quad (60)$$

when the transitions between 0- and π -states occur. The position of the first zero, d_{f1} , depends both on the material parameters of the ferromagnetic layer and the properties of the interfaces and superconducting electrodes, while the distance between the zeros is the function only of ξ_{f2} and therefore depends only on the transport parameters of the ferromagnetic material.

From the structure of coefficients u and v (see Eq.(49) and (60)), it follows that in the limit of small γ_B ($F_{\pm f} = \frac{\Delta}{\sqrt{\omega^2 + \Delta^2}} \exp(\pm i\varphi/2)$ at S/F interfaces) and $\min\{h, \tau_{so}^{-1}, \tau_m^{-1}\} \gg \pi T_c$

$$\frac{d_{fk}}{\xi_{f1}} = \pi k - \arctan\left(\frac{2b - a\sqrt{\alpha_{so}^{-2} - 1}}{2a + b\sqrt{\alpha_{so}^{-2} - 1}}\right), \quad k = 1, 2, \dots \quad (61)$$

In particular, it follows from (61) that for small spin-orbit and spin-flip scatterings $h \gg \tau_{so}^{-1}, \tau_m^{-1}$,

$$\frac{d_{fk}}{\xi_{f1}} \approx \pi k - \frac{\pi}{4}, \quad (62)$$

and the well known result $d_{f1} \approx (3\pi/4)\xi_{f2}$ for the first critical thickness for 0 to π state is reproduced. This d_{f1} value approximately satisfies the condition of validity of the large d_f approximation considered in this section.

It follows from (61) that the critical thickness d_{f1} increases with τ_m^{-1} and τ_{so}^{-1} (see also numerical results below).

An increase of γ_B results in the suppression of the magnitude of $F_{\pm f}(\pm d_f) \sim \Delta(1 + \gamma_B)^{-1}$ near the S/F interfaces, which leads to the decrease of d_{f1} . Formally it is due to the fact that with an increase of γ_B , the coefficient b in (49) and, hence, Σ_1 , may change its sign resulting in the existence of the solution d_{f0} of (60) for $n = 0$. This solution corresponds

to the thickness range in which simple large d_f approximation (48) is no valid anymore. This fact is in the full agreement with our consideration performed for the limit of small d_f . Namely, it follows from (47) that at large γ_B and h we have

$$d_{f1} = \sqrt{6\xi_f \sqrt{\frac{2\Delta}{\pi h} \ln \frac{h}{\Delta} + \alpha + 3\alpha_{so}}} \ll \xi_{f1}. \quad (63)$$

Note that in actual experimental situations, when the approximation $d_f \gg \xi_{f1}$ is not fulfilled, simple expressions (50), (55), (53), (58), (54),(59) are not valid and to analyze the data it is convenient to introduce the effective decay length ξ_{f1}^{eff}

$$\xi_{f1}^{eff} = \frac{1}{d_{m1} - d_{m2}} \ln \frac{I_{cm1}}{I_{cm2}}, \quad (64)$$

where $d_{m1,2}$ are the thicknesses at which the first (I_{cm2}) and second (I_{cm2}) maxima of $I_c(d_f)$ occur.

Below we will focus on the influence of γ_B , τ_{so}^{-1} , and τ_m^{-1} on the critical current.

B. Influence of interface transparency parameter γ_B on I_c

Consider first the simplest case of vanishing τ_{so}^{-1} , τ_m^{-1} . In this limit, we immediately deduce from (40)-(42) that

$$\frac{e\xi_f I_c}{2\pi T_c \sigma_n} = \frac{T}{T_c} \sum_{\omega=0}^{\infty} \frac{\Delta^2 G_S^2}{\omega^2} \text{Re} \left\{ \frac{a + ib}{((\gamma_B \xi_n k)^2 + G_S^2) \sinh[kd_f] + 2G_S \gamma_B \xi_n k \cosh[kd_f]} \right\}, \quad (65)$$

where the coefficients a and b become

$$a = \sqrt{|\tilde{\omega}|} + \sqrt{|\tilde{\omega}|^2 + 1}, \quad (66)$$

$$b = \sqrt{|\tilde{\omega}|} - \sqrt{|\tilde{\omega}|^2 + 1}. \quad (67)$$

The dependence of the critical current as a function of the F layer thickness calculated from (65) for $T = 0.5T_c$, and $h = 3\pi T_c$ for different values of the interface transparency parameter γ_B is presented in Fig. 5. Note that for small γ_B Eq.(65) is formally not applicable, since it was derived under the condition (43) of sufficiently large γ_B . Therefore, for $\gamma_B = 0$, $\gamma_B = 1$ and $\gamma_B = 5$ we have added for comparison the corresponding curves calculated numerically by direct solution of the Usadel equations for arbitrary γ_B , which show that Eq.(65) provides

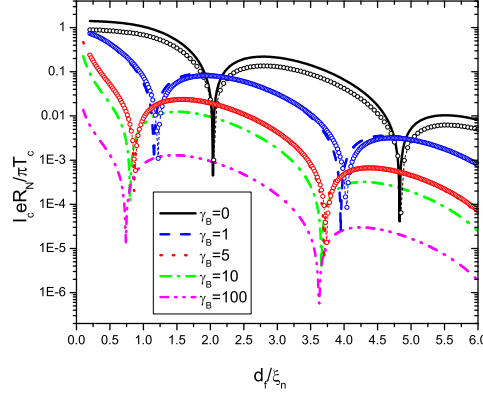


FIG. 5: (Color on line) Influence of the interface transparency parameter γ_B on the thickness dependence of the critical current in S/F/S junction for $\alpha = \alpha_{so} = 0$, $h = 3\pi T_c$ and $\frac{T}{T_c} = 0.5$. Open circles: the results of exact numerical calculations for $\gamma_B = 0$, $\gamma_B = 1$ and $\gamma_B = 5$ (from top to bottom).

reasonable approximation even in the small γ_B range. It is clearly seen from Fig. 5 that with an increase of γ_B , the position of the first zero d_{f1} is shifted into the region $d_f < \xi_{f1}$. As discussed above, the increase of γ_B results in the suppression of $F_{\pm f}(\pm d_f)$ in the F layer, such that $ReF_{\pm f}(x)$ changes sign in the F layer center at smaller d_f .

The results plotted in Fig. 5 make it possible to estimate the upper limit for the $I_c R_N$ product of the SFS junction in a π -state. This upper limit can be achieved in the case of highly transparent interfaces ($\gamma_B = 0$) and in the absence of spin-flip and spin-orbit scattering. As follows from Fig. 5, $I_c R_N^{max} \approx 0.1\pi T_c$ that provides $I_c R_N^{max} \approx 250\mu V$ in the case of Nb electrodes ($T_c = 9K$).

At large F layer thickness, $I_c(d_f)$ is determined by Eqs.(50), (55). If spin-flip and spin-orbit scattering are negligible, the ratio $\xi_{f1}/\xi_{f2} = h/(T + \sqrt{(\pi T)^2 + \hbar^2})$ follows from (58), (59) and depends only on h and T . For typical ferromagnets $h \gtrsim \pi T_c$ and ξ_{f1} approximately equals to ξ_{f2} . However, if the spin-flip scattering and spin-orbit rates become relatively large $\tau_m^{-1}, \tau_{so}^{-1} \gtrsim h$, the situation may change drastically. Consider first the influence of spin-flip scattering on I_c .

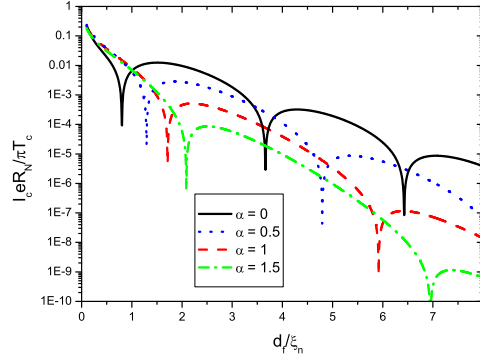


FIG. 6: (Color on line) Influence of the spin-flip scattering parameter α on the thickness dependence of the critical current in S/F/S junction for $\alpha_{so} = 0$, $h = 3\pi T_c$, $\gamma_B = 10$, and $\frac{T}{T_c} = 0.5$.

C. Influence of spin-flip scattering on I_c

If spin-flip scattering is not negligible, then the ratio of the characteristic lengths in the decaying solution (50), (55) becomes

$$\frac{\xi_{f1}}{\xi_{f2}} = \frac{1}{\pi T/h + \alpha + \sqrt{(\pi T/h + \alpha)^2 + 1}}, \quad (68)$$

and for strong spin-flip scattering $\tau_m^{-1} \gtrsim h$ the decay length ξ_{f1} may become much smaller than the oscillation period ξ_{f2} . This results in the much stronger decrease of I_c versus d_f in S/F/S junctions.

The evolution of I_c for different values of τ_m^{-1} calculated from (40) for $T = 0.5T_c$, $h = 3\pi T_c$ and $\gamma_B = 10$ is given in Fig. 6.

One can see that with increasing α , the critical thickness d_{f1} of the first $0 - \pi$ crossover shifts to larger values of d_f .

D. Influence of spin-orbit scattering on I_c

If spin-orbit scattering is not negligible, then the ratio of the characteristic lengths in the decaying solution (50), (55) becomes

$$\frac{\xi_{f1}}{\xi_{f2}} = \frac{\sqrt{1 - \alpha_{so}^2}}{(|\tilde{\omega}| + \alpha_{so} + \sqrt{\tilde{\omega}^2 + 2|\tilde{\omega}|\alpha_{so} + 1})}. \quad (69)$$

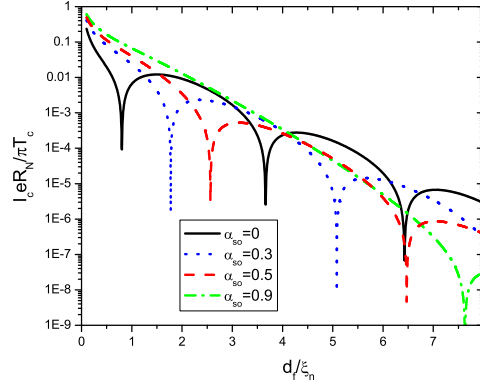


FIG. 7: (Color on line) Influence of the spin-orbit scattering on the thickness dependence of the critical current in S/F/S junction for $\alpha = 0$, $h = 3\pi T_c$, $\gamma_B = 10$, and $\frac{T}{T_c} = 0.5$.

Eq.(69) shows that the difference between the decaying ξ_{f1} and the oscillating length ξ_{f2} increases with τ_{so}^{-1} even faster than for the case of spin-flip scattering. Moreover, the transition to monotonically decaying solution takes place at $\tau_{so}^{-1} \rightarrow h$ and $\xi_{f2} \rightarrow \infty$.

The dependence of critical current on d_f calculated from (40) for $T = 0.5T_c$, $h = 3\pi T_c$ and $\gamma_B = 10$ is shown in Fig. 7. One can see that the oscillation period increases strongly with increasing α_{so} and diverges when $\alpha_{so} = 1$. At the same time, d_{f1} shifts to larger values of d_f .

V. CRITICAL CURRENT OF LONG JUNCTIONS WITH TRANSPARENT INTERFACES AT ARBITRARY TEMPERATURES.

Let us now consider a S/F bilayer with a transparent interface. The complete nonlinear Usadel equation in the F layer has to be employed. For the easy axis of the ferromagnet and using the usual parametrization of the normal and anomalous functions $G_f = \cos \theta_f$ and $F_f = \sin \theta_f$, it may be written in the absence of spin-orbit scattering as

$$\xi_n^2 \frac{\partial^2}{\partial x^2} \theta_f - \left(\frac{|\omega| + i h \text{sign}(\omega)}{\pi T_c} + \frac{\cos \theta_f}{\pi T_c \tau_m} \right) \sin \theta_f = 0, \quad (70)$$

Note that Eq.(70) transforms into (2) in the limit of small $\theta_f \ll 1$.

For S/F/S junctions, this equation may be used and an analytical solution found if $d_f \gg \xi_{f1}$. In that case, the decay of the Cooper pairs wave function in first approximation

occurs independently near each interface [1]. It can therefore be treated separately enough to consider the behavior of the anomalous Green's function near each S/F interface, assuming that the F layer thickness is infinite.

For one interface ($x = -d_f/2$), a first integral of (70) leads to

$$\xi_n \frac{d}{dx} \frac{\theta_f}{2} = \sqrt{\frac{|\omega| + i\hbar \text{sign}(\omega)}{\pi T_c}} \sin \frac{\theta_f}{2} \sqrt{\left[1 + \frac{1}{\tau_m (|\omega| + i\hbar \text{sign}(\omega))} \cos^2 \frac{\theta_f}{2}\right]}, \quad (71)$$

where the boundary conditions $\theta_f(x \rightarrow \infty) = 0$ has been used. Further integration in (71) gives [33]

$$\frac{\sqrt{\left[1 - \varepsilon^2 \sin^2 \frac{\theta_f}{2}\right]} - \cos \frac{\theta_f}{2}}{\sqrt{\left[1 - \varepsilon^2 \sin^2 \frac{\theta_f}{2}\right]} + \cos \frac{\theta_f}{2}} = g_0 \exp \left\{ -2q \frac{(d_f/2 + x)}{\xi_f} \right\} \quad (72)$$

where $k = \sqrt{2}/\xi_f \sqrt{(|\tilde{\omega}| + i\text{sign}(\omega) + \alpha)} = q/\xi_f$, and $\varepsilon^2 = \alpha / (|\tilde{\omega}| + i\text{sign}(\omega) + \alpha)$.

The integration constant g_0 in (72) should be determined from the boundary conditions at S/F interfaces. For simplicity we will assume that the rigid boundary conditions are valid at $x = -d_f/2$, then

$$\theta_f(-d_f/2) = \arctan \frac{|\Delta|}{\omega} \quad (73)$$

and from (72), (73) we finally get

$$g_0 = \frac{(1 - \varepsilon^2) \mathcal{F}(n)}{\left[\sqrt{(1 - \varepsilon^2) \mathcal{F}(n) + 1} + 1 \right]^2},$$

and

$$\mathcal{F}(n) = \frac{(\Delta / (2\pi T))^2}{\left[n + 1/2 + \sqrt{(n + 1/2)^2 + (\Delta / (2\pi T))^2} \right]^2} = \frac{|\Delta|^2}{(\omega + \Omega)^2},$$

where $\Omega = \sqrt{\omega^2 + |\Delta|^2}$. Next, F_f may be determined.

The anomalous Green's function at the center of the F layer in the S/F/S junction may be taken as the superposition of the two decaying functions [34] taking into account the phase difference in each superconducting electrode,

$$\theta_f = \frac{4}{\sqrt{1 - \varepsilon^2}} \sqrt{g_0} \left(\exp \left\{ -q \frac{(d_f/2 + x)}{\xi_f} - i \frac{\varphi}{2} \right\} + \exp \left\{ q \frac{(x - d_f/2)}{\xi_f} + i \frac{\varphi}{2} \right\} \right) \quad (74)$$

As a result, the current-phase relation is sinusoidal and the critical current becomes

$$I_c R_N = 64\pi \frac{d_f T}{\xi_f e} \text{Re} \left(\sum_0^\infty \frac{\mathcal{F}(n) q}{\left[\sqrt{(1 - \varepsilon^2) \mathcal{F}(n) + 1} + 1 \right]^2} \exp(-q \frac{d_f}{\xi_f}) \right). \quad (75)$$

The critical current is proportional to the small factor $\exp(-qd_f/\xi_n)$. The terms neglected in our approach are much smaller and are of the order of $\exp(-2qd_f/\xi_n)$. Therefore, they give a tiny second harmonic term in the current-phase relation.

It should be underlined that this expression coincides with the one previously obtained in [29] in the limit $\tau_m^{-1} \rightarrow 0$ (no magnetic scattering) and for $T_c \ll h$.

In addition, note that in the limit of vanishing magnetic scattering, the temperature dependence of the critical thickness d_{fk} of F layer when $I_c = 0$ may appear only through the variation of k with ω (where $k \sim \sqrt{2(|\tilde{\omega}| + i\text{sign}(\omega))}/\xi_f$ in this case). As the characteristic range of the variation of the Matsubara frequencies in the sum in (75) is $\omega \sim \pi T_c$, then in the limit $h \gg \pi T_c, \tau_m^{-1}$, the dependence of d_{fk} on T will be weak. However, when the spin scattering is not weak, i.e. $\tau_m^{-1} \gtrsim h$, another mechanism of the temperature dependence of the d_{fk} emerges due to the temperature dependent term $\tau_m^{-1} \cos \theta_f$ in the Usadel equation (70), or, in another words, due to the complex ω dependent function $1 - \varepsilon^2$. For a strong ferromagnet, $h \gg \pi T_c$, the latter mechanism may become stronger than the 'thermal' one related to $k(\omega)$. It is not difficult to take into account both mechanisms in the numerical calculation of the sum (75).

As an illustration, we present in Fig. 8 the theoretical fit of the experimental data for NbCu_{0.52}Ni_{0.48}Nb junctions by Sellier *et al.* [35], making use of Eq.(75) valid in the limit of small interface resistances ($\gamma_B = 0$). The F layer thickness used for fit is $d_f = 18$ nm while the experimental value presented in [35] is 19 nm. The difference may be explained by the uncertainty in F layers determination that is around 1 nm, and may even increase due to the presence of a magnetically dead layer near S/F interface. Taking this in mind, the theoretical description of the critical current temperature dependence can be considered as rather satisfactory. Besides, Houzet *et al.* [9] have performed numerical calculations and got also good fit of another experimental curve of [35] ($d_f = 17$ nm) for the set of parameters which are in the same range that we have used.

As another application of the formalism, we present in Fig. 9 the theoretical fit of the experimental data of Ryazanov *et al.* [36] for NbCu_{0.47}Ni_{0.53}Nb junctions with $d_f = 22$ nm. Good agreement is achieved assuming $h = 650$ K, $\alpha = 1.35$ and $d_f = 21$ nm. As in the previous fit, small difference in d_f may be explained by the uncertainty in F layers determination.

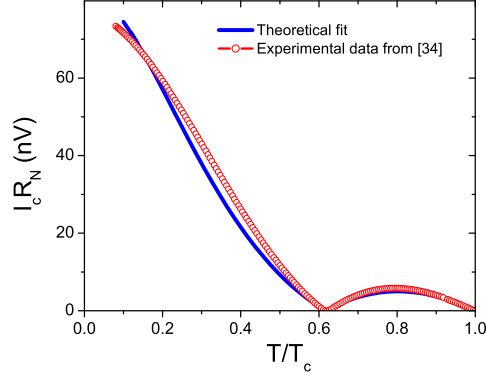


FIG. 8: (Color on line) Fit to the experimental data from Ref.[35] for the critical current in a NbCu_{0.52}Ni_{0.48}Nb junction. The fitting parameters are: $h = 220K$ and $\alpha = 3$.

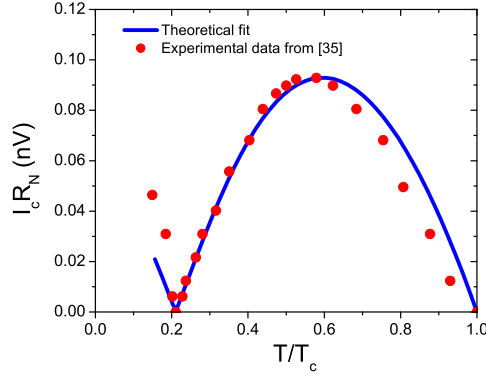


FIG. 9: (Color on line) Fit to the experimental data from Ref.[36] for the critical current in a NbCu_{0.47}Ni_{0.53}Nb junction. The fitting parameters are: $h = 650K$ and $\alpha = 1.35$.

Note that the rather complicated expression for the critical current (75) simplifies near T_c and may be written as (for $T_c \ll h$)

$$I_c R_N = \frac{\Delta^2 \pi d_f}{2e T_c \xi_{f2}} \frac{1}{\cos(\Psi)} \exp\left(-\frac{d_f}{\xi_{f1}}\right) \sin\left(\Psi + \frac{d_f}{\xi_{f2}}\right), \quad (76)$$

where Ψ is defined by $\tan(\Psi) = \frac{\xi_{f2}}{\xi_{f1}}$. The damping oscillatory behavior of the critical current is therefore retrieved, and the simplicity of the previous expression makes it useful for theoretical description of the evolution of the critical current with the thickness of the F layer.

VI. CONCLUSION

We have made detailed theoretical investigation of the influence spin-dependent scattering in the ferromagnet on the critical temperature of S/F multilayered systems and the critical current of S/F/S Josephson junctions. More precisely, we have demonstrated that spin-flip and spin-orbit scatterings both lead to the decrease of the decaying length and the increase of the oscillations period. Besides, spin-orbit scattering may be more harmful for superconductivity than spin-flip scattering. Indeed, the oscillations of T_c and I_c can be destroyed by spin-orbit scattering, while spin-flip scattering can only modify them. This allows to distinguish these pair-breaking mechanisms, which both should be taken into account for theoretical fits of experimental data. Moreover, the simultaneous introduction of the spin-flip and the spin-orbit scattering leads to important new prediction that the perpendicular spin flip can compensate spin-orbit and vice versa. Then the perpendicular magnetic scattering may restore the oscillations of T_c and I_c which would be otherwise absent if spin-orbit scattering is strong enough.

We have also studied the influence of the interface transparency on T_c and I_c in S/F and S/F/S structures, respectively. The nonmonotonous behavior of T_c with the interface transparency parameter γ_B was predicted in the case of thin F-layers due to multiple scattering at the interfaces. We have shown that the same mechanism is responsible for the 0- π transition in S/F/S junctions with small thickness d_f in the case of large γ_B . For larger d_f detailed analytical and numerical study of the influence of γ_B parameter is presented.

It was predicted in Ref.[3] that in the case of noncollinear magnetic ordering the long-ranged triplet component of the superconducting condensate could be generated. The spin-orbit and the perpendicular magnetic scattering are rather harmful for this long-ranged triplet component. Our analysis shows that the ferromagnetic alloys like $\text{Cu}_x\text{Ni}_{1-x}$, where following our estimates the parameter $1/h\tau_m$ may exceed unity, are not suitable candidates for the experimental search for the triplet component.

Finally, note that it may be interesting to study the Josephson junctions with the ferromagnetic layer substituted by a paramagnetic one. Applying an external magnetic field H , it is possible to produce the polarization of the magnetic atoms and then generate an internal field $h \sim \chi H$, where χ is the paramagnetic susceptibility. The variation the external field allows to change the relative contribution of the scattering mechanisms and the exchange

field and then to modify the properties of the junction in a controllable way. In particular, it could provoke the transition from 0 to π state.

The authors thank M. Daumens, M. Houzet, M. Kulic, C. Meyers, and V.V. Ryazanov for useful discussions. We also thank H. Sellier and V.V. Ryazanov for communication of their experimental data. This work was supported in part by EGIDE Programme 10197RC, ESF PI-Shift Programme, RFBR grant N 06-02-90865 and NanoNed programme under project TCS.7029.

VII. APPENDIX:

The coefficients $A_{\omega\pm}$ and $B_{\omega\pm}$ that appear in (34) and (35) may be written as

$$A_{\omega+} = \frac{2\Delta G_S \cos(\varphi/2)}{|\omega| \{ \gamma_B \xi_n k_+ \sinh[k_+ d_f] + |G_S| \cosh[k_+ d_f] \} (1 + \eta_\omega^2)}, \quad (77)$$

$$B_{\omega+} = \frac{2i\Delta G_S \sin(\varphi/2)}{|\omega| \{ \gamma_B \xi_n k_+ \cosh[k_+ d_f] + |G_S| \sinh[k_+ d_f] \} (1 + \eta_\omega^2)}, \quad (78)$$

$$A_{\omega-} = -\frac{2\Delta G_S \eta_\omega \cos(\varphi/2)}{|\omega| \{ \gamma_B \xi_n k_- \sinh[k_- d_f] + |G_S| \cosh[k_- d_f] \} (1 + \eta_\omega^2)}, \quad (79)$$

$$B_{\omega-} = -\frac{2i\Delta G_S \eta_\omega \sin(\varphi/2)}{|\omega| \{ \gamma_B \xi_n k_- \cosh[k_- d_f] + |G_S| \sinh[k_- d_f] \} (1 + \eta_\omega^2)}, \quad (80)$$

The symmetry relations following from (34) -(36) are at $h \leq \tau_{so}^{-1}$

$$\eta_\omega = \eta_{-\omega}^*, \quad A_{-\omega+}^* = A_{\omega+}, \quad A_{-\omega-}^* = A_{\omega-}, \quad B_{-\omega+}^* = -B_{\omega+}, \quad B_{-\omega-}^* = -B_{\omega-}. \quad (81)$$

and if $h \geq \tau_{so}^{-1}$:

$$\begin{aligned} \eta_{-\omega}^* \eta_\omega &= -1, \quad \beta_{\omega+} = \beta_{\omega-}^* = \beta, \\ \eta_{-\omega}^* A_{-\omega+}^* &= A_{\omega-}, \quad A_{-\omega-}^* = \eta_\omega A_{\omega+}, \quad \eta_{-\omega}^* B_{-\omega+}^* = -B_{\omega-}, \quad B_{-\omega-}^* = -\eta_\omega B_{\omega+}. \end{aligned} \quad (82)$$

These relations allow us to simplify the calculations for the determination of the critical current.

[1] A. I. Buzdin, Rev. Mod. Phys. **77**, 935 (2005).

- [2] A. A. Golubov, M. Yu. Kupriyanov, and E. Il'ichev, *Rev. Mod. Phys.* **76**, 411 (2004).
- [3] F. S. Bergeret, A. F. Volkov, and K. B. Efetov, *Rev. Mod. Phys.* **77**, 1321 (2005).
- [4] V. V. Ryazanov, V. A. Oboznov, A. Yu. Rusanov, A. V. Veretennikov, A. A. Golubov, and J. Aarts, *Phys. Rev. Lett.* **86**, 2427 (2001).
- [5] H. Sellier, C. Baraduc, F. Lefloch, and R. Calemczuck, *Phys. Rev. B* **68**, 054531 (2003).
- [6] V. A. Oboznov, V. V. Bol'ginov, A. K. Feofanov, V. V. Ryazanov, and A.I. Buzdin, cond-mat/0508573.
- [7] G. Eilenberger, *Z. Phys.* **214**, 195 (1968).
- [8] L. Usadel, *Phys. Rev. Lett.* **25**, 507 (1970).
- [9] M. Houzet, V. Vinokur, and F. Pistolesi, cond-mat/0505514.
- [10] P. Fulde and K. Maki, *Phys. Rev.* **141**, 275 (1966).
- [11] A. A. Abrikosov, L. P. Gor'kov, and I. E. Dzyaloshinski, *Methods of Quantum Field Theory in Statistical Physics* (Dover, New York), 1975.
- [12] A. I. Buzdin, *Pis'ma Zh. Eksp. Teor. Phys.* **42**, 283 (1985) [*JETP Lett.* **42**, 350 (1985)].
- [13] A. I. Buzdin and M. Y. Kuprianov, *Pis'ma Zh. Eksp. Teor. Phys.* **52**, 1089 (1990) [*JETP Lett.* **52**, 487 (1990)].
- [14] Z. Radovic, M. Ledvij, L. Dobrosavljevic-Grujic, A. I. Buzdin, and J. R. Clem, *Phys. Rev. B* **44**, 759 (1991).
- [15] E. A. Demler, G. B. Arnold, and M. R. Beasley, *Phys. Rev. B* **55**, 15174 (1997).
- [16] S. Oh, Y. Kim, D. Youm, and M. R. Beasley, *Phys. Rev. B* **63**, 052501 (2000).
- [17] L. R. Tagirov, *Phys. C* **307**, 145 (1998).
- [18] Vladimir I. Fal'ko, A. F. Volkov, and C. Lambert, *Phys. Rev. B* **60**, 15394 (2002).
- [19] A. Millis, D. Rainer, and J. A. Sauls, *Phys. Rev. B* **38**, 4504 (1988).
- [20] M. Fogelström, *Phys. Rev. B* **62**, 11 812 (2000).
- [21] J. C. Cuevas and M. Fogelström, *Phys. Rev. B* **64**, 104502 (2001).
- [22] M. Eschrig, J. Kopu, J. C. Cuevas, and Gerd Schön, *Phys. Rev. Lett.* **90**, 137003 (2003).
- [23] A. I. Buzdin, A. V. Vedyayev and N. V. Ryshanova, *Europhys. Lett.* **48**, 686 (1999).
- [24] I. Baladié and A. Buzdin, *Phys. Rev. B* **67**, 014523 (2003).
- [25] M. Yu. Kuprianov and V. F. Lukichev, *Zh. Eksp. Teor. Fiz.* **94**, 139 (1988) [*Sov. Phys. JETP* **67**, 1163 (1988)].
- [26] J. Aarts, J.M.E. Geers, E. Brueck, A.A. Golubov, R. Coehoorn, *Phys. Rev. B* **56**, 2779 (1997).

- [27] Ya. V. Fominov, N. M. Chtchelkatchev, and A. A. Golubov, Phys. Rev. B **66**, 014507 (2002).
- [28] A. I. Buzdin, L. N. Bulaevskii, and S. V. Panyukov, Pis'ma Zh. Eksp. Teor. Phys. **35**, 147 (1982) [JETP Lett. **35**, 178 (1982)].
- [29] A. I. Buzdin, and M. Y. Kuprianov, 1991, Pis'ma Zh. Eksp. Teor. Phys. **53**, 308 (1991) [JETP Lett. **53**, 321 (1991)].
- [30] V. N. Krivoruchko and R. V. Petryuk, Phys. Rev. B **66**, 134520 (2002).
- [31] F. S. Bergeret, A. F. Volkov, and K. B. Efetov, Phys. Rev. B **68**, 064513 (2003).
- [32] A. I. Buzdin, Pis'ma Zh. Eksp. Teor. Phys. **53**, 308 [JETP Lett. **78**, 583 (2003)].
- [33] L. Cr  tinon, A. K. Gupta, H. Sellier, F. Lefloch, M. Faur  , A. Buzdin, and H. Courtois, Phys. Rev. B **72**, 024511 (2005).
- [34] K. K. Likharev, Rev. Mod. Phys. **51**, 101 (1979).
- [35] H. Sellier, C. Baraduc, F. Lefloch, and R. Calemczuck, Phys. Rev. Lett. **92**, 257005 (2004).
- [36] V. V. Ryazanov, V. A. Oboznov, A. S. Prokofiev, V. V. Bolginov and A. K. Feofanov, Journal of Low Temp. Phys. **136**, 385 (2004).