¹¹¹Cd- TDPAC study of pressure-induced valence transition in YbAl₂

A.V. Tsvyashchenko, L.N. Fomicheva

Vereshchagin Institute for High Pressure Physics, RAS, 142190 Troitsk, Russia

V.B. Brudanin, O.I. Kochetov, A.V. Salamatin, A. Velichkov

Joint Institute for Nuclear Research, P.Box 79, Moscow, Russia

M. Wiertel, M. Budzynski

Institute of Physics, M. Curie-Sklodowska University, 20-031 Lublin, Poland

A.A. Sorokin, G.K. Ryasniy, B.A. Komissarova

Skobeltsyn Institute of Nuclear Physics, 119899 Moscow, Russia

M.Milanov

Institute for Nuclear Research and Nuclear energy, BAS, 1000 Sofia, Bulgaria

The quadrupole interaction at 111 Cd impurity nuclei in the intermediate-valence compound YbAl₂ has been measured under pressure up to 80 kbar by the TDPAC spectroscopy. It was found that the quadrupole frequency v_Q measured on the 111 Cd located at the Al sites in YbAl₂, varies nonlinearly and increases by almost four times with the pressure increase up to 80 kbar. A linear correlation between the mean Yb valence, derived from Yb L₃ OFY-XAS and RXES measurements, and the electric field gradient (the quadrupole frequency $v_Q = eQV_{zz}/h$) has been observed. The quadrupole frequencies on 111 Cd in the GdAl₂, YbAl₃, TmAl₃ and CaAl₂ compounds have been measured, also. The possibility of determining the valence of Yb in the Yb compounds with p-metals from the relation $v_Q(v(P)) = v_2 + (v_3 - v_2) v(P)$ has been considered.

PACS number(s): 76.80.+y, 71.28.+d

INTRODUCTION

Ytterbium intermetallic compounds exhibit interesting physical phenomena such as intermediate valence, Kondo, or heavy fermion behavior¹. These properties are highly sensitive to chemical environment as well as to external pressure or temperature. These is due to the fact that in the atomic ground state Yb is divalent with a filled f^{14} shell, but in the solid state the f-electrons may play an active role in the formation of the electronic band structure. The accurate theoretical description of the Yb compounds remains a challenge. Nevertheless, by applying self-interaction corrections (SIC)² in the local-spin-density approximation (LSDA), the authors could give a valid description of the effective valences of Yb in the Yb compounds. In this description, for a nominal trivalent case, where Yb possesses a localized f^{13} shell, the $14^{th}f$ -electron forms a very narrow band situated among normal s-d-derived conduction states. The Fermi level is pinned to this narrow band that becomes partially occupied. As a consequence, the total f occupancy is non-integer and falls in between

13 and 14, and the nominally trivalent Yb configuration therefore describes an intermediate valent state with the number of the band f - electrons, $n_{f=(0 \le n_{f \le 1})}$.

The conventional definition of the effective valence for rare earths identifies the valence by the number of the band f-electrons having passed into the 5d-electron band (hereinafter they are referred to as "band f-electrons" in inverted commas),1- $n_f = n_{5d}$, or the number of f holes $1-n_f = n_h^{-1}$. Thus, the Yb valence is determined as $v = 3 - n_f = 2 + n_{5d} = 2 + n_h$.

In order to obtain quantitative experimental information on the mean valence, researchers widely employ the following techniques: L_{III} – edge x-ray-absorption spectroscopy (XANES)³, Mössbauer effect (ME) (the mean valence derived from isomer shift measurements)⁴ and photoemission spectroscopy of the 4 f- levels⁵. It should be noted that the parameters, measured by these techniques, couldn't be calculated from the first principles.

On the other hand, the electric field gradient (EFG) is a ground-state property of a solid and depends sensitively on the asymmetry of the electronic charge in a crystal. Blaha *et al.* developed a first-principles method to compute the EFGs. They have used the full-potential linear augmented-plane-wave (FL-LAPW) method and have calculated the EFG directly from the self-consistent charge density by solving the Poisson's equation.

But since the formation of the electron bands by hybridization between the states of different shells leads to a non-integer occupation of the related shells and to the redistribution of the charge density, one can expect that the EFG may also reflect the change of the valence of rare earth ions.

Indeed, the experimental studies of the electric (nuclear) quadrupole interaction (EQI) preformed by the time-differential perturbed angular correlation (TDPAC) method in a series of intermetallic compounds RIn_3^7 , RSn_3^7 and RAl_2^8 (R=a rare earth element) demonstrated a sharp drop of the EFG at ^{111}Cd in $YbIn_3$, in RSn_3 with R=Eu and Yb, and in $EuAl_2$ with regard to other trivalent rare earths R^{+3} . This drop was assigned to be due to the difference in the valence between Eu and Yb with v=2 and the compounds with $R=R^{+3}$.

When performing *ab initio* numerical analysis⁹ of the experimental data⁷ on the EFG of 111 Cd in YbIn₃, YbSn₃ and EuSn₃, the authors used the FL-LAPW method 6,10 . They showed that the increased V_{zz} value in R⁺³In(Sn)₃ relative to the EFG values observed in R⁺²In(Sn)₃ is caused by an additional polarization of Cd p-electrons due to a strong f - p hybridization near the xy plane⁹.

For all R³⁺Al₂ compounds it was shown⁸ that the EQI of ¹¹¹Cd is characterized by the quadrupole coupling constant (the quadrupole frequency) $v_Q \approx 50$ MHz, slightly dependent on Z of a rare earth element, whereas in Eu⁺²Al₂ it is several times lower, $v_Q \cong 8$ MHz. No data for YbAl₂ were reported in [ref. 8]. However, the ¹⁵¹Eu Mössbauer studies¹¹ under hydrostatic pressure up to 410 kbar revealed that – contrary to expectations – the 4*f* electrons in EuAl₂ remain fully localized, that is, the Eu ions are divalent, even at the reduction of the unit cell volume by ~ 30%.

On the other hand, the resent results¹² of the pressure-induced valence transition investigations performed by Yb L_3 OFY-XAS and RXES for YbAl₂ have revealed that the Yb valence increases from 2.25 at ambient pressure to 2.8 at 80 kbar. In so doing, preliminary high-pressure x-ray diffraction studies¹³ had found no changes in the crystal structure of YbAl₂ up to 80 kbar.

In view of the said above, in this work for studies by the ¹¹¹Cd -TDPAC method of a pressure-induced valence change we chose the YbAl₂ compound crystallizing in the cubic

structure of a MgCu₂ type. The experimental determination of the pressure dependence of the quadrupole coupling constant $v_Q=eQV_{zz}/h$ (the quadrupole frequency) measured on ¹¹¹Cd probes by the time-differential perturbed angular correlation method enabled us to determine the linear dependence of the EFG on the number of the "band-f-electrons", or $1 - n_f = n_h = n_{5d}$. We demonstrated that this dependence can be used for determining the valence of Yb ions for the YbAl₃ and YbIn₃ compounds.

EXPERIMENT

The measurements were carried out by the time-differential perturbed angular correlation method using the 171-245 keV γ -ray cascade in 111 Cd populated through the 2.8 d isotope 111 In electron capture decay. The cascade proceeds via the 245 keV level with the half-life $T_{1/2} = 84$ ns, spin I = 5/2, and quadrupole moment O = 0.83 b.

The ¹¹¹In activity was produced via the ¹⁰⁹Ag $(\alpha, 2n)$ ¹¹¹In reaction through irradiating a silver foil with the 32 MeV α -beam. The nuclear probe ¹¹¹In-¹¹¹Cd was introduced into the lattice of YbAl₂, YbAl₃, GdAl₂, TmAl₃, and CaAl₂ by the high pressure synthesis: the constituents (Yb, Tm, Gd, Ca and Al) taken in proper amounts with an overall weight of about 500 mg were melted together with a small piece of the irradiated silver foil (\approx 0.5 mg) in a special chamber under pressure of 80 kbar ¹⁴.

The X-ray diffraction of the powdered samples evidenced that the alloys were single phase; YbAl₂ had the cubic Laves phase structure, and YbAl₃, TmAl₃ had the cubic Cu₃Au structure. Our previous experience has proved that this procedure ensures the substitution of ¹¹¹In for Ru in the Laves compounds LaRu₂ and CeRu₂ ¹⁴, and, as will be shown below, for Al in GdAl₂⁸, and, presumably, in YbAl₂, YbAl₃, CaAl₂ and TmAl₃.

The TDPAC measurements were carried out using a 4-detector spectrometer equipped with a small-size hydraulic four-arm press of the capacity up to $300 t^{15}$.

As the samples were polycrystalline and paramagnetic at room temperature, the perturbation of the angular correlation can be described by the perturbation factor for the static electric quadrupole interaction ¹⁶:

$$G_{22}(t; v_q, \eta, \delta) = s_{20} + \Sigma s_{2n} cos(\omega_n t) exp(-1/2\delta\omega_n t).$$

The hyperfine frequencies ω_n depend on the quadrupole coupling constant $v_Q=eQV_{zz}/h$ (the quadrupole frequency), and the asymmetry perameter $\eta=(V_{xx}-V_{yy})/V_{zz}$, where $V_{ii}=\partial^2 V/\partial i^2$ (i=x,y,z) are the principal-axis components of the EFG tensor. The coefficients s_{2n} depend only on η ($1 \ge \eta \ge 0$). For the nuclear spin I=5/2, n=1, 2, 3. The exponential factor accounts for possible random lattice defects, and δ is the relative half-width of the Lorentzian distribution. Here we restrict ourselves to the perturbation parameter of the second order since the unperturbed angular correlation coefficient $A_{44} << A_{22}$ ($A_{22}=-0.18$).

The perturbation factor $G_{22}(t)$, describing a nuclear spin precession due to a hyperfine interaction, was determined in a usual way from the angular anisotropy, obtained by combining the delayed coincidence spectra measured at the angles of 90° and 180° between detectors, $N(90^{\circ},t)$ and $N(180^{\circ},t)$, through the expression $R(t) = -A_{22}Q_2G_{22}(t)$, where


$$R(t) = 2[N(180^{\circ}, t) - N(90^{\circ}, t)] / [N(180^{\circ}, t) + N(90^{\circ}, t)], Q_2 \approx 0.80$$
 is the solid-angle correction.

A 100 mg sample of YbAl₂ doped with ¹¹¹In was positioned inside a rock-salt ampoule that was used as a pressure-transmitting medium. The high pressure was generated in a calibrated "toroid"-type device ¹⁷. The calibration of the device was confirmed through

measuring the EQI of ¹¹¹Cd in ¹¹¹In-doped metallic Zn at normal pressure and at nominal pressure of 30 *kbar*. The obtained values, ν_Q =131 and 113 MHz, respectively, were in good agreement with those reported by da Jornada and Zavislak ¹⁸.

RESULTS AND DISCUSSION

The ¹¹¹Cd - TDPAC spectra $R(t) = -A_{22}Q_2G_{22}(t)$ observed in the YbAl₂ and GdAl₂ compounds at different pressures are presented in Fig.1 and 2.

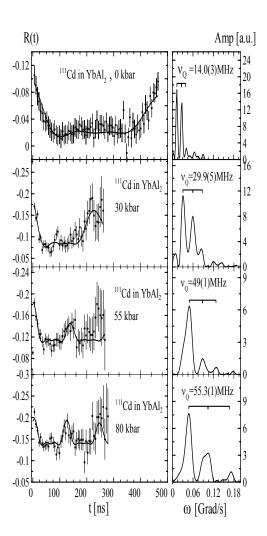

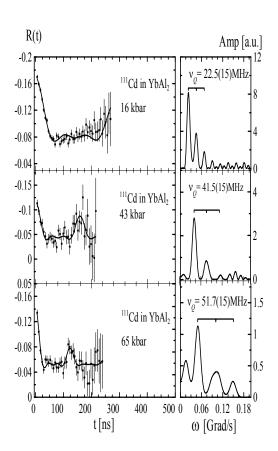


Fig. 1. Time spectra of the angular correlation anisotropy, R(t) (left panel) and their Fourier transform (right panel), for ¹¹¹Cd in YbAl₂ measured at various pressures. The increase in the deviation of the anisotropy spectrum with the increase of pressure from a zero line is due to the scattering in the sample that varies in shape from a cylinder to a thin disk (see ref. 19) as pressure rises.

The TDPAC spectrum for YbAl₂ measured at normal pressure can be best fitted with v_Q =14.0(3) MHz assuming the asymmetry perameter η = 0. Here we note in advance that in all cases the zero pressure R(t) curves were the same before and after compression, and the values of the quadrupole frequency (QF) v_Q extracted from the experimental R(t) curves coincided. The EQI parameters measured at normal pressure for GdAl₂, v_Q = 51(1) MHz,

 $\eta = 0$, were in good agreement with the data reported in [ref.8]. As was mentioned, this result confirms that in the sample prepared by the synthesis at high pressure through the method described above, ¹¹¹In substitutes for Al.

The value of the quadrupole frequency v_Q for YbAl₂ is several times lower than that for GdAl₂ (where the Gd ion is trivalent); the same was earlier observed for EuAl₂⁸.

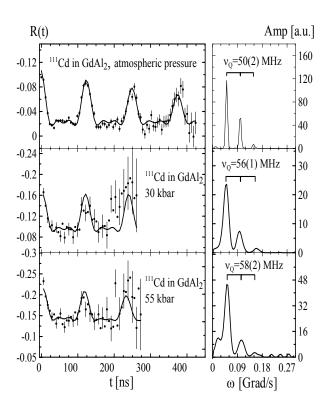


Fig. 2. Time spectra of the angular correlation anisotropy, R(t) (left panel) and their Fourier transform (right panel), for ¹¹¹Cd in GdAl₂ measured at various pressures.

The variations of the QF v_Q with pressure for ¹¹¹Cd in YbAl₂ and GdAl₂ are shown graphically in Fig. 3.

As seen from the pressure dependence of the quadrupole frequency v_Q measured on the ^{111}Cd impurity nuclei located at the Al sites in YbAl₂ (see Fig.3), the QF varies nonlinearly and increases by almost four times with the pressure increase up to 80 kbar. For GdAl₂ the QF rises with the same pressure increase for not more that 10%. A similar behavior was observed for the pressure-induced change in the isomer shift of EuNi₂Ge₂ pointing to a valence transition from Eu⁺² to Eu⁺³ around 50 kbar in [ref. 20].

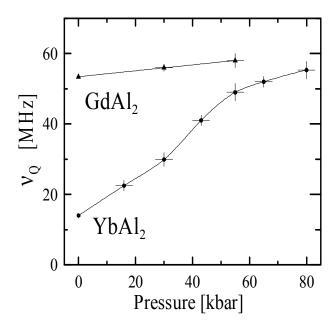


Fig. 3. Pressure dependence of the quadrupole frequency v_Q for 111 Cd in YbAl₂ and GdAl₂.

This considerable difference in the QF values and behaviour according to pressure for these particular compounds can be explained by the following fact. The ytterbium ion valence in YbAl₂ at normal pressure is 2.25 and it rises to 2.8 12 with the pressure increase to 80 kbar. In GdAl₂, the gadolinium ion valence is 3 and as the pressure in this range goes higher, it does not change. Since the valency change ($\upsilon = 2 + n_d = 2 + (1 - n_f)$) is determined by the filling of the 5*d*- band by the transition of *f*-electrons, both the QF value and QF variation according to pressure is governed by the fact that the main contribution to the electric field gradient is made by the "band-*f*-electrons". If the number of the "band-*f*-electrons" remains the same, then the increase of the EFG can occur due to the reduction of the lattice parameter, as was shown in [Ref. 7] for cubic compounds RIn₃. This can explain an inessential pressure-dependent rise of the QF, observed for GdAl2.

Using the data obtained in [Ref. 12] for the pressure dependence of the ytterbium ion valence, we have plotted the dependence of the EFG at ¹¹¹Cd in YbAl₂ on the number of the "band *f*-electrons" (1 - $n_f = n_{5d}$) and have found this dependence to be linear (see Fig.4).

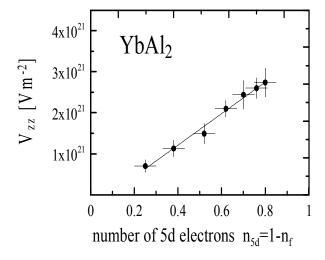


Fig. 4. The electric field gradient $(V_{zz} = v_Q h / eQ)$ for ¹¹¹ Cd in YbAl₂ versus the number of the band *f*-electrons having passed into the 5d-band $(1 - n_f = n_{5d})$.

Thus, based upon a linear dependence of the EFG (or the quadrupole frequency which is directly measured in the experiment) on the number of the "band f-electrons" $(1-n_f)$, one can determine the valence $[\upsilon = 2+(1-n_f) = 2+\upsilon(P)]$ of the ytterbium ions by using the following relation: $\nu(\upsilon(P)) = \nu_2 + (\nu_3 - \nu_2) \upsilon(P)$, where $\nu(\upsilon(P))$ - is the QF measured on "111Cd in a ytterbium compound with an p-metals (for example Al, In); ν_3 - is the QF measured in a similar compound with a trivalent ytterbium or a trivalent rare earth; ν_2 — is the QF measured in a similar compound with divalent ytterbium or with another divalent metal, for example, Eu, or Ca. This relation is similar to the one determining the valence for Eu from isomeric shift 4,21 .

Indeed, for YbAl₂ from a linear dependence of the QF, v_2 is equal to -5.8(4) MHz and the value of $(v_3 - v_2)$ is equal to 76.3(6) MHz. As ytterbium in the YbAl₂ compound at normal pressure has a non-integer valence, for the evaluation of v_2 we have measured the QF in CaAl₂. This compound has the same crystal structure as YbAl₂, but Ca is usually regarded as a divalent analogue of Yb. From the ¹¹¹Cd -TDPAC measurements we found the value v_2 for CaAl₂ to be equal to 5.7(2) MHz (see fig.5.)and close to the v_2 value defined from QF linear dependence for YbAl₂.

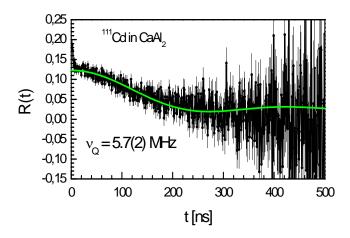


Fig.5. Time spectrum of the angular correlation anisotropy, R(t) for ^{111}Cd in $CaAl_2$ measured at normal pressures.

It is also known²² that by employing the X-ray L_{111} - absorption technique, the Yb ion valence for the YbAl₃ compound was determined and found equal to 2,83 at room temperature (i.e., $v(P) = (1-n_f) = 0,83$). To verify our assertion that the $(1-n_f)$ - quadrupole frequency dependence is linear for other compounds, we have performed the measurements of the QF for the YbAl₃ and TmAl₃ compounds that have a Cu₃Au – type crystalline structure. Angular anisotropy spectra for these compounds are given in Fig.6.

It turned out that for YbAl₃, the QF value is equal to 73.3 MHz, and for TmAl₃ it is 85,2 MHz. To determine the valence of the Yb ions in this compound we employ the relation suggested above. We assume that the value $(v_3 - v_2)$ does not depend on the crystalline structure and remain equal to 76,3 MHz, as it was found for YbAl₂, while the v_2 value do depend on the crystalline structure of the compound. Assuming that v_3 (Yb⁺³Al₃) = v(Tm⁺³Al₃)= 85,2 MHz, we can easily determine v_2 (Yb⁺²Al₃)= 8,9 MHz. Then for YbAl₃ the value v(P) = [v(YbAl₃) - v_2 (Yb⁺²Al₃)]/ (v_3 - v_2) = (73.3-8.9)/ 76.3 = 0.84. The ratio of these frequencies gives us the value v(P) = 0,84 and, accordingly, the valence 2.84 for Yb ions in YbAl₃. Thus, the valence determined through the TDPAC method is in good agreement with the data²² on the valence of Yb in YbAl₃. If we use this line of reasoning for YbIn₃, then, from the data⁷ on the quadrupole frequency measurements by ¹¹¹Cd-TDPAC (for YbIn₃ v_Q = 38,7 MHz, and for TmIn₃ v_Q = 87,7 MHz), we obtain the valence of a Yb ion in YbIn₃ equal to 2,36 and the value v₂(Yb⁺²In₃) = 11.4 MHz. This is close but not similar to the value of a Yb ion (v = 2,50) in [Ref. 23]. The difference can be accounted for by the fact that the valence in [Ref. 23] was found without using the L_{III} – edge x-ray-absorption spectroscopy (XANES) technique.

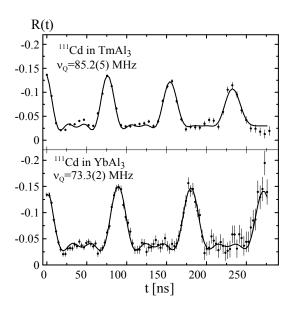


Fig. 6. Time spectrum of the angular correlation anisotropy, R(t) for ^{111}Cd in $TmAl_3$ and $YbAl_3$, measured at normal pressures.

CONCLUSION

In this way, the results obtained in this work make it possible to state that the variation of the EFG (the quadrupole frequency $v_Q=eQV_{zz}/h$) for the Yb compounds with p –metals is linearly connected with the number of the f–electrons having changed over to a conduction band, i.e., with the number $(1-n_f)$. This regularity allows the determination of the Yb valence through the ¹¹¹Cd-TDPAC method.

In the work by Svane et. al 2 when calculating the Yb ion valence from the first principles, a linear correlation was also determined between the difference of the energies of the valent states and the number $(1-n_f)$ of the electrons having come over to a conduction

band. However, since the change of the energies between two different valent states is caused by the redistribution of f-electrons, which, in its turn, causes the variation of the EFG, one can speak of an agreement between the theory² and experimental results obtained in the present work. Although for drawing a correct comparison, theoretical calculations of the EFG vs Yb valence dependence are necessary.

ACKNOLEGEMENTS

This work was supported by the grants of the Russian Foundation for Basic Research (project nos. 07-02-00280) and by special programs of the Department of Physical Science, Russian Academy of Sciences. The work at the Joint Institute for Nuclear Research was carried out under the auspices of a Polish representative in the JINR.

- P. Wachter, *Handbook on the Physics and Cheistry of Rare Earths* (North-Holland Amsterdam, 1993), Vol.19, Chap. 132.
- ² A. Svane, W.M. Temmerman, Z. Szotec, L. Petit, P. Strange, and H. Winter, Phys. Rev. B **62**, 13394 (2000).
- ³ K.R. Bauchspeiss, W. Boksch, E. Holland-Moritz, H. Launois, R. Pott, and D. Wohlleben, *Valence Fluctuations in Solids*, edited by L. M. Falicov, W. Hanke, and M.B Maple (North Holland, Amsterdam, 1981) p. 417.
- ⁴ G. Schmiester, B. Perscheid, G. Kindl, and J. Zukrowsky, *in Valence Instabilities*, edited by P. Wachter and H. Boppart (North Holland, Amsterdam, 1982) p. 219.
- ⁵ S.-J. Oh, J.W. Allen, M.S. Torikachvili, and M.B. Maple, J. Magn. Magn. Mater., **52**, 183 (1985).
- P. Blaha, K. Schwarz, and P. Herzig, Phys. Rev. Lett. 54, 1192 (1985); P. Blaha, K. Schwarz, J. Phys. F 17,899 (1987); P. Blaha, K. Schwarz, and P. H. Dederichs, Phys. Rev. B 37, 2792 (1988).
- S. Schwarz, D. Shirley, Hyperfine Interact. **3, 67** (1977).
- ⁸ S. N. Mishra, R. G. Pillay, K. Raghunathan *et al.*, Phys. Lett. **91A**, 193 (1982).
- ⁹ S. J. Asabadi, S. Cottenier, H. Akbarzadeh, R. Saki, M. Rots, Phys. Rev. B **66**, 195103 (2002).
- P. Blaha, K. Schwarz, G. Madsen, D. Kvasnicka, and J. Luitz, WIEN2k, An Augmented Plane Wave + Local Orbitals Program for Calculating Crystal Properties (Karlheinz Schwarz, Tech. Univ. Wien, Vienna, 2001).
- ¹¹ A. Gleissner, W. Potzel, J. Moser, G. M. Kalvius, Phys. Rev. Lett. **70**, 2032 (1993).
- C. Dallera, E. Annese, J.-P. Rueff, A. Palenzona, G. Vanko, L. Braicovich, A. Shukla, M. Grioni, Phys. Rev. B 68, 245114 (2003).
- A. Palenzona and S. Cirafici, High Temp. High Press., 17, 547 (1985).
- ⁴ A. V. Tsvyashchenko, L. N. Fomicheva, A. A. Sorokin, G. K. Ryasny,
 - B. A. Komissarova, L. G. Spinkova, K.V. Klementiev, A. V. Kuznetsov,
 - A. P. Menushenkov, V. N. Trofimov, and R. Cortes, Phys. Rev. B, 65, 174513 (2002).
- ¹⁵ V. B. Brudanin, D. V. Flossofov, O. I. Kochetov, N. A. Korolev, M. Milanov,
 - V. Ostrovskiy, V. N. Pavlov, A, V, Salamatin, V. V. Timkin, A. I. Velichkov,
 - L. N. Fomicheva, A. V. Tsvyashchenko, Z. Z. Akselrod, Nucl. Instr. and Meth. A **547**, 389 (2005).
- ¹⁶ R. M. Steffen and H. Frauenfelder, *in Perturbed Angular Correlations*, edited by E. Karlsson. E. Matthias and K. Siegbahn (North-Holland, Amsterdam, 1964).

- L. G. Khvostantsev, L. F. Vereshchagin, and A. P. Novikov, High Temp.-High. Press., **9**, 637 (1977).
- ¹⁸ J. A. H. da Jornada and F. C. Zawislak, Phys. Rev. B, **20**, 2617 (1979).
- ¹⁹ K. Siegbahn, *Alpha-, Beta- and Gamma-Ray Spectroscopy* (North-Holland Publishing Company, Amsterdam, 1965), Vol.3.
- ²⁰ H. -J. Hesse and G. Wortmann, Hyperfine Interact., **93**, 1499 (1994).
- I. Serdons, S. Nasu, R. Callens, R. Coussement, T. Kawakami, J. Ladriére, S. Morimoto, T. Ono, K. Vyvey, T. Yamada, Y. Yoda, and J. Odeurs, Phys. Rev. B 70, 014109 (2004).
- ²² J. M. Lawrence, G. H. Kwei, P. C. Canfield, J. G. DeWitt, A. C. Lawson, Phys. Rev. B **49**, 1627 (1994).
- ²³ J. C. P. Klasse, F.R. de Boer, and P. F. de Chatel, Physica 106 B, 178 (1981).