Orbital Dynamics: The Origin of Anomalous Magnon Softening in Ferromagnetic Manganites

G. Khaliullin^{1,2} and R. Kilian¹

¹ Max-Planck-Institut für Physik komplexer Systeme, Nöthnitzer Strasse 38, D-01187 Dresden, Germany ² Max-Planck-Institut für Festkörperforschung, Heisenbergstrasse 1, D-70569 Stuttgart, Germany (Version date: 15 April, 1999)

We study the renormalization of magnons by charge and coupled orbital-lattice fluctuations in colossal magnetoresistance compounds. The model considered is an orbitally degenerate double-exchange system coupled to Jahn-Teller active phonons. The modulation of ferromagnetic bonds by low-energy orbital fluctuations is identified as the main origin of the unusual softening of the zone-boundary magnons observed experimentally in manganites.

PACS number(s): 75.30.Ds, 75.30.Et

Recently, distinct new features in the spin dynamics of the ferromagnetic manganese oxide compound $Pr_{0.63}Sr_{0.37}MnO_3$ have been reported [1]. Striking deviations from the predictions of the canonical double-exchange (DE) theory [2–4] were observed. In particular, an anomalous softening of magnons at the zone boundary was found even well below the Curie temperature T_C . It is noted that these anomalies are closely related to the reduced values of T_C : For higher- T_C compounds no considerable deviations from a simple cosine dispersion is observed [5].

These experimental findings seem to be of high importance. They in fact indicate that some very specific features of magnetism in colossal magnetoresistance manganites have still to be identified. In this paper we propose a mechanism which might explain the above experimental observations. Our basic idea is the following: The strength of ferromagnetic interaction in a given bond strongly depends on which orbital is occupied by an e_q electron (Fig. 1). Suppose that orbitals and Jahn-Teller (JT) distortions are disordered in the ferromagnetic phase. It is then evident that temporal fluctuations of orbitals affect the short-wavelength magnons through a strong modulation of exchange bonds. Quantitatively, the effect is expected to be controlled by the characteristic time scale of orbital fluctuations: A slowing-down of the dynamics of the coupled system of orbitals and JT phonons should lead to a stronger magnon renormalization. In other words, the observed zone-boundary magnon softening is interpreted in this picture as a precursor effect in the proximity of static orbital-lattice ordering.

More specifically, we calculate the dispersion of onemagnon excitation at zero temperature. First, we map the ferromagnetic Kondo-lattice model onto a Hamiltonian of interacting magnons and spinless fermions. Yet the fermions carry orbital quantum number, the fluctuations of which the magnon can scatter on. Second, we show that as the orbitals are strongly coupled to the lattice there is an indirect coupling of magnons to JT phonons via the orbital sector. Put another way, the orbital-lattice coupling produces a low-energy component in the orbital fluctuation spectrum at phonon frequencies. We then calculate the self-energy corrections to the magnon dispersion perturbatively (employing a 1/S expansion). Charge fluctuations are found to produce a moderate softening of magnons throughout the Brillouin zone. The effect of orbital and lattice fluctuations on the magnon dispersion is more pronounced and becomes dramatic as static order in the orbital-lattice sector is approached.

We start with a model describing the ferromagnetic coupling of double-degenerate e_g -band electrons to an otherwise noninteracting system of localized spins S_t on a cubic lattice:

$$H = -\sum_{\langle ij\rangle_{\gamma}} t_{\gamma}^{\alpha\beta} \left(e_{i\sigma\alpha}^{\dagger} e_{j\sigma\beta} + \text{H.c.} \right) - J_{H} \mathbf{S}_{it} \mathbf{s}_{ie}$$
$$+ \sum_{\alpha} U n_{i\uparrow\alpha} n_{i\downarrow\alpha} + \sum_{\alpha\neq\beta}' \left(U' - J_{H} \hat{P} \right) n_{i\alpha} n_{i\beta}$$
(1)

with $\gamma \in \{x, y, z\}$ and $\hat{P} = (s_{i\alpha}s_{i\beta} + \frac{3}{4})$. Hereafter, the indices α/β and σ stand for orbital and spin quantum numbers of e_g electrons, respectively; summation over repeated indices is implied and double counting is excluded from the primed sum. The spin operator $s_{i\alpha}$ acts on orbital α and $s_{ie} = \sum_{\alpha} s_{i\alpha}$. The last two terms in Eq. (1) describe intra- (inter-) orbital Coulomb interaction U(U') and Hund's coupling between e_g electrons in doubly occupied states. Correlations are assumed to be strong: $U, U', (U' - J_H) \gg t$. The important point is the peculiar orbital and bond dependencies of the electron hopping matrix elements. In orbital basis $\alpha \in \{|3z^2 - r^2\rangle, |x^2 - y^2\rangle\}$ (see Fig. 1) one has [6]:

$$t_{x/y}^{\alpha\beta} = t \begin{pmatrix} 1/4 & \mp \sqrt{3}/4 \\ \mp \sqrt{3}/4 & 3/4 \end{pmatrix}, \quad t_z^{\alpha\beta} = t \begin{pmatrix} 1 & 0 \\ 0 & 0 \end{pmatrix}.$$

We work in the limit $J_H \to \infty$. Then the combined action of the on-site Hund's "ferromagnetism" and the spin-diagonal nature of electron hopping results in a global ferromagnetic ground state. Two different contributions

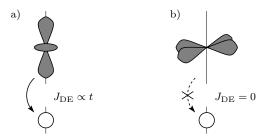


FIG. 1. The e_g -electron transfer amplitude which controls the double-exchange interaction $J_{\rm DE}$ strongly depends on orbital orientation.

to the spin stiffness should be noticed: Conventional double exchange due to metallic charge motion and superexchange which accounts for the kinetic energy gain by virtual hoppings of e_g electrons. We now derive the effective Hamiltonian describing the spin excitations at $T \ll T_C$.

Double exchange.— At $J_H \to \infty$, S_t and the e_g spin s_e are not independent anymore: $s_{ie} = n_{ie}S_t/2S_t$. They form a total on-site spin S_i with spin value $S_t + \frac{1}{2}$ if an e_g electron is present, $n_{ie} = 1$, or simply S_t otherwise. The unification of band and local spin subspaces implies spin-charge separation. That is, the spin component $b_{i\sigma}$ of the e_g electron $e_{i\sigma\alpha} = b_{i\sigma}c_{i\alpha}$ is decoupled and "absorbed" by the total spin, and we are left with a charged fermion $c_{i\alpha}$ carrying the orbital index. At $T \ll T_C$, the Schwinger boson $b_{i\downarrow}$ simply becomes a part of the magnon operator b_i , namely $b_{i\downarrow} = b_i/(2S)^{1/2}$, while $b_{i\uparrow}$ is almost condensed, $b_{i\uparrow} = (n_{ie} - n_{i\downarrow})^{1/2} \approx 1 - b_i^{\dagger}b_i/4S$. Hereafter, $S = S_t + \frac{1}{2}$. Further, we keep the relevant leading 1/S terms only and assume small doping x. The kinetic energy then reads

$$H_{\rm kin} = -\sum_{\langle ij\rangle_{\gamma}} t_{\gamma}^{\alpha\beta} c_{i\alpha}^{\dagger} c_{j\beta} + \frac{1}{2S} \sum_{\langle ij\rangle_{\gamma}} t_{\gamma}^{\alpha\beta} \times c_{i\alpha}^{\dagger} c_{j\beta} \left(\frac{1}{2} b_{i}^{\dagger} b_{i} + \frac{1}{2} b_{j}^{\dagger} b_{j} - b_{i}^{\dagger} b_{j} \right) + \text{H.c.}$$
 (2)

The first term here describes the fermionic motion in a ferromagnetic background (yet this motion is strongly correlated in the presence of orbital disorder [7,8]), while the second term controls the spin dynamics and spin-fermion interaction. The latter term would come out from a spin-wave expansion of an effective Heisenberg model $J_{\text{DE}}(S_iS_j)$ with $J_{\text{DE}} = (2S^2)^{-1}t_{\gamma}^{\alpha\beta}\langle c_{i\alpha}^{\dagger}c_{j\beta}\rangle$ if one considers the fermionic sector on average as in meanfield treatments of the DE model. However, the bond variable $c_{i\alpha}^{\dagger}c_{j\beta}$ is a fluctuating complex quantity and the spin structure of Eq. (2) is therefore not of Heisenberg form. Explicitly $(T \ll T_C)$:

$$H_{\rm kin} = -\sum_{\langle ij\rangle_{\gamma}} t_{\gamma}^{\alpha\beta} c_{i\alpha}^{\dagger} c_{j\beta}$$

$$\times \left[\frac{3}{4} + \frac{1}{4S^2} \left(S_i^z S_j^z + S_i^- S_j^+ \right) \right] + \text{H.c.}$$
 (3)

In the classical limit for spins, one recovers from Eq. (3) the effective fermionic model with phase-dependent hopping [9–11]. In addition to the above peculiarities, the band/local duality of spin in the DE system further results in the following important point: Going to momentum representation in Eq. (2) one immediately realizes that the magnon-fermion interaction vertex does not vanish at zero-momentum transfer. What is wrong? The boson b_i should not be regarded as a physical magnon. The true Goldstone particle of the DE model is the following object with both local spin and itinerant features:

$$B_{i} = b_{i} \left[n_{ic} + \sqrt{\frac{2S - 1}{2S}} (1 - n_{ic}) \right]$$

$$\approx b_{i} - \frac{1}{4S} (1 - n_{ic}) b_{i}. \tag{4}$$

The composite character of the physical magnon B_i is the price one has to pay for spin-charge separation and for the rearrangement of the original Hilbert space. The itinerant component of B_i is of order 1/S only. However, the spin stiffness is itself of the same order, and the 1/S correction in Eq. (4) is of crucial importance to ensure spin dynamics consistent with the Goldstone theorem. Now, commuting Eq. (4) with Eq. (2) one finds the mean-field magnon dispersion ω_p and the correct momentum structure of the magnon-fermion scattering vertex:

$$[B_{\mathbf{p}}, H] = \omega_{\mathbf{p}} B_{\mathbf{p}} + \frac{t}{2S} \sum_{\mathbf{q}} A_{\mathbf{p}}^{\alpha\beta}(\mathbf{k}) c_{\mathbf{k}\alpha}^{\dagger} c_{\mathbf{k}-\mathbf{q},\beta} B_{\mathbf{p}+\mathbf{q}}, \quad (5)$$
$$A_{\mathbf{p}}^{\alpha\beta}(\mathbf{k}) = \gamma_{\mathbf{k}}^{\alpha\beta} - \gamma_{\mathbf{k}+\mathbf{p}}^{\alpha\beta}.$$

Here, $\omega_{\mathbf{p}} = zD_s(1-\gamma_{\mathbf{p}})$, $D_s = J_{\rm DE}S$, $J_{\rm DE}$ is defined above, z = 6, and the form factors $\gamma_{\mathbf{k}} = z^{-1} \sum_{\delta} \exp(i\mathbf{k}\delta)$, $\gamma_{\mathbf{k}}^{\alpha\beta} = (zt)^{-1} \sum_{\delta} t_{\delta}^{\alpha\beta} \exp(i\mathbf{k}\delta)$. The physics behind the second term in Eq. (5) is the temporal fluctuations of the "exchange constant" due to the charge and orbital dynamics. From now on, the conventional diagrammatic method with bare magnon-fermion vertex given in Eq. (5) can be used.

Now we turn to the correlations in the fermionic band. We separate the *charge* and *orbital* degrees of freedom by the parameterization $c_{i\alpha} = h_i^{\dagger} f_{i\alpha}$, where the slave boson h_i and the fermion $f_{i\alpha}$ represent the density and orbital fluctuations, respectively [8]. Further, approximating $\delta(c_{i\alpha}^{\dagger}c_{j\beta}) = \langle h_j^{\dagger}h_i \rangle f_{i\alpha}^{\dagger}f_{j\beta} + \langle f_{i\alpha}^{\dagger}f_{j\beta} \rangle h_j^{\dagger}h_i$, one finds from Eq. (5) two different contributions to the magnon self energy.

Superexchange.— At low dopings, the virtual charge transfer across the Hubbard gap becomes of importance. In limit of large J_H , transitions to the high-spin intermediate state with energy $U_1 = (U' - J_H) \ll U', U$ dominate. The corresponding superexchange Hamiltonian is then obtained to be:

$$H_{\text{SE}} = -J_{\text{SE}} \sum_{\langle ij \rangle_{\gamma}} \left[\mathbf{S}_{i} \mathbf{S}_{j} + S(S+1) \right] \left(1 - \tau_{i}^{\gamma} \tau_{j}^{\gamma} \right). \quad (6)$$

Here, $J_{\text{SE}} = (t^2/U_1)[2S(2S+1)]^{-1}$ and $\tau^{x/y} = (\sigma^z \pm \sqrt{3}\sigma^x)/2$, $\tau^z = \sigma^z$ with Pauli matrices $\sigma^{x/z}$ acting on orbital subspace f_α . Eq. (6) is the generalization of orbitally degenerate superexchange models [6,12] for arbitrary values of spin. Superexchange is of ferromagnetic nature because the $J_H \to \infty$ limit is assumed, and the exchange strength depends on orbital orientations [13]. In an orbitally disordered state one can represent the orbital part of Eq. (6) in terms of fluctuating bond operators $f_{i\alpha}^{\dagger} f_{j\beta}$ [8]. Then the effect of superexchange is simply to add a new term

$$A_{\mathbf{p}}^{\alpha\beta}(\mathbf{k}, \mathbf{q}) = x_0 \left(\gamma_{\mathbf{k}}^{\alpha\beta} + \gamma_{\mathbf{k} - \mathbf{q}}^{\alpha\beta} - \gamma_{\mathbf{k} + \mathbf{p}}^{\alpha\beta} - \gamma_{\mathbf{k} - \mathbf{q} - \mathbf{p}}^{\alpha\beta} \right)$$
(7)

to the scattering amplitude in Eq. (5) and to renormalize $D_s \to (J_{\rm DE} + J_{\rm SE})S = t\chi_0(x+x_0)/2S$. Here the constant $x_0 = 2\chi_0 t/U_1$ with mean-field parameter $\chi_0 = \langle f_{i+c}^\dagger f_i \rangle \approx \frac{1}{2}(1-x)$ defines the effective doping level below which the superexchange contribution becomes of importance.

To summarize up to now: We have developed a quantum theory of the double-exchange model at $T < T_C$ which also includes the correlation effects present in transition metal oxides. The obvious advantage of this approach over earlier treatments [3,4] is that the theory has a transparent structure adjusted to describe the lowenergy spin dynamics, and the large atomic scale J_H does not appear in the calculations, either. Yet the corrections t/J_H can be accounted for perturbatively, if necessary.

Indirect magnon-phonon coupling via orbital sector.— An important piece of physics relevant to the experiment [1] is still missed in model (1), that is the Jahn-Teller orbital-lattice coupling [14]. This can be written as:

$$H_{\rm JT} = -g_0 \left(Q_{2i} \sigma_i^x + Q_{3i} \sigma_i^z \right), \tag{8}$$

where Q_2 and Q_3 are the distortions of appropriate symmetry [6]. The deformation energy including intersite correlations is given by

$$H_{\rm ph} = \frac{1}{2} K \sum_{i} \mathbf{Q}_{i}^{2} + K_{1} \sum_{\langle ij \rangle_{\gamma}} \tilde{Q}_{3i}^{\gamma} \tilde{Q}_{3j}^{\gamma}, \tag{9}$$

with $\tilde{Q}_3^{x/y} = (Q_3 \pm \sqrt{3}Q_2)/2$, $\tilde{Q}_3^z = Q_3$, and $\mathbf{Q} = (Q_2, Q_3)$. In general, the JT interaction strongly mixes the orbital and lattice dynamics, leading to a fluctuation of exchange bonds at low (phonon) frequencies. Here, we treat this problem only perturbatively as shown in Fig. 2. We arrive at the following effective spin-phonon Hamiltonian:

$$H_{\text{s-ph}} = -\sum_{pq} (g_{pq}Q_{-q}) B_p^{\dagger} B_{p+q}. \tag{10}$$

The coupling constants $g_{pq}^{(\alpha)} = g_0 a_0 (\eta_q^{(\alpha)} - \eta_p^{(\alpha)} - \eta_{p+q}^{(\alpha)}) / S$, where $\eta_q^{(2)} = -\sqrt{3}(c_x - c_y)/2$, $\eta_q^{(3)} = c_z - \frac{1}{2}c_x - \frac{1}{2}c_y - \frac{1}{2}c$




FIG. 2. Effective spin-phonon coupling. Perturbatively, it is controlled by the orbital susceptibility (fermion bubble), Jahn-Teller (open dot $\propto g_0$) and double-exchange (filled dot $\propto t$) interaction vertices.




FIG. 3. Magnon self energies.

 $\frac{1}{2}c_y$, $c_\alpha \equiv \cos q_\alpha$, and the parameter $a_0 = t(x + x_0)\langle (f_{i+c}^{\dagger}f_i)(\sigma_i^z)\rangle_{\omega=0}$.

Magnon self energies— We are now in the position to calculate the renormalization of the magnon dispersion. The leading $1/S^2$ corrections are shown in Fig. 3. Charge and orbital susceptibilities in Figs. 3(a) and 3(b), respectively, are calculated using mean-field Green's functions in slave boson h and fermion f subspaces. For the spectral density of JT phonons in Fig. 3(c) we use

$$\rho_{\pm}^{\rm ph}(\omega, \mathbf{q}) = \frac{1}{\pi} \frac{\omega}{\omega_{\mathbf{q}}^{\pm}} \frac{\Gamma}{(\omega - \omega_{\mathbf{q}}^{\pm})^2 + \Gamma^2}$$
(11)

accounting phenomenologically for the damping Γ due to coupling to orbital fluctuations. The phonon dispersions $\omega_{\mathbf{q}}^{\pm} = \omega_0^{\mathrm{ph}} [\kappa_{1\mathbf{q}} \pm (\kappa_{2\mathbf{q}}^2 + \kappa_{3\mathbf{q}}^2)^{1/2}]^{1/2}$ with $\omega_0^{\mathrm{ph}} = (K/M)^{1/2}$ follow from Eq. (9). Here, $\kappa_{1\mathbf{q}} = 1 + k_1(c_x + c_y + c_z)$, $\kappa_{2\mathbf{q}} = k_1 \eta_{\mathbf{q}}^{(2)}, \ \kappa_{3\mathbf{q}} = k_1 \eta_{\mathbf{q}}^{(3)}, \ \text{and} \ k_1 = K_1/K.$ The expressions obtained from the diagrams in Fig. 3 contain summations over momentum space which we perform numerically. We find the effect of charge fluctuations on the magnon spectrum to be quite featureless and moderate (see Fig. 4), which is due to the fact that the spectral density of charge fluctuations lies well above the magnon band. On contrary, the relatively low-energy fluctuations of the orbital and lattice degrees of freedom are found to affect the spin-wave dispersion in a peculiar way, particularly in (0,0,q) and (0,q,q) directions. Fig. 4 shows the magnon dispersion. The hopping amplitude t = 0.4 eVis chosen to fit the spin stiffness in Pr_{0.63}Sr_{0.37}MnO₃; further we use $U_1 = 4 \text{ eV}$ [12]. The phonon contribution depends on the quantity $(g_0a_0)^2/2K \equiv E_{\rm JT}a_0^2$. We set $E_{\rm JT}a_0^2 = 0.004$ eV [15], $\omega_0^{\rm ph} = 0.08$ eV [16], $\Gamma = 0.04$ eV. Our key observation is the crucial effect of intersite correlations of JT distortions, controlled by k_1 , on the magnon dispersion (see Fig. 5). To explain the experimental data [1] we are forced to assume ferro-type correlations $(k_1 < 0)$. We interpret this surprising result

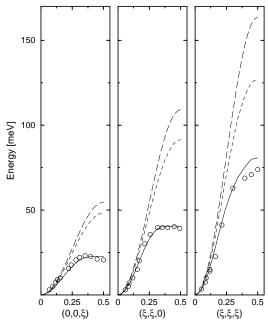


FIG. 4. Magnon dispersion along $(0,0,\xi)$, $(\xi,\xi,0)$, and (ξ,ξ,ξ) directions, where $\xi=0.5$ at the zone boundary. Solid lines represent the theoretical result including charge, orbital, and lattice effects and are fitted to experimental data [1] denoted by circles. For comparison the bare dispersion and the one including only charge effects are indicated by long-dashed and dashed lines, respectively. The parameter $k_1=-0.33$.

in the following way: Conventionally $k_1 > 0$ corresponding to AF order of JT distortions and orbitals is expected in undoped compounds [6]. However, in the doped case charge mobility prefers a ferro-type local orientation of orbitals which minimizes the kinetic energy. This competition between JT and kinetic energies can be simulated by tuning k_1 . At large enough doping, ferro-type orbital correlations are expected to prevail, hence effectively $k_1 < 0$. In fact, a ferro-type ordering of orbitals leading to a layered AFM spin structure is experimentally observed [17,18] at dopings about x = 0.5. As this instability is approached, low-energy, quasi static fluctuations of exchange bonds develop, yielding a magnon evolution as shown in Fig. 5. Remarkably, the small q spin stiffness is not affected by this physics, while a strong reduction of T_C by soft magnons at the zone boundary is predicted. This explains the origin of the anomalous enhancement of the D_s/T_C ratio in low- T_C manganites [19].

In summary, we have presented a theory of spin dynamics in a model relevant to manganites, emphasizing particularly the interplay between double-exchange physics and orbital-lattice dynamics. The unusual magnon dispersion in lower- T_C compounds is explained as due to the proximity to orbital-lattice ordering. Apparently, strongly correlated orbital fluctuations play a crucial role in the physics of manganites.

We would like to thank H. Y. Hwang for stimulating discussions.

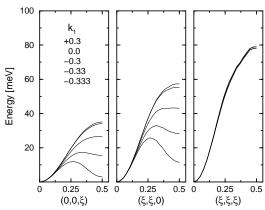


FIG. 5. Magnon dispersion for different values of k_1 . $E_{\rm JT}a_0^2=0.006$ eV is used. The softening enhances as $k_1\to -\frac{1}{2}$ corresponding to ferro-type orbital-lattice order.

- [1] H. Y. Hwang et al., Phys. Rev. Lett. 80, 1316 (1998).
- [2] C. Zener, Phys. Rev. 82, 403 (1951); P. W. Anderson and H. Hasegawa, *ibid.* 100, 675 (1955); P.-G. de Gennes, *ibid.* 118, 141 (1960).
- [3] K. Kubo and N. Ohata, J. Phys. Soc. Jpn. 33, 21 (1972).
- [4] N. Furukawa, J. Phys. Soc. Jpn. **65**, 1174 (1996).
- [5] T. G. Perring et al., Phys. Rev. Lett. 77, 711 (1996).
- [6] K. I. Kugel and D. I. Khomskii, Sov. Phys.-Usp. 25, 231 (1982).
- [7] S. Ishihara, M. Yamanaka, and N. Nagaosa, Phys. Rev. B 56, 686 (1997).
- [8] R. Kilian and G. Khaliullin, Phys. Rev. B 58, R11 841 (1998).
- [9] E. Müller-Hartmann and E. Dagotto, Phys. Rev. B 54, R6819 (1996).
- [10] A. J. Millis, P. B. Littlewood, and B. I. Shraiman, Phys. Rev. Lett. 74, 5144 (1995).
- [11] It is noticed that the phase-dependent part of the fermionic hopping is only of order 1/S (see Eq. (2)).
- [12] L. F. Feiner and A. M. Oleś, Phys. Rev. B 59, 3295 (1999).
- [13] The effect of superexchange-bond fluctuations on the magnon spectrum in the antiferromagnetic Kugel-Khomskii model was recently studied in G. Khaliullin and V. Oudovenko, Phys. Rev. B **56**, R14 243 (1997).
- [14] A. J. Millis, b. I. Shraiman, and R. Mueller, Phys. Rev. Lett. 77, 175 (1996).
- [15] A mean-field calculation gives $a_0 \approx 0.1$. Our fitting then implies a reasonable Jahn-Teller binding energy $E_{\rm JT} \approx 0.4$ eV.
- [16] This number is consistent with optical reflectivity data in Y. Okimoto et al., Phys. Rev. Lett. 75, 109 (1995).
- [17] H. Kawano et al., Phys. Rev. Lett. 78, 4253 (1997).
- [18] Y. Moritomo et al., Phys. Rev. B 58, 5544 (1998).
- [19] J. A. Fernandez-Baca et al., Phys. Rev. Lett. 80, 4012 (1998).