

Orbital character of O $2p$ unoccupied states near the Fermi level in CrO_2

C. B. Stagarescu,[†] X. Su, and D. E. Eastman

James Franck Institute, The University of Chicago, 5640 South Ellis Avenue, Chicago, Illinois 60637

K. N. Altmann and F. J. Himpsel

Department of Physics, University of Wisconsin Madison, 1150 University Avenue, Madison, Wisconsin 53706-1390

A. Gupta

IBM T. J. Watson Research Center, Yorktown Heights, New York 10598

(July 5, 2021; submitted for publication, October 12, 1999)

The orbital character, orientation, and magnetic polarization of the O $2p$ unoccupied states near the Fermi level (E_F) in CrO_2 was determined using polarization-dependent X-ray absorption spectroscopy (XAS) and X-ray magnetic circular dichroism (XMCD) from high-quality, single-crystal films. A sharp peak observed just above E_F is excited only by the electric field vector (\mathbf{E}) normal to the tetragonal c -axis, characteristic of a narrow band (≈ 0.7 eV bandwidth) constituted from O $2p$ orbitals perpendicular to c (O $2p_y$) hybridized with Cr $3d_{xz-yz}$ t_{2g} states. By comparison with band-structure and configuration-interaction (CI) cluster calculations our results support a model of CrO_2 as a half-metallic ferromagnet with large exchange-splitting energy ($\Delta_{exch-split} \approx 3.0$ eV) and substantial correlation effects.

Half-metallic ferromagnets are materials exhibiting metallic character for the majority-spin electrons but a semiconducting gap for the minority-spin electrons.¹ Correspondingly, one expects complete spin polarization at the Fermi level, making this class of materials ideal for spin-polarized emitters to be used in magnetic tunneling applications such as magnetic random access memory^{2,3} or spin-polarized scanning tunneling microscopy.⁴ CrO_2 is a ferromagnetic metal with a Curie temperature of $T_C \approx 390$ K. Recently, it has generated substantial interest⁵⁻¹⁰ because its band structure has been predicted to be half-metallic.^{6,7,11} Point contact spectroscopy measurements of a spin polarization of about 90% have been reported recently,⁹ providing experimental indication of its half-metallic character.

Recent advances¹² have made possible the growth of high-quality, epitaxial thin films of CrO_2 by chemical vapor deposition. Samples used in our experiment were as-prepared 4000 Å thick CrO_2 films grown on (100) TiO_2 substrates. X-ray diffraction indicated that the films were single phase and the CrO_2 in-plane $\langle 100 \rangle$ and $\langle 001 \rangle$ (a_{\parallel} and c) axes were aligned with the respective axes of the TiO_2 substrate. The third axis, crystallographically equivalent to a_{\parallel} and normal to the surface of the films, will be denoted as a_{\perp} . The films exhibited a sharp ferromagnetic transition with a Curie temperature of about 393 K and a strong in-plane magnetic anisotropy with c and a_{\parallel} being the easy-axis and hard-axis directions, respectively. Cr_2O_3 spectra were taken from high-purity pressed-powder samples.¹³ Our experiments were performed at the high-resolution Hermon beamline¹⁴ of the University of Wisconsin-Madison Synchrotron Radiation Center. The XAS spectra were taken with a resolution of about 150 meV at 550 eV by measuring the total electron yield. The degree of linear polarization was 85-90%. The XMCD measurements

were taken with circularly polarized light ($\approx 80\%$) from CrO_2 samples in switching remnant magnetization along the easy-axis which was positioned horizontally and situated at 45° with respect to the direction of the incoming radiation.

To elucidate the spatial orientation and orbital character of the O $2p$ empty states we have employed polarization-dependent XAS measurements with linearly polarized light. The results are shown in Fig. 1(a). The CrO_2 spectrum displays a sharp peak (1) at ≈ 529.2 eV, followed by two other features (2) and (3) at energies of 2.3 and 3.4 eV higher. The sharp peak (1) exhibits a large intensity variation of $\approx 90\%$, with a maximum for the geometry with the electric field vector of the light \mathbf{E} arranged along a_{\parallel} (normal to the c -axis). As shown further in Fig. 1(b), the ϕ dependence of (1) follows accurately a $\cos^2(\phi)$ curve. Our fit to the data, together with the degree of linear polarization of 85-90%, gives an orientation of peak (1) perpendicular to the c -axis of more than 95%.¹⁵ The azimuthal dependence of the higher lying features (2) and (3) is considerably smaller exhibiting an excursion of about 28% between the 0° and 90° orientations. At the same time its sign is opposite to that of (1) which indicates a dominant contribution from O $2p$ states parallel to the c -axis.

The O K XAS polarization dependence has its origin in the orientation of the O $2p$ - Cr $3d$ hybrid states with respect to the crystalline axes. The building blocks of the CrO_2 's rutile structure are CrO_6 octahedra arranged along and slightly elongated in the direction of the tetragonal c axis. The O $2p$ - Cr $3d$ hybridization mechanism can be easily understood in a Goodenough molecular-orbital model electronic structure scheme.¹⁶ The ligand crystal-field splits the Cr $3d$ manifold into three t_{2g} and two e_g states. Due to the distinction between the $a_{\perp}(a_{\parallel})$ and the c -axes in the tetragonal rutile structure,

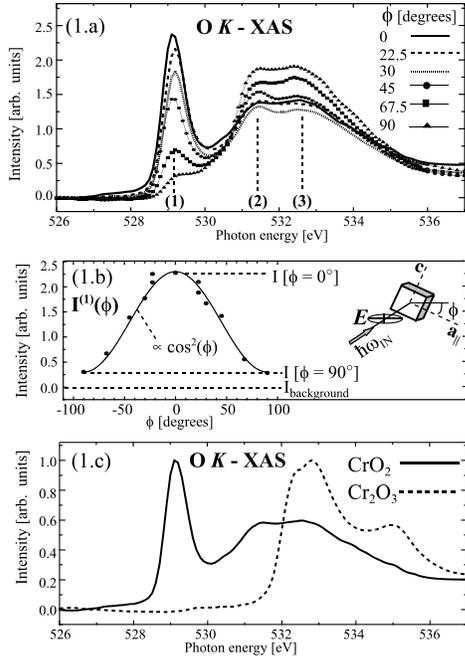


FIG. 1. (a). O K XAS of CrO_2 taken in a geometry with fixed polar angle between the c axis and the photon direction ($\theta=90^\circ$) and variable azimuthal angle (ϕ) between the photon direction and a_{\parallel} . (b). Intensity variation of the peak (1) with ϕ . The experimental geometry is shown in the inset. (c). Comparison of the O K XAS of CrO_2 and Cr_2O_3 .

the t_{2g} group of Cr $3d$ states undergoes a further, small degeneracy splitting into an orbital normal to the c -axis (d_{xz-yz}) and two other having non-zero c -axis projections (d_{xz+yz} and d_{xy}). Oxygen atoms are situated in a trigonal environment forming planar CrO_3 clusters with the three closest Cr atoms, with the planes of these CrO_3 clusters running parallel to the c axis and oriented at 45° with respect to the a_{\parallel} and a_{\perp} directions. This trigonal ligand environment of oxygen leads to two sp^2 combinations (O $2s$ and $2p_{x,y}$) with non-zero c -axis projections situated in the planes of the CrO_3 clusters and one remaining p state (O $2p_y$) that resides in the a_{\parallel} - a_{\perp} planes. The Cr d_{xz-yz} states are therefore properly oriented to lead to π -type bonding with the O $2p$ orbital which is perpendicular to the c -axis, i.e., O $2p_y$. Thus, the preceding analysis of the polarization dependence allows us to clearly identify peak (1) with empty states normal to the tetragonal c -axis formed by O $2p_y$ hybridized with Cr $3d_{xz-yz}$ t_{2g} . This result is confirmed by a recent band-structure calculation of CrO_2 which finds that in the first ≈ 2 eV above E_F the empty O $2p$ states are 100% oriented perpendicular to the c -axis.¹⁷

Even under normal pressure/temperature conditions CrO_2 (Cr^{4+}) undergoes a chemical reduction to Cr_2O_3 (Cr^{3+}) which is the stable oxidation state of Cr. For our samples, we estimated by tunneling measurements a Cr_2O_3 surface layer thickness of about 10 Å. We have addressed the issue of spectral contamination effects of the

native insulating surface layer by measuring O K XAS from Cr_2O_3 on the same experimental setup. The results are shown in Fig. 1(c). In contrast to CrO_2 , the Cr_2O_3 O K XAS spectrum displays significant intensity only above 532 eV having the highest intensity at about 532.8 eV. Therefore we can conclude that the energy region from 529 to about 532 eV in our CrO_2 O K XAS does not contain any spectral interference from the surface layer of Cr_2O_3 .

Our CrO_2 O K XAS spectra (peak (1) at 529.2 eV) have been taken with a resolution of 150 meV and an accuracy of the absolute photon energy scale of about ± 100 meV. Previously reported O K absorption energies for peak (1) taken from powder CrO_2 are of 527.0 eV¹⁰, 530.0 eV¹⁸, and ≈ 530.5 eV⁸. Our experience with measuring the CrO_2 and Cr_2O_3 absorption spectra suggests that these differences are due to monochromator absolute energy calibration errors rather than to sample differences. The previously reported CrO_2 O $1s$ x-ray photoemission (XPS) binding energy¹⁹, $E_B = 529.3$ eV, is 0.1 eV above the absorption peak (1). Taking into account the limited accuracies of the two measurements, an energy difference of 0.7 ± 0.3 eV remains between the O $1s$ XPS binding energy and the measured absorption edge at ≈ 528.6 eV, where we assume a 0.2 eV accuracy of the XPS measured binding energy.

The electron excited in the absorption process interacts with its environment which consists of the other valence electrons (correlation) and the positive charge of the core-hole (additional attractive potential). To understand the effect of these interactions on the absorption spectra we will compare our data with recent CI²⁰ and band structure calculations.^{6,7} The CI calculations start with a simplified model of a transition metal oxide as a MO_6 cluster formed by a transition metal (M, d^n) ion situated in the octahedral ligand field of six oxygen ions (O^{2-}). Then, the valence electronic structure is described by allowing for $d-d$ Hubbard charge transfer ($d^n d^n \rightarrow d^{n-1} d^{n+1}$), metal-ligand charge-transfer (e.g. $d^n \rightarrow d^{n+1} \underline{L}$ where \underline{L} = valence oxygen hole), and metal-ligand hybridization which results in a ligand-hole content in the ground-state. The oxygen K absorption spectrum is obtained by calculating the differences in total energy (and the strength of the transitions) between excited-states resulting from annihilation of a valence ligand-hole by addition of one electron to a mixed metal-oxygen state (e.g. $d^{n+1} \underline{L} \rightarrow d^{n+1}$). In Fig. 2 we compare the calculated CI oxygen XAS spectrum with the experimental spectra of two isoelectronic $3d^2$ oxides, CrO_2 (Cr^{4+}) and V_2O_3 (V^{3+}).²¹ First, there is a good similarity between the O K XAS spectra of the two $3d^2$ oxides which indicates that, due to strong $p-d$ hybridization, the O K edge absorption is mainly determined by the underlying $3d$ electronic structure. Second, a good correspondence is found between the three strongest CI transitions and the three most prominent experimental absorption features, which validates the choice of parameters used in the calculation.

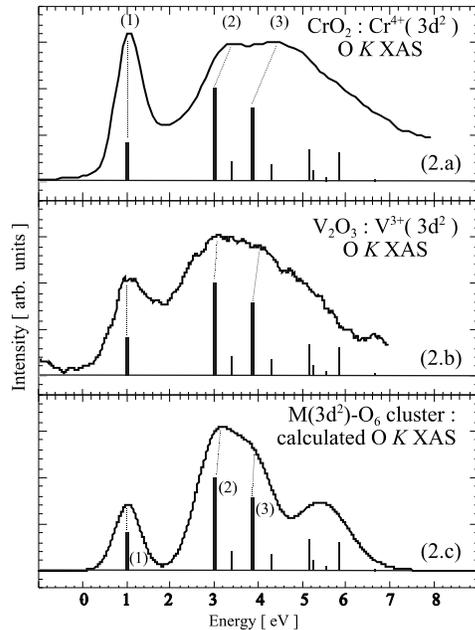


FIG. 2. Comparison between experimental and CI calculated O K absorption for $3d^2$ oxides. (a). CrO_2 O K XAS (spatially averaged, counting twice the doubly degenerate a -axis (a_{\parallel} , a_{\perp}) and once the c -axis). (b). V_2O_3 O K absorption spectrum (representative for V_2O_3 in the metallic state).²¹ (c). CI calculation.²⁰ The common energy scale is that of the CI spectrum, the first strong measured absorption features being aligned to the first CI excited state. For clarity the three strongest final states are shown with thicker lines and the discrete excitation spectrum is replotted in panels 2(a) and 2(b). The continuous curve in 2(c) was obtained from the discrete CI spectrum by a Gaussian convolution that simulates the effect of bandwidth broadening (0.7 eV at (1) and 1.0 eV for higher energies).

Finally, two contributions can be proposed as the origin of the small energy difference (≈ 0.4 eV) observed for the CrO_2 features (2) and (3) (Fig. 2(a)). First, a more accurate description of CrO_2 would have to incorporate the deviation of the ligand-field from octahedral symmetry due to the tetragonal crystal structure distortion. Second, the attractive core-hole potential (not included in the CI calculation) can, in principle, be expected to have a stronger effect (increased downward energy shift) on the narrow, more localized t_{2g} peak (1) than on the broader features (2) and (3).

The two band-structure calculations used in this study^{6,7} are both based on the local-spin-density approximation of the density-functional theory (LSDA). As far as the low-energy excitation spectrum is concerned (e.g. transport properties) both calculations agree in finding CrO_2 to be a half-metal with a low density of fully spin-polarized states at E_F . However the two calculations differ importantly in the values obtained for the exchange-splitting energy responsible

for ferromagnetism²² ($\Delta_{exch-split} \approx 3.0$ eV in Ref. 6, $\Delta_{exch-split} \approx 1.8$ eV in Ref. 7) and in the treatment of the on-site electron-electron correlation. In the LSDA approach of Lewis *et al.*⁷ the effects of electron-electron correlation are included in an averaged, mean-field way. In contrast, Korotin *et al.*⁶ use a LSDA scheme modified by the explicit inclusion of a potential correction²³ ($U=3$ eV) in order to account for the Coulomb interaction between localized d electrons.

We find a good similarity between the O K XAS and the envelope of the O $2p$ unoccupied DOS obtained by Korotin *et al.*, as can be observed by comparing spectra in panels (a) and (b) of Fig. 3. In particular, the amount of orbital overlap included in the calculation results in a band broadening consistent with the measured width (≈ 0.7 eV) of the O $2p_y$ - Cr $3d_{xz-yz}$ t_{2g} peak (1) (Fig. 3(a)). The two other O K XAS features, (2) and (3) at higher energies, correspond to local DOS maxima that have a mixed O $2p$ - Cr $3d$ e_g spin-up and O $2p$ - Cr $3d$ t_{2g} spin-down character. It becomes clear when looking at the theoretical spin-up/spin-down projected DOS in Fig. 3(c) and 3(d) that the essential parameter controlling the good agreement with the LSDA+U calculation (i.e. the appearance of a broad minimum in the empty DOS at ≈ 1.5 eV above E_F and of significant local maxima (2) and (3) at higher energies, as observed experimentally) is the large upward shift of the spin-down DOS ($\Delta_{exch-split} \approx 3.0$ eV). Our data are not well reproduced by the LSDA calculation⁷ which has $\Delta_{exch-split} \approx 1.8$ eV. This smaller exchange-splitting leads directly to a spin-down DOS filling in the region of the broad experimental minimum (≈ 1.5 eV above E_F) and to the presence of the other (higher energy) significant DOS features (mainly due to spin-down t_{2g} states) shifted closer to E_F , as seen in Fig. 3(e). An experimental $\Delta_{exch-split}$ can be determined in a "rigid band" approximation by slightly adjusting the (LSDA+U) exchange-splitting energy shift to fit our data (features (2) and (3)). This "DOS-fit" yields $\Delta_{exch-split} \approx 3.2$ eV. Given the uncertainties in this fitting²⁴ and experimental accuracies, we conclude that our data indicate a $\Delta_{exch-split} \approx 3.0$ eV. This is consistent with the LSDA+U calculation,⁶ in which a large $\Delta_{exch-split}$ was obtained as an explicit consequence of including a considerable correlation energy ($U=3$ eV). Thus, our experimental results supports the conclusion of the LSDA+U work⁶ that on-site correlation effects beyond the average LSDA value are present CrO_2 . Interestingly, we also observe that the correlation energy parameter U is consistent (same origin) for the LSDA+U calculation⁶ (obtained by the local-orbital expansion method described by Pickett *et al.*²³) and the CI calculation.^{20,25}

Finally, as the first empty oxygen states have been experimentally determined to be of O $2p_y$ origin, a substantial magnetic orbital polarization of these states is expected since their Cr $3d_{xz-yz}$ t_{2g} counterparts are fully spin-polarized (Fig. 3(d)). Indeed, we have measured a clear O K XMCD signal (not shown here), similar to

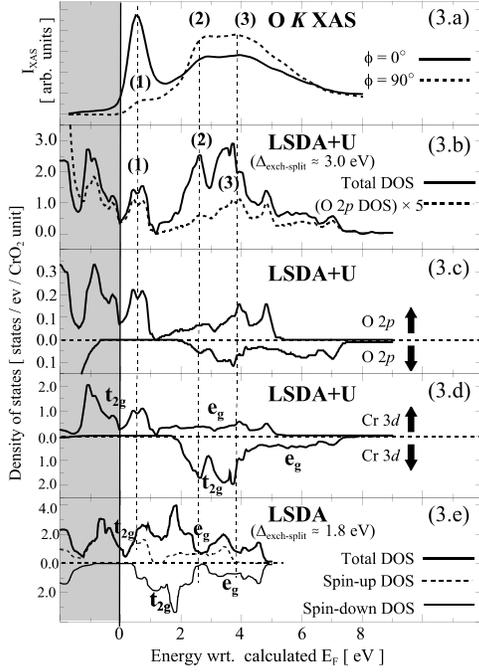


FIG. 3. Comparison of the CrO₂ O K XAS with calculated DOS. The theoretical DOS are plotted against their calculated binding energy scales. The XAS peak (1) is aligned to the isolated set of empty states (1) in the calculated DOS. (a). CrO₂ O K XAS for two azimuthal angles $\phi = 0^\circ$ and 90° . (b). Total DOS and O 2*p* partial DOS from the LSDA+U calculation of Korotin *et al.*⁶ (c, d). O 2*p* and Cr 3*d* spin resolved DOS from the same LSDA+U work.⁶ (e). Total, spin-up, and spin-down DOS from the LSDA calculation of Lewis *et al.*⁷

that obtained previously by Attenkofer *et al.*⁸ from polycrystalline CrO₂.

In conclusion, we used polarization-dependent XAS to determine the orbital character of the unoccupied O 2*p* states just above E_F in CrO₂ which are found to be O 2*p_y* states hybridized with Cr 3*d_{xz-yz}* *t_{2g}*, with a bandwidth of ≈ 0.7 eV. A large experimental exchange-splitting energy of $\Delta_{exch-split} \approx 3.0$ eV was estimated by comparison between our data and band-structure calculations. Our results support a model of CrO₂ as a half-metallic ferromagnet with substantial correlation effects.

The help of X. W. Li in growth of the sample and of M. Bissen and R. Hansen in setting the experiment is gratefully acknowledged. The authors thank M. A. Korotin for communicating his results prior to publication. One of the authors (C. B. S.) thanks G. A. Sawatzky and D. I. Khomskii for useful discussions. This work was supported in part by the DOE under Contract W-31-109-ENG-38. The Synchrotron Radiation Center, UW-Madison, is supported by the NSF under Award No. DMR-9531009.

[†] Author to whom correspondence should be addressed (electronic mail: c-stagarescu@uchicago.edu).

- ¹ R. A. de Groot, F. M. Mueller, P. G. van-Engen, and K. H. J. Buschow, Phys. Rev. Lett. **50**, 2024 (1983).
- ² W. J. Gallagher *et al.*, J. Appl. Phys. **81**, 3741 (1997).
- ³ J. M. Daughton, J. Appl. Phys. **81**, 3758 (1997).
- ⁴ R. Wiesendanger *et al.*, Phys. Rev. Lett. **65**, 247 (1990).
- ⁵ J. M. D. Coey *et al.*, Phys. Rev. Lett. **80**, 3815 (1998); H. Y. Hwang and S.-W. Cheong, Science **278**, 1607 (1997); I. I. Mazin, D. J. Singh, and C. Ambrosch-Draxl, Phys. Rev. B **59**, 411 (1999).
- ⁶ M. A. Korotin, V. I. Anisimov, D. I. Khomskii, and G. A. Sawatzky, Phys. Rev. Lett. **80**, 4305 (1998).
- ⁷ S. P. Lewis, P. B. Allen, and T. Sasaki, Phys. Rev. B **55**, 10253 (1997).
- ⁸ K. Attenkofer and G. Schütz, J. Phys. IV France **7**, C2-459 (1997).
- ⁹ R. J. Soulen *et al.*, Science **282**, 85 (1997).
- ¹⁰ T. Tsujioka, T. Mikoza, J. Okamoto, and A. Fujimori, Phys. Rev. B **56**, R15509 (1997).
- ¹¹ K. Schwarz, J. Phys. F **16**, L211 (1986).
- ¹² X. W. Li, A. Gupta, and G. Xiao, Appl. Phys. Lett. **75**, 713 (1999); X. W. Li *et al.*, J. Appl. Phys. **85**, 5585 (1999).
- ¹³ Alfa Aesar, Chromium(III) oxide, 99%.
- ¹⁴ M. Bissen *et al.*, Rev. Sci. Instrum. **66**, 2072 (1995).
- ¹⁵ Label **E** used in the inset of Fig. 1(b) denotes the dominant, horizontal component (\mathbf{E}_{\parallel}) of the electrical vector. Due to the incomplete linear polarization (85-90%) a small, vertical component (\mathbf{E}_{\perp}) was also present which accounts to within 5% for the leftover intensity of peak (1) at $\phi=90^\circ$.
- ¹⁶ J. B. Goodenough, in Prog. Sol. State Chem. **5**, 145 (1971); P. I. Sorantin and K. Schwarz, Inorg. Chem. **31**, 567 (1992) (Note that the *x, y, z* subscripts attached to the *d* and *p* orbitals denote local coordinates in the CrO₆ octahedra and not the crystalline directions); B. L. Chamberland, CRC Crit. Rev. Sol. State Mat. Sci. **7**, 1 (1977).
- ¹⁷ M. A. Korotin *et al.* (unpublished) and G.A. Sawatzky (private communication).
- ¹⁸ Th. Schedel-Niedrig, Th. Neisius, C. T. Simmons, and K. Köhler, Langmuir **12**, 6377 (1996).
- ¹⁹ I. Ikemoto *et al.*, J. Solid State Chem. **17**, 425 (1976).
- ²⁰ J. van Elp and A. Tanaka, Phys. Rev. B **60**, 5331 (1999).
- ²¹ O. Müller *et al.*, Phys. Rev. B **56**, 15056 (1997).
- ²² The LSDA work (Ref. 7) gives $\Delta_{exch-split}=1.8$ eV. For the LSDA+U calculation, we have estimated $\Delta_{exch-split} \approx 3.0$ eV by measuring the energy between the “centers of mass” of the distinct Cr 3*d t_{2g}* spin-up/spin-down DOS.
- ²³ W. E. Pickett, S. C. Erwin, and E. C. Ethridge, Phys. Rev. B **58**, 1201 (1998)
- ²⁴ If the apparent increase in the (1)-(2) energy separation (Fig. 2) is confirmed (e.g by comparison with a more accurate CI calculation) to be a core-hole effect, $\Delta_{exch-split}$ would need to be corrected to ≈ 2.8 eV.
- ²⁵ J. van Elp *et al.*, Phys. Rev. B **44**, 1530 (1991)