

All taper coupled microspherical light source

Danny G. O'Shea^{1,2}, Jonathan M. Ward^{2,3}, Brian J. Shortt^{2,3}, Michel Mortier⁴,

Patrice Féron⁵ and S  le Nic Chormaic^{1,2,3}

¹Physics Department, National University of Ireland, University College Cork, Ireland

²Tyndall National Institute, Prospect Row, Cork, Ireland

*³Department of Applied Physics and Instrumentation, Cork Institute of Technology,
Bishopstown, Cork, Ireland*

*⁴Laboratoire de Chimie de la Mati  re Condens  e de Paris, ENSCP, 11 rue Pierre et Marie
Curie, 75005 Paris, France*

*⁵ENSSAT-FOTON (CNRS-UMR 6082) Universit   de Rennes 1, 6 rue de Kerampont, BP 80518,
22305 Lannion Cedex, France*

We present initial results on the realization of an all taper coupled multicolor microspherical glass light source fabricated from the erbium doped fluoride glass ZBLALiP. Whispering gallery mode lasing and upconversion processes give rise to laser and fluorescent emissions at multiple wavelengths from the ultraviolet to the infrared. A single-mode tapered fiber coupling scheme, which serves to both launch pump light at 980 nm into the microresonator cavity and collect the resulting infrared lasing, is employed. We demonstrate the use of a second separate fiber taper to outcouple the upconversion spectrum over several hundred nanometers. Thirteen discrete emissions ranging from 320 to 850 nm have been observed in the upconversion spectrum. The processes responsible for the generation of the observed wavelengths are outlined.

OCIS codes: 000.1600, 140.3380, 140.3500, 160.2540, 300.6280

In recent years, much effort has been devoted to the exploitation of upconversion mechanisms in rare-earth ion doped materials to yield a range of wavelengths from near infrared to ultraviolet. One such class of device which has shown interesting optical properties is the rare-earth doped microspherical whispering gallery mode laser.^{1,2} These miniature resonant cavities offer appealing advantages for applications in laser engineering due to their small size of several tens of microns in diameter, high-Q whispering gallery modes reaching 10^{10} and small mode volumes.³ The close proximity of numerous energy levels in triply-ionized rare earth ions is advantageous for obtaining fluorescence through various upconversion mechanisms such as excited state absorption (ESA), energy transfer upconversion (ETU) and photon avalanche (PA).⁴ This combination of interesting active medium and resonant cavity has resulted in much research focusing on the characterization of doped microspheres. We report here on the realization of an all taper coupled multiwavelength microspherical light source based on the upconversion emissions from an erbium-doped ZBLALiP ($\text{ZrF}_4\text{-BaF}_2\text{-LaF}_3\text{-AlF}_3\text{-LiF-PbF}_2$) fluoride glass microsphere. Emissions from the ultraviolet to the infrared are observed and outcoupled and in particular we report, to the best of our knowledge, the first observation of 320 nm upconversion emission following 980 nm pumping of Er^{3+} and the first use of a fiber taper to outcouple the upconversion spectrum over several hundred nanometers.

The Er:ZBLALiP (refractive index 1.49 at 1550 nm) microspheres studied for this work contain erbium at a concentration of 0.2 mol%, which equates to $4 \times 10^{19} \text{ Er}^{3+} \text{ ions/cm}^3$. It should be noted that, at this concentration, energy transfer (ET) is not expected to play a major role and as such excited state absorption (ESA) is the dominant mechanism in the upconversion process.⁵ Nevertheless, due to the non-trivial problem of distinguishing the two mechanisms, some authors

have suggested that ET may play a role even when the dopant concentration is below the critical value of about 1 mol%.^{6,7,8} A systematic study to distinguish between the two will be presented in a future paper and we suggest here the most likely transitions responsible for the observed spectrum. The suitability of fluoride glasses as rare-earth host materials has long been known⁹ as their low phonon energies determine multiphonon relaxation rates and, ultimately, the efficiency of upconversion processes. The material studied here has improved stability with respect to similar fluorozirconate glasses and has been shown by Mortier *et al.*¹⁰ to be an excellent host for rare-earth ions.

In our work, the C-band lasing characteristics and upconversion spectrum have been investigated at room temperature using a single mode 980 nm laser diode pump with a spectral width of about 1 nm and under CW pumping conditions. A detailed description of the experimental approach is given elsewhere.¹¹ To achieve efficient coupling of the pump into the microsphere and efficient collection of the infrared lasing spectrum, a 1550 nm SMF-28 fiber was adiabatically tapered to 1 μ m diameter using a direct heating technique.¹² The transmission loss of these tapers is typically less than 0.1 dB/cm. Optimum mechanical alignment of the taper and microsphere is achieved by traversing the microsphere to different locations along the taper until the microsphere emission spectrum about 1550 nm is maximized. This spectrum is recorded by connecting one end of the pump fiber taper to an optical spectrum analyzer. The transmission through the pump fiber is also monitored during the alignment and typically 10–15 % of the pump light is coupled into the microsphere. This coupling efficiency is in part due to the broad spectral nature of the pump laser relative to the whispering gallery mode resonances of the microsphere and can be improved by the use of a narrow linewidth pump source.¹³ Characteristic whispering gallery mode bands about the sphere equator are also observed. The

upconversion spectrum is detected in two ways. The first is via the use of a second fiber taper located on the microsphere equator diametrically opposed to the pump fiber taper, as shown in the inset to Fig. 1. This detection fiber taper is non-adiabatic, $2\ \mu\text{m}$ diameter, fabricated from multimode fiber (Thorlabs AFS50/125Y) and is connected to a spectrometer with $0.4\ \text{nm}$ spectral resolution. We employ the two taper system as it enables us to simultaneously detect the lasing emissions about $1550\ \text{nm}$ via the pump taper and the upconversion emissions via the second multimode fiber taper. This technique allows us to study the competition between both sets of processes. The second method relies on the use of a high numerical aperture fiber coupled spectrometer to detect the free space scattering spectrum from the microsphere.

Successful excitation of the ${}^4\text{I}_{13/2} \rightarrow {}^4\text{I}_{15/2}$ transition results in whispering gallery mode lasing resonances within the microsphere as shown in Fig. 1. The microsphere eccentricity, given by $\varepsilon = (\Delta\omega_{\text{ecc}}/\omega_{nml}) \cdot (l^2/|m| - 1/2)$ where l and m are the angular mode numbers, and ω_{nml} is the angular frequency of the mode, is calculated to be $\sim 2.1\ \%$ for $l = |m|$ with corresponding azimuthal mode splitting, $\Delta\omega_{\text{ecc}}$, of $\sim 11\ \text{GHz}$. Analysis of the lasing peaks enables us to measure the free spectral range (FSR), ν_{FSR} , between successive mode groups with difference in angular mode number l of 1, to be $\sim 7.8\ \text{nm}$ ($0.97\ \text{THz}$). This agrees closely with the calculated value of $\nu_{\text{FSR}} = c/\pi ND \sim 7.9\ \text{nm}$ ($0.96\ \text{THz}$), indicating a microsphere diameter, $D \approx 66\ \mu\text{m}$ as expected. It can be seen that each group of modes contains four distinct lasing peaks which are thought to be due to the excitation of multiple radial modes in the sphere. The peak power of a single outcoupled lasing peak presented here is $\sim 30\ \text{nW}$, which is about a factor of 10 less than the maximum observed by us. The spacing between TE and TM modes ($\nu_{\text{TE/M}}$) in Fig. 1 ($6.8\ \text{nm}$) also agrees well with the calculated value of $6.4\ \text{nm}$. The loaded cavity Q is typically $2\text{--}5 \times 10^4$

and is measured as the FWHM of an individual lasing peak. This value is limited by the finite spectrometer resolution of 0.07 nm.

The Er:ZBLALiP upconversion spectrum recorded coincidently to the lasing spectrum (Fig. 1) is shown in Fig. 2. Thirteen discrete peaks have been noted in the scattering spectrum (Fig. 2(a)) and numbered from T1-T13. Approximately 700 μ W of 980 nm pump light was coupled into the microsphere. The detection efficiency of the upconversion outcoupling taper has not been optimized, and this combined with increased fiber attenuation towards wavelengths shorter than about 500 nm, results in transitions T1 and T5 not being resolved in the taper spectrum (Fig. 2(b)). The transitions have initially been identified on the basis of the erbium energy level diagram shown in Fig. 3 and on the accepted Er³⁺ emission wavelengths in the literature. The centre wavelength associated with each transition is shown in Fig. 3. Further understanding of the transition(s) responsible for a particular wavelength can be obtained by the intensity dependence behavior of the fluorescence at a particular wavelength. In the case of ESA, the dependence of the fluorescence intensity upon pump power usually exhibits a simple power law dependence with slope n equal to the number of photons absorbed. Preliminary measurements have, for example, yielded a slope corresponding to $n = 1.5$ for transitions 6 (T6) and 7 (T7) whereas a slope of 2 is expected. This can be understood as depletion of the ⁴I_{15/2} ground state.¹⁴ The limited resolution of the spectrometer used to study the upconversion combined with the smaller microsphere FSR at shorter wavelengths means that the whispering gallery mode structure is only visible for emissions at wavelengths longer than about 800 nm. The mode structure for the 849 nm (T13) emission is distinguishable in the inset of Fig. 2(a).

Our results demonstrate a broad range of emission from 320 nm to 850 nm. We suggest that the combination of high cavity quality factor (Q) and low whispering gallery mode volume

serves to significantly enhance the probability of excited state absorption by enhancing the pump intensity within the microsphere. This is reflected in the fact that a large number of the observed transitions are likely the result of 3- and 4-photon absorption events for what is a relatively modest (sub mW) pump power coupled into the microsphere. The emission line centered at 318 nm (T1) is most likely a 4-photon process populating the $^2P_{3/2}$ state, which in turn radiatively relaxes to the $^4I_{15/2}$ ground state. Three pump photons populate the $^2G_{7/2}$ state. The $^2G_{7/2}$ – $^2P_{3/2}$ energy gap of $\sim 3600 \text{ cm}^{-1}$ combined with a phonon energy of 650 cm^{-1} is such that the $^2P_{3/2}$ state is unlikely to be populated by energy transfer processes e.g. thermalization and as such we suggest the absorption of a fourth pump photon is necessary to explain T1. This transition has previously been reported in Er^{3+} -doped glass but was identified as a 3-photon process following pumping at 637 nm.¹⁵ The same authors also reported emissions corresponding to the transitions T3, T4, T7 and T9. Transition T1 has also been reported¹⁶ in an Yb^{3+} - Er^{3+} co-doped material although in that case the excitation process involved successive energy transfers from Yb^{3+} . It should be noted that this is very different from our work which involves a single dopant, does not rely on a sensitizer ion and in which ETU does not play a major role due to the low dopant concentration. The transitions $^2P_{3/2} \rightarrow ^4I_{13/2}$ (T3) and $^2P_{3/2} \rightarrow ^4I_{11/2}$ (T4) are also thought to involve 4-photon excitation. Xu and Jiang¹⁷ have observed transitions T1, T3 and T4 following pumping at 545 nm. Transitions T6, T7, T12 and T13 have been reported following 980 nm pumping.¹⁸ The ultra-violet line at 383 nm (T2) and the 492 nm emission (T5) have been reported under 973 nm excitation.¹⁹ Arahira *et al.*²⁰ observed Er^{3+} emission at 700 nm and have attributed it to the transition $^4F_{7/2} \rightarrow ^4I_{13/2}$ following absorption of three pump photons at 1480 nm. We presume this assignment was on the basis of the 3-photon resonance $^4F_{7/2} \rightarrow ^4I_{15/2}$. We have also observed emission about 700 nm (T11) but propose it to follow the transition $^2H_{9/2} \rightarrow ^4I_{11/2}$ based on the

observed intensity ratio compared with the branching ratios calculated from Judd-Ofelt theory.²¹ Finally we have observed emissions centered at 618 nm (T8) and 667 nm (T10). We are presently unaware of other reports on such emissions from Er^{3+} .

In conclusion, we have demonstrated an all taper coupled multiwavelength upconversion microsphere light source and proposed the Er^{3+} transitions involved. We have used tapered optical fibers to both pump the microsphere and collect the resulting upconversion and C-band lasing emissions. We believe this to be the first use of fiber tapers to outcouple such a broad range of wavelengths from a microspherical light source and that this device could find many uses as a miniature all fiber multicolor light source.

This work is funded by Science Foundation Ireland under grant 02/IN1/128. D. O'Shea acknowledges support from IRCSET through the Embark Initiative RS/2005/156. B. Shortt's e-mail address is brian.shortt@cit.ie.

References

1. M. Cai, O. Painter, and K. J. Vahala, *Opt. Lett.* **25**, 1430 (2000).
2. F. Lissillour, D. Messenger, G. Stéphan, and P. Féron, *Opt. Lett.* **26**, 1051 (2001).
3. M. L. Gorodetsky, A. A. Savchenkov, and V. S. Ilchenko, *Opt. Lett.* **21**, 453 (1996).
4. M-F. Joubert, *Opt. Mat.* **11**, 181 (1999).
5. J. P. van der Ziel, F. W. Ostermayer, and L. G. Van Uitert, *Phys. Rev. B* **2**, 4432 (1970).
6. R. Rolli, M. Montagna, A. Chiasera, G. C. Righini, S. Pelli, A. Jha, V.K. Tikhomirov, S.A. Tikhomirova, A. Monteil, S. Chaussedent, and M. Ferrari, *Phil. Mag. B* **82**, 573 (2002).

7. T. Catunda, L. A. O. Nunes, A. Florez, Y. Messaddeq, and M. A. Aegerter, Phys. Rev. B. **53**, 6065 (1996).
8. M. D. Shinn, W. A. Sibley, M. G. Drexhage, and R. N. Brown, Phys. Rev. B. **27**, 6635 (1983).
9. D. S. Funk and J. G. Eden, IEE J. Sel. Top. Quant. Elec. **1**, 784 (1995).
10. M. Mortier, P. Goldner, P. Féron, G. M. Stephan, H. Xu, and Z. Cai, J. Non-Crys. Sol. **326&327**, 505 (2003).
11. B. J. Shortt, J. Ward, D. O'Shea, and S. Nic Chormaic, Proc. SPIE **6187**, 618708 (2006).
12. J. M. Ward, D. G. O'Shea, B. J. Shortt, M. J. Morrissey, K. Deasy, and S. G. Nic Chormaic, Rev. Sci. Instrum. **77**, 083105 (2006).
13. J. C. Knight, G. Cheung, F. Jacques, and T. A. Birks, Opt. Lett. **22**, 1129 (1997).
14. H. Fujiwara and K. Sasaki, J. Appl. Phys. **86**, 2385 (1999).
15. C. L. Pope, B. R. Reddy, and S. K. Nash-Stevenson, Opt. Lett. **22**, 295 (1997).
16. L. F. Johnson, J. E. Geusic, H. J. Guggenheim, T. Kushida, S. Singh, and L. G. van Uitert, Appl. Phys. Lett. **15**, 48 (1969).
17. H. Xu, and Z. Jiang, Phys. Rev. B. **66**, 035103-1 (2002).
18. F. Vetrone, J-C. Boyer, J. A. Capobianco, A. Speghini, and M. Bettinelli, Appl. Phys. Lett. **80**, 1752 (2002).
19. A. Biswas, G. S. Maciel, C. S. Friend, and P. N. Prasad, J. Non-Crys. Sol. **316**, 393 (2003).
20. S. Arahira, K. Watanabe, K. Shinozaki, and Y. Ogawa, Opt. Lett. **17**, 1679 (1992).
21. A. Florez, Y. Messaddeq, O.L. Malta, and M.A. Aegerter, J. Alloys Compounds **227**, 135 (1995).

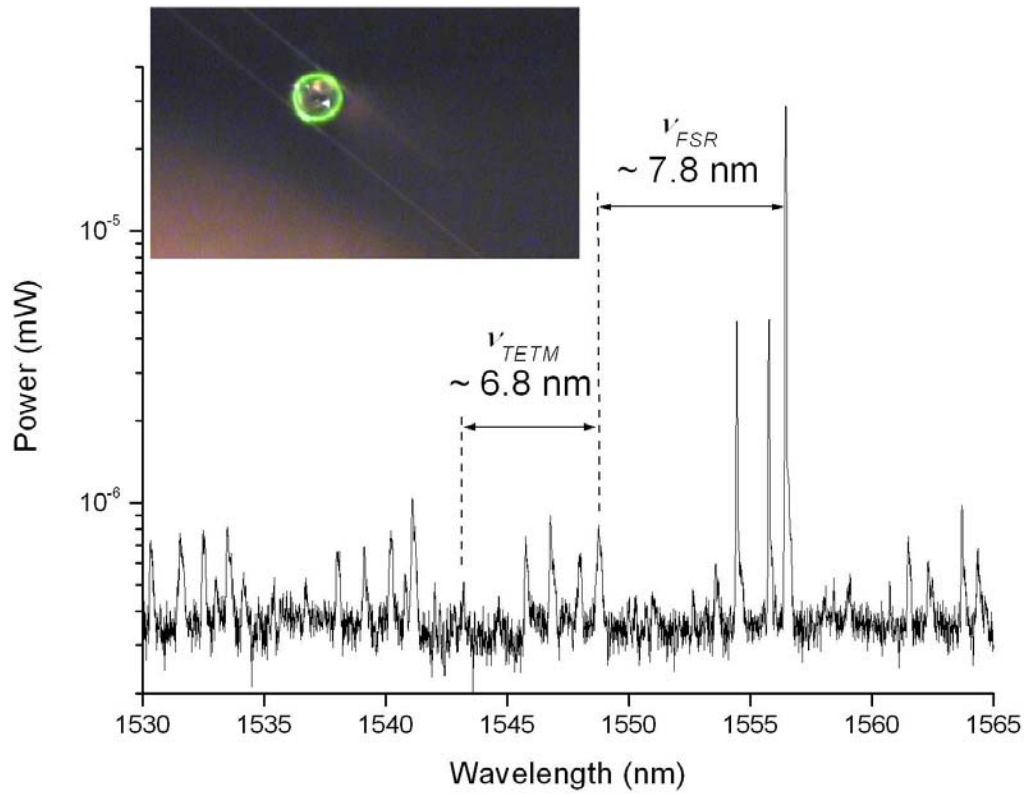


Fig. 1. 66 μm diameter microsphere lasing spectrum about 1550 nm showing whispering gallery mode structure. Inset: microsphere with pump full taper (bottom) and upconversion outcoupling half taper (top).

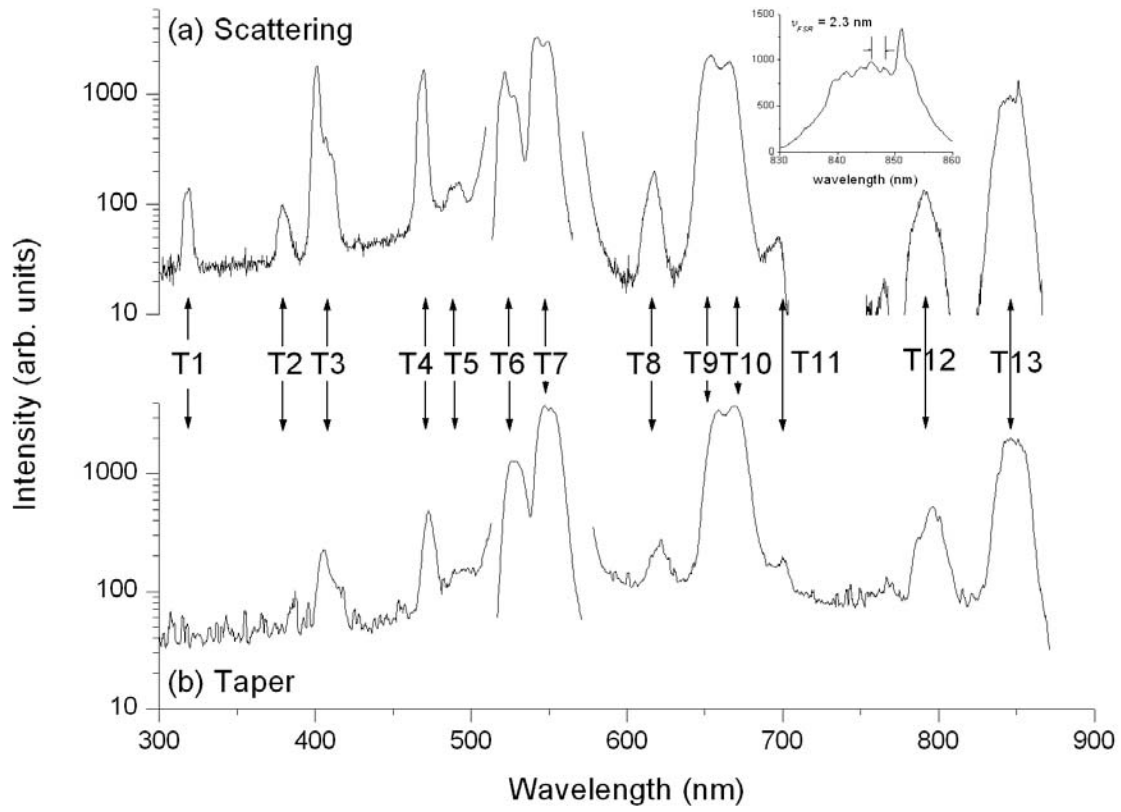


Fig. 2. Er:ZBLALiP microsphere upconversion spectrum with (a) scattering and (b) fiber taper detection schemes. The spectrometer integration time was reduced by a factor of 40 about the green transitions T6 and T7. Inset: whispering gallery mode structure about T13.

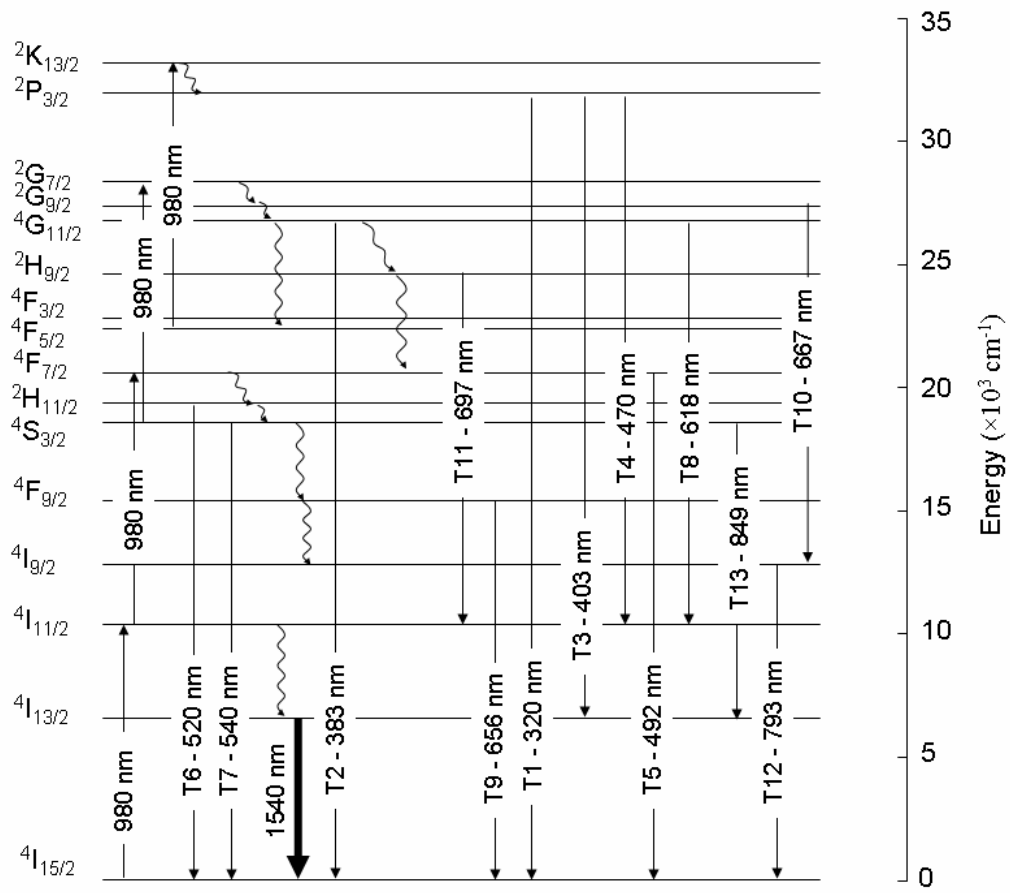


Fig. 3. Erbium energy level diagram with radiative (solid lines) and non-radiative transitions. The thick line indicates C-band lasing transition.